

# **LEARNING MATERIAL**

**SEMESTER & BRANCH : 6<sup>th</sup> SEMESTER CIVIL ENGINEERING**

**THEORY SUBJECT : CONCRETE TECHNOLOGY (TH – 4)**

**NAME OF THE FACULTY : ER. NANDINI PRADHAN**

20  
27-04-2021  
Chapter-1

# Concrete Technology

Cement + Sand + Aggregate

↓  
Fine aggregate      ↓  
Coarse aggregate

Mixing → Characteristic strength

- Concrete is the most widely used man made construction material in the world.
- It is obtained by mixing cementing materials & some times admixtures in required proportion. The mixture when placed in forms & allowed to cure, hardens into a rock like mass i.e. known as concrete.
- The hardening is caused by chemical reaction occur between water & cement & it continues a long time.
- The strength, durability & other characteristics of concrete depends upon the properties of its ingredients used in the mixture.

## # Grades of concrete:

- Concrete is generally graded according to the compressive strength.
- The various grade of concrete are mentioned in IS 456-2000 & IS 1343-1980.
- In the designation of concrete mix the letter 'M' refers to the mix design & the number of specified characteristic strength of 150mm cubes at 28 days expressed in MPa (N/mm<sup>2</sup>).
- The concrete of grade M5 / M7.5 is suitable for simple foundations, foundations for

masonry walls & other simple & temporary reinforcement concrete construction.

→ The concrete of grade lower than  $M_{15}$  is not suitable for reinforced concrete work.

→ The concrete of grade lower than  $M_{20}$  is not suitable for prestressed concrete work.

06-28-09-2

Group	Ordinary concrete			Standard concrete						High strength concrete					
Grade designation	$M_{10}$	$M_{15}$	$M_{20}$	$M_{25}$	$M_{30}$	$M_{35}$	$M_{40}$	$M_{45}$	$M_{50}$	$M_{55}$	$M_{60}$	$M_{65}$	$M_{70}$	$M_{75}$	$M_{80}$
Specified characteristic strength at 28 days (N/mm <sup>2</sup> )	10	15	20	25	30	35	40	45	50	55	60	65	70	75	80
Mix proportion	1:3:6	1:2:4	1:1.5:3	1:1:2	Design mix										

Note -

$M_5 = 1:5:10$

$M_{7.5} = 1:4:8$

Uses of concrete grade:-

A)  $M_5, M_{10}, M_{15}$  → These are used for plain concrete work such as leveling course, bedding for footing etc.

B)  $M_{25}, M_{30}, M_{35} \rightarrow$  These are used for RCC (Reinforced cement concrete) like floors, footings, columns, beams, slab etc.

C)  $M_{40} \rightarrow$  This is used for prestressed concrete work (slabs, beams, column, footing etc).

D)  $M_{45}, M_{50} \rightarrow$  These are used for RCC, runways, concrete roads, prestressed concrete girder, RCC-column, prestressed beam.

E)  $M_{55} \rightarrow$  This is used for prestressed concrete girder / pier.

F)  $M_{60}, M_{65}, M_{70}, M_{75} \rightarrow$  These are used for RCC work where high compressive strength is required such as high rise building, long span bridge, dam, coastal construction etc.

\* Advantages of concrete:—

1. Concrete is economical in the long run as compared to other engineering material.
2. Concrete possesses a high compressive strength & the corrosive & weathering effects are minimal.
3. The newly mixed concrete can be easily handled, moulded & formed in any shape @ size.
4. It is ~~the~~ strong in compression & has unlimited structural applications - in combination with steel reinforcement.
5. Concrete can even be sprayed on & filled into fine cracks for repairs.

6. Concrete can be pumped & hence it can be laid in difficult positions.

7. It is durable, fire resistant & requires very little maintenance.

\* Advantages of concrete:-

> The following are the disadvantages of concrete:-

(i) Concrete has low tensile strength; hence cracks easily. Therefore concrete is reinforced with steel bars (ii) mixture of steel bars.

(iii) Fresh concrete shrinks on drying & hardened concrete expands on wetting.

(iv) Concrete expands & contracts with the change in temperature. Hence expansion joints have to be provided to avoid the formation of cracks due to thermal movement.

(v) Concrete under sustained loading undergoes creep, resulting in the reduction of prestress in the prestressed concrete construction.

(vi) Concrete is entirely impervious to moisture & contains soluble salts which may cause efflorescence.

\* Properties of concrete:-

> Concrete making is not just a matter of mixing ingredients to produce a plastic mass, but good concrete has to satisfy performance requirement in the plastic state.

- In the plastic state, the concrete should be workable & free from bleeding & segregation.
- Segregation is the separation of coarse aggregate from concrete & bleeding is the separation of cement paste from concrete.
- Segregation & bleeding result in poor quality concrete.
- The hardened concrete should be strong, durable & impermeable.
- Among all the properties of concrete, the compressive strength is considered to be most important.

## Chapter - II

## Cement

pt. 30 DV. 2

→ cement is a building material which is used in construction work.

→ The cement commonly used is portland cement.


→ The mixture of cement, sand & water is known as cement mortar.

→ When aggregate is added to this paste it is converted to concrete.

→ The ingredients of concrete can be classified into two groups - i.e. active & inactive.


→ The active group consists of cement/binder, whereas the inactive group comprises fine & coarse aggregate.

\* Cement compounds :-

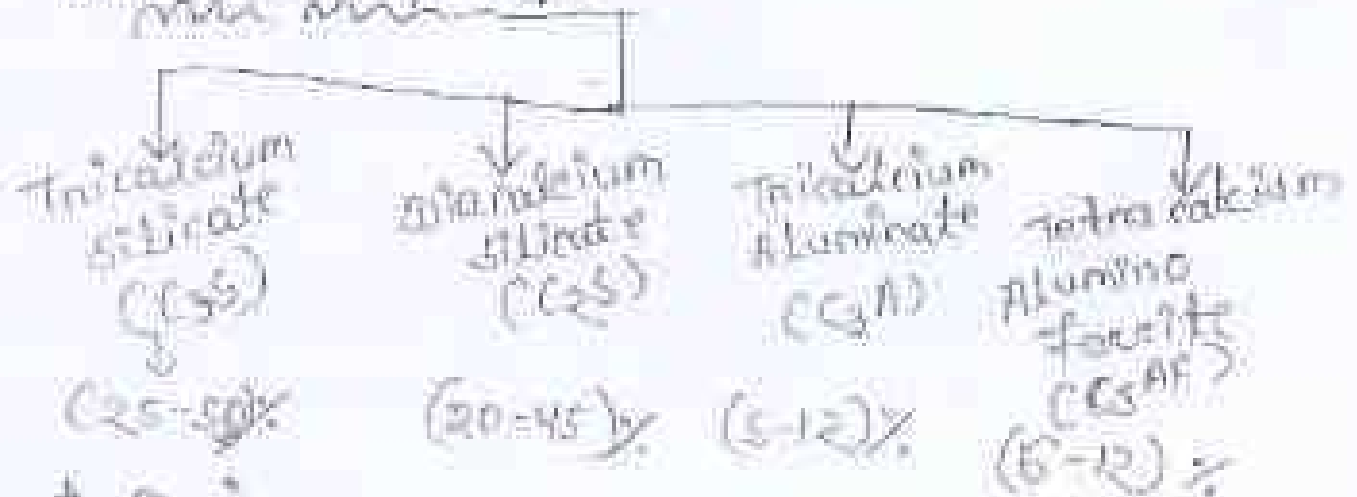

at Basic pos.

## \* Basic properties of cement compounds

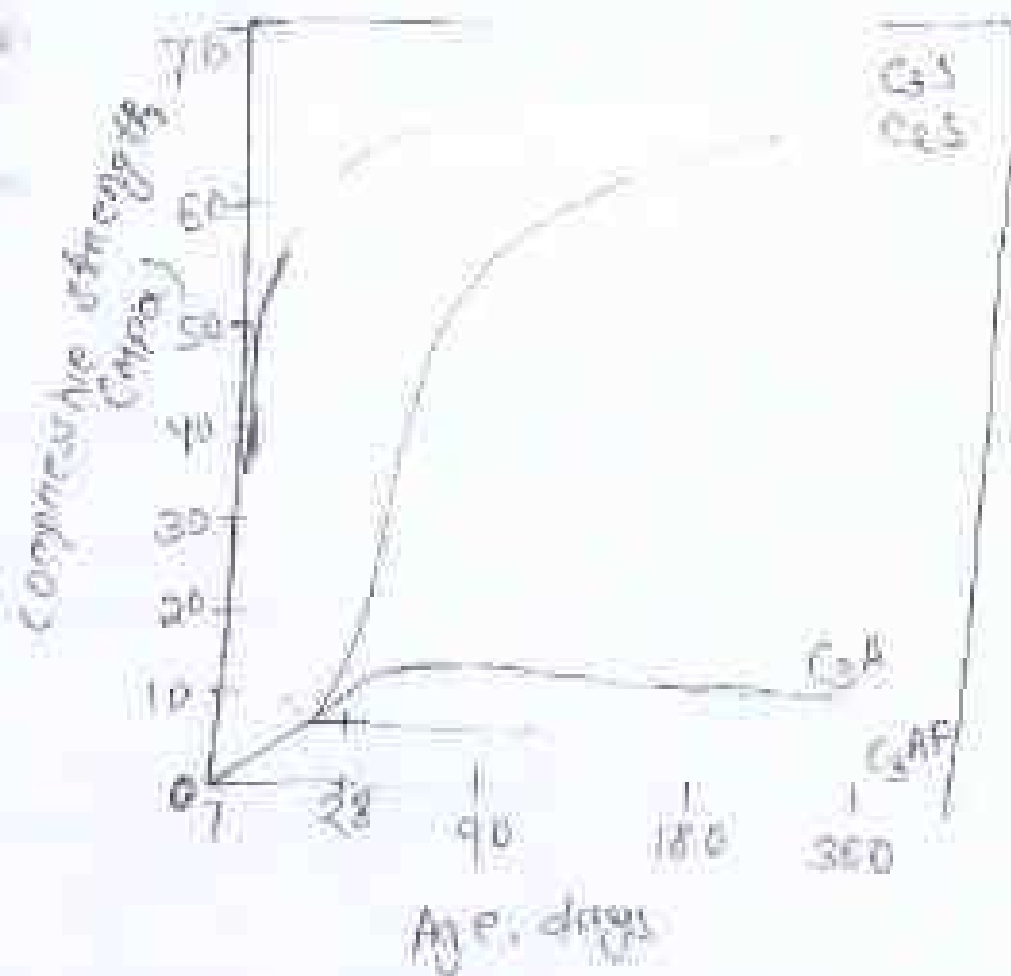



01-05-2021  
summary

- The two silicates namely  $C_3S$  &  $C_2S$  which together constitute about 70-80% of the cement, control the most of the strength giving properties.
- Upon hydration both  $C_3S$  &  $C_2S$  give the same product called calcium silicate hydrate ( $C_3S_2H_8$ ) & calcium hydroxide ( $Ca(OH)_2$ ) having a faster rate of reaction accompanied by greater heat evolution, develops early strength.
- On the other hand dicalcium silicate ( $C_2S$ ) hydrates & hardens slowly & provides much of the ultimate strength.
- It is likely that both  $C_3S$  &  $C_2S$  contribute equally to the eventual strength of the cement.
- $C_3S$  &  $C_2S$  need approximately 24-25 percent by weight of water.
- For chemical reaction  $C_3S$  liberates nearly three times as much calcium hydroxide on hydration as  $C_2S$ .
- $C_2S$  provides more resistance to chemical attack.
- Thus a higher percentage of  $C_3S$  provides  $C_2S$  results in rapid hardening with a faster gain in strength at a higher

## heat of hydration

→ On the other hand a higher percentage of  $C_3S$  results in low hardening, less heat of hydration & greater resistance to chemical attack.

→ The compound tricalcium aluminate ( $C_3A$ ) is characteristically fast reacting with water & may lead to an immediate stiffening of paste & this process is known as flash set.

→ The rate of gypsum added in the manufacture of cement is to prevent such a fast action.

→  $C_3A$  needs with 40% of water by mass & this is more than that required for  $C_3S$  hydration.

→ However, the amount of  $C_3A$  in cement is comparatively small; the net water required for the hydration of cement is not sufficient & is not affected.

→ It provides weak resistance against sulphate attack & its contribution to the development of strength of cement is perhaps less significant than the silicates.

→ In addition the  $C_3A$  is responsible for the highest heat of evolution, both in the initial period & in the long run.

→ Like  $C_3A$ ,  $C_3AF$  hydrates rapidly but its individual contribution to the

overall strength of cement is insignificant. However  $C_3A$  is more stable than  $C_2A$ .

→ In terms of oxide composition, a high lime content generally increases the setting time & results in higher strength.

→ A decrease in lime content reduces the strength of concrete.

→ A high silica content prolongs the setting time & gives more strength.

→ The presence of excess unburnt lime is harmful, since it results in delayed hydration causing expansion & unsoundness.

→ Iron oxide is not a very active constituent of cement & generally acts as a catalyst & helps the burning process.

→ The presence of iron oxide derives the cement grey in colour.

→ Magnesia, if present in large quantity, then it leads to unsoundness.

## Hydration of cements

→ The extent of hydration of cement and the resultant micro structure of fully hydrated cement influences the physical properties of concrete.

The microstructure of hydrated cement is more or less similar to silicate phases. When the cement comes in contact with water, the hydration of cement proceeds in inward and out ward in the sense that the unhydration products get deposited on the outer periphery and the nucleus of unhydrated cement inside gets gradually diminished in volume.

→ This reaction proceeds slowly for 2-5 hours (called induction or dormant period) before according accelerating as the surface skin breaks.

→ At any stage of hydration having, the concrete paste consist of gel (a finely grained product of hydration having large surface area collectively called gel) the remnant of unreacted cement, silicon hydroxide ( $\text{CaOH}_2$ ) and water, besides some other minor compound.

→ The crystals of various resulting compound from water taking random place a 3 dimensional network gradually filling the space originally occupied by the

water, resulting in stiffening and subsequent development of strength as shown in accordingly. The hardened cement paste has a porous structure the pore size varying from very small ( $4 \times 10^{-6}$  cm) to a much larger value, the pores being called gel pores and capillary pores, respectively.

→ The pore system inside the hardened cement paste may or may not be continuous.

→ As the hydration proceeds the deposit of hydration products on the original cement grain makes the diffusion of water to unhydrated nucleus more and more difficult thus reducing the rate of hydration with time.

The reactions compounds of cement and their products may be represented symbolically.



or symbolically.



Reactions in the presence of gypsum are.



(Initial state hydration)



(Monosulfate hydrate)  
The above equations (with  $C = CaO$ ,  $S = SiO_2$  and  $H = H_2O$ ) only refer to the process in which the cement compounds react with water to form colloidal dimensions (less than 2  $\mu m$ ) to 1  $\mu m$  or more.

The calcium hydroxide ( $Ca(OH)_2$ ) liberated during the reaction of silicate hydrate phase crystallizes in the available free space. The product  $C_3S_2H_3$  representing calcium silicate hydrate, a gel structure, is normally expressed by hyphenation  $C-S-H$ , which signifies that it is not a well-defined compound.

The simplistic scanning-electron micrograph of hydration of cement.

The hydration of  $C_3S$  produces a comparatively lesser quantity of  $C-S-H$  than that produced by  $C_2S$ . On the other hand,  $C_3S$  liberates nearly three times as much calcium hydroxide on hydration as  $C_2S$ . However,  $Ca(OH)_2$  is not a desirable product in the concrete mass as it is soluble in water and gets leached out making the concrete porous.

The only advantage of  $Ca(OH)_2$  is its being alkaline in nature and maintaining a pH value of around 13. In the concrete, a pH value at this level passivates reinforcing steel against corrosion. In general, the quality and density of  $C-S-H$  produced due to hydration of  $C_2S$  is slightly inferior to that formed by hydration of  $C_3S$ . The hydration product  $C_2S$  is rather dense and its specific surface is higher.

On hydration of C<sub>3</sub>A a calcium aluminate system  $\text{CaO} \cdot \text{Al}_2\text{O}_3 \cdot \text{H}_2\text{O}$  is formed. The cubic compound C<sub>3</sub>AH<sub>6</sub> is probably the only stable product.

→ Hydration of C<sub>3</sub>AH<sub>6</sub> is believed to form a system  $\text{CaO} \cdot \text{Fe}_2\text{O}_3 \cdot \text{H}_2\text{O}$ . A hydrated calcium ferrate of the form C<sub>3</sub>FH<sub>6</sub> is comparatively more stable. In the presence of gypsum depending upon the concentration of aluminate and sulfate ions in the solution phase, the precipitating crystalline product is either calcium aluminate trisulfate hydrate ( $\text{C}_3\text{S}_3\text{H}_2$ ) or calcium aluminate monosulfate hydrate. The product calcium aluminate trisulfate hydrate is effective, which crystallizes as short prismatic needles on account of high sulfate aluminate molar ratio in the solution phase during first hour of hydration when sulfate solution gets depleted, aluminate ions concentration increases due to renewed hydration and the aluminate is gradually converted into monosulfate which is the final product of hydration of Portland cement containing more than five percent C<sub>3</sub>A.

### Rate of Hydration:

→ As mentioned earlier, the reaction of the compound C<sub>3</sub>A with water is very fast so that flash setting i.e. setting without strength development can occur because the C-A-H phase prevents the

Hydration of  $C_2S$  and  $C_3S$ . However, some of the  $C_3A$  present in the clinker dissolves immediately in water and the sulfate ions in the solution react with some of them to form insoluble calcium sulfaluminate, which deposits on the surface of the  $C_3A$  to form a protective colloidal membrane and thus retards the direct hydration reaction.

When all the surface is consumed, hydration can accelerate. The amount of ~~moist~~ sulfate must, therefore, be carefully controlled to leave a little excess  $C_3A$  to hydrate directly.

The hardening of  $C_3S$  appears to be catalyzed by  $C_3A$  so that  $C_3S$  becomes almost solely responsible for the gain of strength up to about 28 days by growth and interlocking of C-S-H gel.

→ The later age increase in strength is due to the hydration of  $C_2S$ . The rate of strength development can, therefore, be modified by changes in the relative quantities of these compounds.

### Mechanism of Hydration

→  $C_3A$  reacts from beneath the thin membrane of calcium sulfaluminate formed on the  $C_3A$  surface.

→ Owing to the larger volume of calcium sulfaluminate pressure develops and the membrane eventually bursts, allowing the sulfate in solution to come in contact with unreacted  $C_3A$  to reform the membrane.

→ The cycle process continues until all the sulfate in solution is consumed whereupon the  $C_3A$  can



Hydrate directly at a faster rate and the hydration of calcium sulfaluminate into needle like monosulfate crystals leads to the loss of workability and to setting.

→ This gives rise to the induction period which ends when the protective membrane is disrupted.

→ Although the reaction between  $C_3S$  and water proceeds at the same time in a properly retarded cement.

→ The end of induction period of  $C_3S$  hydration coincides with the point at which the sulfate in solution is no longer available for reaction. Setting now, is due to the simultaneous growth of aluminate hydrate, monosulfate and silicate hydrate in the inter-particle space.

→ The above theory is termed as protective membrane hydration.

Effect of admixtures on hydration:

→ Some admixtures may reduce the electric repulsion between the individual positively charged hydrating cement particles so that they approach closer and stick to form agglomerates which grow and eventually settle out.

→ This process is termed flocculation and the agglomerates floc.

→ The anions may flocculate the colloidal membrane thus making more permeable.

\* Abraham's Law:- Water to cement and compressive strength;

Amount of average composition requires about 25% of water mass for chemical reaction.

In addition, an amount of water is needed to fill the gel pores.

Nearly 100 years ago, Gull Abram discovered the direct relationship between water to cement ratio and strength. That is lower the water used, higher the strength of concrete, since too much water leaves lots of pores in the cement paste.

→ According to Abraham's Law, the strength of fully compacted concrete at a given age and normal temperature is inversely proportional to the water cement ratio.

→ Here the water-cement-ratio is the relative weight of the water to the cement in the mixture.

→ For most applications, water-to-cement should be bet<sup>n</sup> 0.4 and 0.5, lower for lower permeability and higher strength.

→ In concrete lower water content results in very stiff concrete that are difficult to place.

→ The water to cement ratio is selected by engineer according to the requirement of place.

\* Physical properties of portland cement:-



→ The cement to be used in construction must have certain given qualities in order to play its part effectively in a structure.

→ When these properties lie within a certain range then the cement performance will be satisfactory.

→ Also based on these properties it is possible to compare the quality of cement from different sources.

→ The important physical properties of a cement are :-

1) Fineness :-

→ The fineness of cement is a measure of the size of particles of cement & is expressed in terms of specific surface area of cement.

→ It can be calculated by particle size distribution.

→ It is an important factor in determining the rate of gain of strength & uniformity of quality.

→ For a given weight of cement the surface area is more for a finer cement than a coarser cement.

→ Finer the cement, the higher the rate of hydration, as more surface area is available for chemical reaction.

→ This results in early development of strength.

→ If the cement is ground beyond the certain limit its cementation properties may be adversely affected due to prehydration by atmospheric moisture.

→ As per Indian standard specifications the residue of cement should not exceed 10% when sieved

It is sieve.

Setting time:-

Cement when mixed with water forms paste which gradually becomes less plastic & finally a hard mass is obtained.

In this process the setting stage is reached when the cement paste is sufficiently rigid to withstand a definite amount of pressure.

→ The time to reach this stage is known as setting time.

→ The time at which the cement paste loses its plasticity is termed as initial setting time.

→ The time taken to reach the stage when the paste becomes a hard mass is known as final setting time.

It is essential for proper concreting that the initial setting time be sufficiently long for finishing operations i.e. transpounding / placing the concrete.

→ The setting time decreases with the rise in temperature upto  $30^{\circ}\text{C}$  & vice-versa.

→ For an ordinary Portland cement the initial setting time should not be less than 30 minutes & final setting time should not be more than 600 min (10 hrs).

→ A phenomenon of abnormal premature hardening with in a few minutes of mixing the water is termed as flash set.

3- Soundness:-

The unsoundness of cement is caused by the undesirable expansion of some of its constituents sometimes after setting.

→ The large change in volume results in disintegration / severe cracking

→ The unsoundness is due to the presence of lime & magnesia.

→ The free lime hydrates very slowly because it is covered by the thin film of cement which prevents direct contact between lime & water.

→ After the setting time, the moisture penetrates very slowly into the free lime resulting in its hydration.

→ The unsoundness of cement may be reduced by:-

a) Limiting the  $MgO$  (Magnesia) content to less than


0.5%.

b) Fine grinding.

c) thorough mixing.

→ The chest test for soundness is done by Le-Chatelier in lab.

→ The expansion carried out in the manner described in IS 269-1989 should not be more than 10 mm in Le-Chatelier test.

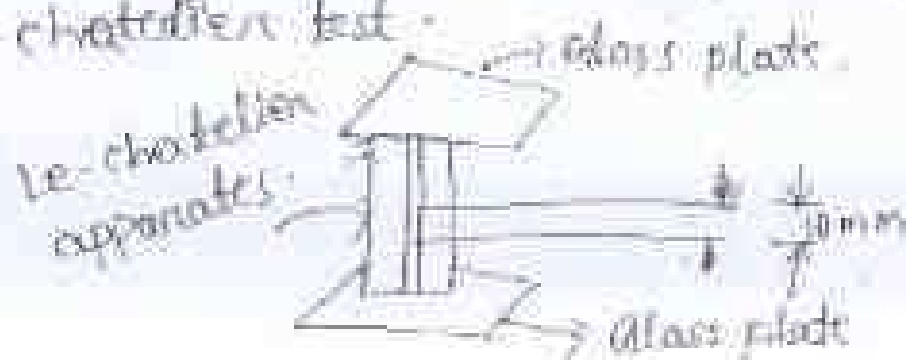

## Compressive strength :-

- It is one of the important properties of cement.
- The strength test is generally carried out in compression on samples.
- To measure the strength of concrete crushing test and compressive strength test should be done.
- These are conducted on standardised aggregates under carefully controlled conditions and then they give a good indication on strength quality of cement.
- Cement mortar cubes (1:3) having an area of  $500\text{mm}^2$  are prepared and tested in compression testing machine.
- For ordinary portland cement the value of compressive strength for 3 days and 7 days should not exceed  $16\text{mpa}$  and  $22\text{mpa}$ .
- The compressive strength test should be done in 3 days, 7 days and 28 days by using either universal testing machine (or) compressive test machine.
- The grade that are used for making the concrete should be mentioned in IS 650:1991 and IS 456:2000.

## Standard sand:-

A particular variety of sand available at Erode in Tamil Nadu is used as standard sand which closely resembles the Leighton Buzzard sand (the British standard sand) in its properties.

The imported Leighton sand has been replaced by Ennore sand. The standard sand has following properties.

- a) The standard sand shall be of quartz, of light gray or whitish variety and shall be free from silt.
- b) The sand grains shall be angular with shape approximating to spherical forms.
- c) The sand shall pass through IS: 850 -  $\mu\text{m}$  sieve and not more than 10 percent shall pass through IS: 600 -  $\mu\text{m}$  sieve.
- d) It shall be free from organic impurities.

5. Heat of hydration :-  
on minimum :-

- The silicates and aluminates of cement react with water to form a binding medium, which solidifies into a hardened mass.
- This reaction is termed hydration, which is exothermic with approximately 120 cal/g heat being liberated. In the interior of mass concrete constructions like dams etc, the temperature can be as high as  $50^{\circ}\text{C}$  above the initial temperature of concrete mass at the time of placing the concrete.
- This high temperature is found to persist for for a prolonged period. At the same time, the exterior of the concrete mass loses some heat so that a steep temperature gradient may be established, and during the subsequent cooling of the interior, severe cracking may occur.

On the other hand, the heat of hydration may be advantageous in preventing the freezing of water in the capillaries of freshly placed concrete in cold weather.

The heat of hydration is defined as the quantity of heat, in calories per gram of hydrates cement liberates on complete hydration at a given temperature. The different com

The different cement compounds hydrate at different rates and liberate different quantities of heat. On adding water to cement, a rapid heat evolution lasting for few minutes is due to reaction of aluminates.

However, this initial heat evolution ceases quickly as solubility of aluminates is restricted by  $\text{Ca}(\text{OH})_2$ .

The total heat generated in the complete hydration process will depend upon the relative quantities of major compounds of cement.

A normal cement generally produces approximately 70 cal/g of heat in 7 days and 90 to 100 cal/g in 28 days.

It is determined by measuring the quantities of heat liberated by unhydrated and hydrated cements in a mixture of nitric and hydrofluoric acids; the difference between the two values represents the heat of hydration.

The heat of hydration of low-heat Portland cement should not be more than 25 and 75 cal/g at 7 and 28 days, respectively.

The heat of hydration increases with



place.

→ For ordinary Portland cement (OPC) it varies from 37 cal/g at 5°C to 80 cal/g at 40°C. For common types of Portland cements, about 60 per cent of the total heat is liberated between 1 and 3 days about 75 percent in 7 days and 83 to 91 percent in six months.

→ By restricting the quantities of compounds  $C_3A$  and  $C_3S$  in cement, the high rate of heat liberation increases with the fineness of cement but the total amount of heat liberated is unaffected by the fineness.

6. Specific gravity:-

→ The specific gravity of Portland cement is generally about 3 but that of cement manufactured from materials other than limestone and clay, the value may vary. → Specific gravity is not an indication of the quality of cement. It is used in calculation of mix proportions.

\* Guide composition of ordinary Portland cement:-

Oxide	Percentage	Average
(1) Lime ( $CaO$ )	60-75	63
(2) Silica ( $SiO_2$ )	17-25	20
(3) Alumina ( $Al_2O_3$ )	3-5-9	6.3
(4) Iron oxide ( $Fe_2O_3$ )	0.5-6	3.3

oxide (Mg) Magnesia (MgO)	0.5 - 4	2.4
(6) Sulphur trioxide (SO <sub>3</sub> )	1 - 2	1.5
(7) Alkali that is soda / Potash	0.5 - 1.3	1.0

### \* Types of cement :-

→ By using additives, changing the chemical composition of the Portland cement by varying the percentage of four compounds that are present in the cement it is possible to obtain various type of cement.

→ A gradual increase of G.S. content and fineness has enabled general purpose of Portland cement to develop very high strength at early ages.

→ Following are the main types of Portland cement:-

- (1) Ordinary Portland cement OPC.
- (2) Non-OPC cement.

### \* General purpose of Portland cement:-

The commonly used Portland cement in India is known as 33-grade (IS: 269-1987), 43-grade (IS: 812-1989) and 53-grade (IS: 12269-1987) having 28 days mean compressive strength cured in 33 MPa.

43 MPa and 53 MPa respectively.

→ All the three grades of ordinary Portland cement are produced from the same materials as explained earlier.

→ The higher strengths are achieved by increasing the tricalcium silicate ( $C_3S$ ) content and also by finer grinding of the clinker.

→ The fineness of 53 grade cement obtained by Blaine's air permeability test is specified to be of the order of  $35000 \text{ m}^2/\text{kg}$ .

→ The requirements of the initial and final setting times are same as that of conventional OPC.

→ The conventional OPC, i.e. 22 grade cement has virtually disappeared and has been displaced by high strength 43 grade cement. The minimum compressive strengths of the 43 grade cement are 22 MPa and 32 MPa at the end of three days and seven days, respectively.

→ The use of this cement was originally restricted to the production of railway sleepers and generally referred to as sleeper cement.

→ The railway specifications require that the initial setting time should not be less than 90 minutes.

→ At higher water cement ratios, the concrete produced with high-strength cement has about 80 percent higher strength and a lower

Since cement nodules, it has 40 percent higher strength than that of concrete using 33-grade OPC.

The cost of high-strength Portland cement is only marginally higher than the OPC.

The use of this cement in the usual 1:2:4 nominal mix, with a water-cement ratio of 0.60 to 0.65 can heavily yield M25 concrete.

Its composition and properties are governed by IS: 2112-1989. Greater fineness of 43 and 53 grade cements increase workability due to reduction of friction between aggregates.

Moreover, due to shorter setting time and faster development of strength, the stripping time is shorter.

Although cement of grades 43 and 53 are desirable for economical design of high-grade concrete but they can also be used for lower grade concretes. However, to make high-strength concrete a high-performance concrete, will require extremely careful batching, mixing, transportation, placing, compaction and curing.

IS: 10262-1982 has classified OPC grade as follows from A to F depending upon the 28 days compressive strength as: (i) A (32.5-37.5 MPa), (ii) B (37.5-42.5 MPa), (iii) C (42.5-47.5 MPa), (iv) D (47.5-52.5 MPa), (v) E (52.5-57.5 MPa), (vi) F (57.5-62.5 MPa). Accordingly, the 33, 43 and 53 grades of cement correspond to categories A, C and E, respectively.

However, most of the 13 grade cements available in the market generally fall in the category I and the 23 grade cements available are generally in the category F or above.

→ The actual strength of cement must be ascertained either from the manufacturer or through laboratory tests before it is used in concrete mix design to get the maximum benefit of the additional strength and superior quality.

Special-purpose cements:-

The special-purpose cements are manufactured for the specific performance requirements. The frequently used ones are the following.

1- OPC-based cements.

2- Non-OPC cements.

These cements have some further classifications, which are described below.

OPC-based cements

1- Rapid-hardening Portland cement:-

→ This cement is similar to OPC but with higher  $C_3S$  content and finer grinding.

→ A higher fineness of cement particles provides greater surface area not less than 32500  $\text{cm}^2/\text{g}$  in action with water.

→ It gains strength more quickly than OPC, though the final strength is only slightly higher.

The one-day strength of this cement is equal to the three-day strength of 33-grade OPC with the same water-cement ratio.

→ This cement is used where a rapid strength development is required. The rapid gain of strength is useful where a rapid strength development is required.

→ The rapid gain of strength is accompanied by a higher rate of heat development during the hydration of cement.

→ This may have advantages in cold weather concreting but a higher concrete temperature may lead to cracking due to subsequent thermal contraction, and hence should not be used in mass concreting of thick structural sections.

→ The composition, fineness and other properties are governed by IS: 8041-1990. It is only about 10 per cent costlier than OPC. It is recommended for prefabricated concrete constructions, road repairs and in applications requiring early stripping of forms.

2- Low-Heat Portland cement:-

→ This cement is less reactive than OPC and is obtained by increasing the proportion of  $C_2S$  and reducing  $C_3S$  and  $C_4A$ .

→ This reduction in the content of more rapidly hydrating compounds,  $C_3S$  and  $C_4A$  results in a slow development of strength but the ultimate strength is the same.

→ In any case, to ensure a sufficient rate of development of strength, the specific surface of cement must not be less than  $32000 \text{ mm}^2/\text{kg}$ .

→ The initial setting time is greater than OPC.

→ The properties and composition are governed by IS: 12600-1989.

→ This cement is recommended for the use in mass concrete construction such as where temperature rise by heat of hydration can become excessive.

### 3 - Sulfate-resisting cement:-

→ A portland cement with low  $C_3A$  (less than five percent) and  $C_4AF$  contents is very effective against sulfate attack. Such a cement having high silicate content is called sulfate-resisting cement.

→ The content of tetra-aluminoferite  $C_4AF$  in OPC varies between 6 to 12 percent.

→ As it is not feasible to reduce the  $Al_2O_3$  content of raw material,  $Fe_2O_3$  is added to the raw materials mixture to increase  $C_4AF$  content at the expense of  $C_3A$ .

→ IS: 456-2000 limits the total content of  $C_4AF$  and  $C_3A$  such that  $2C_3A + C_4AF$  shall not exceed 25 percent. Such a cement with low  $C_3A$  content is effective against sulfate attack whereas the ordinary Portland cement is susceptible to attack of sulfates in solution which contribute to the formation

concrete and react with free  $\text{Ca(OH)}_2$ , hydrate of calcium aluminate and even hydrated silicates to form calcium sulfoaluminate having a volume of approximately 227 percent of the volume of original aluminates. This expansion within the hardened structure of cement paste results in cracks and subsequent disruption.

➤ This phenomenon is called sulfate attack, which is greatly accelerated if accompanied by an alternate wetting and drying cycle as in the case of marine environment.

➤ The worst sulfate resisting cement is recommended for concretes to be used in the marine environment, foundations in chemically aggressive soils, for pipes to be buried in marshy regions or sulfate bearing soils, and construction of sewage treatment plants.

#### (4) Masonry cement:-

➤ This cement is manufactured by intimately grinding a mixture of OPC clinker and gypsum with mineral additives (pozzolanas) or inert (non-pozzolanic) materials such as: limestone, dolomite, carbonated etc. and air-entraining agents in suitable proportions generally to a fineness greater than that of OPC.

➤ Masonry cement conforming to the standard specification can be produced by intergrinding 3 parts of Portland cement clinker, 5 parts of fly ash and 5 parts of granulated blast furnace slag or 1 part of Portland cement clinker, 2 parts of fly ash and 2 parts of hydrated lime with suitable quantity of gypsum and an air-entraining admixture.



Masonry cement mortar is considered superior to plain mortar, lime-cement mortar and cement mortar.

It combines the desirable properties of cement mortar ~~and~~ relating to strength and setting, and lime mortar relating to workability and water retention.

Thus a masonry cement produces a smooth, plastic, cohesive and strong, yet workable mortar.

The cracks due to shrinkage and temperature movement are considerably reduced. Its properties and properties are governed by IS 3461-1968

The physical requirements of the masonry cement are:

#### A) Fineness

Residue on 45 micron sieve, max. 15 percent

#### B) Setting times

(i) Initial setting time, min. 90 minutes

(ii) Final setting time, max. 24 hours

#### C) Soundness

(i) Le-chatelier expansion, max. 15 mm

(ii) Autoclave expansion, max. 0.1 percent

The following properties are measured on the mortar composed of one part of masonry cement and three parts of standard sand by volume.

#### a) Compressive strength

(i) at 7 days, min. 25 MPa

(ii) at 28 days, min. 50 MPa

b) Air content, min. 6 percent

## Water-retention

flow after suction as compared to the original flow, min 50 percent

## Waterproof Portland cement:-

Waterproof cement is manufactured by adding a waterproofing substance to ordinary Portland cement during mixing.

The common admixtures are calcium stearate, aluminium stearate and the gypsum treated with lauric acid.

## White Portland cement:-

The process of manufacturing white cement is the same as of ordinary Portland cement but the amount of iron oxide, which is responsible for grayish colour, is limited to less than one percent.

→ This is achieved by careful selection of raw materials and often by the use of refined turn oil (CRO) or gas fuel in place of pulverized coal in the kiln.

→ The suitable raw materials are clark and high purity limestones having 95 percent  $\text{CaCO}_3$  and less than 0.1 percent iron oxide contents, and white clays.

→ Its composition and properties are governed by IS: 8042-1984. Generally white cement is finer than the gray cement.

## 7- Colored portland cement:-

- These are basically Portland cements to which pigments are added in quantities up to 10 per cent during the process of grinding the cement clinker.
- A good pigment should be permanent, i.e., colour should be durable under exposure to light and weather, and chemically inert when mixed with cement. For lighter colours, white cement has to be used as base.

## 8- Hydrophobic cement:-

- This type of cement is obtained by adding water repellent film forming substances like stearic acid, tallow oil, oleic acid and pentachlorophenol to clinker during grinding of cement clinker.
- These acids form a film around the cement particles which prevent the entry of atmospheric moisture, and the film breaks down when the concrete is mixed and then the normal hydration takes place.
- The film forming material also entrains certain amount of air in the body of concrete which improves its workability.
- Its composition and properties are governed by IS: 8043-1971.
- This cement is useful for the places having high humidity, poor transportation system and places damaged for long time. In such places, it does not deteriorate and loses strength.

part of its strength.

→ The physical and chemical requirements for some of the commonly used cements are summarized.

9. Air-entraining cement:-

→ This cement is manufactured by mixing small quantity of air-entraining agent like alkali salts of rosin, resins, synthetic detergents, alkyl aryl sulfates type and calcium lignosulfonate with ordinary Portland cement.

→ These agents in powder or in liquid form are added to the extent of 0.025 to 0.10 per cent by weight of OPC cement clinker at the time of grinding.

→ At the time of mixing, these cements produce fine, discrete non-coalescing air bubbles in the concrete mass which enhances workability and reduces tendency to segregation and bleeding.

10. Expansive cement:-

→ Cement which does not shrink while hardening and thereafter, but expands slightly with time is called expansive cement.

→ This cement does not suffer any volume change in volume on drying. Expansive cement is obtained by mixing about 8 to 20 parts of the sulfoaluminate with 100 parts of the OPC and 15 parts of the stabilizer.

→ In one type of expansive cement called shrinkage compensating cement, the neutralizer is the expansive

cement called shrinkage compensating cement, the restraint to the expansion induces compressive stress which approximately offsets the tensile stress induced by shrinkage.

→ In another type called self stressing cement, the concrete induces significant compressive stresses after the occurrence of drying shrinkage.

→ In addition to neutralizing the shrinkage they provide prestressing effect in the performance of a flexural member.

→ This cement is commonly used for grouting anchor bolts or grouting machine foundations on prestressed concrete ducts wherein drying shrinkage may otherwise defeat the purpose of grout.

## II Oil-well cement :-

→ The annular space between steel casing and surrounding rock foundation through which oil well has been drilled, is sealed off by cement slurry to prevent escape of oil or gas.

→ The cement slurry also seals off any other fissure or cavities in the rock layer. For this purpose cement slurry has to be pumped down to points located in the annulus around the casing, at considerable depth where prevailing temperature may be as high as  $250^{\circ}\text{C}$  under pressure up to 150 MPa.

→ The slurry used for this purpose must remain mobile to be able to flow under these conditions for periods up to several hours and then harden.

setting rapidly to give sufficient strength to support  
over-casting.

It may also have to resist corrosive conditions from  
sulfur gases and water containing dissolved salts.

The type of cement suitable for above conditions  
is called oil-well cement.

The cement produced by inter-grinding Portland  
cement clinker, fly ash, gypsum and certain other  
inert materials in suitable proportions has been  
found to conform to the requirements of an oil  
well cement.

These retarders prevent quick setting and avoid  
slurry in mobile condition of facilitate penetration  
to all facilitate penetration to all fissures and cavities.

The composition and properties are governed by IS: 1122  
1956.

Very high strength cements:

The cements of this category can be obtained by  
improving particle packing density and microstructure  
of cement paste as follows.

1. Removing entrapped air:

In the conventionally mixed cement paste and  
slurry large voids or defects are usually present  
due to entrapped air which limit the strength.

In one of the systems, water soluble polymer is used  
as rheological aid to permit cement to be mixed  
with a very small amount of water and at final  
mixing stage entrapped air is removed by  
application of vacuum pressure of 5 MPa.

4. This process has resulted in a strength of 300 MPa for calcium aluminate system and 500 MPa for OPC. This system is called macro-defect free cement.

2. Providing densely packed system:-

→ OPC and ultra fine silica fume (5 to 20 percent) are mixed to obtain a densified system containing homogeneously arranged particles.

→ A compressive strength of 270 MPa has been obtained with silica fume substituted paste.

3. Achieving densification with warm pressing:-

By the method of warm pressing i.e., applying heat and pressure simultaneously to cement paste results in reduction of porosity and generation of very homogeneous fine microstructure with small porosity.

→ By warm pressing of mixture of Portland and calcium cements has resulted in compressive strength of 650 MPa.

Non-OPC Cements:-

1. High-alumina cement:-

→ This cement is totally different from OPC and concrete made with it has properties different from OPC concrete.

→ High-alumina cement (HAC) is very reactive and produces a very high early strength.

→ About 80 percent of the ultimate strength is developed at the age of 24 hours and even at 6 or 8 hours.

High-alumina cement has an initial setting time of about four hours and the final setting time of about five hours. Generally no additives are added to alumina cement.

For the same water cement ratio, the alumina cement is more workable than Portland cement.

The strength is adversely affected by rise in temperature. H.A.C is extremely resistant to chemical attack and is suitable for under sea water applications.

The raw materials used for its manufacture are limestone or chalk and bauxite which are crushed into lumps not exceeding 100 mm.

These raw materials with appropriate proportion of coke are charged into the furnace which is fired with pulverised coal or oil.

The fusion takes place at temperature about  $1500^{\circ}\text{C}$ .

The solidified material is fragmented and then ground to a fineness of 25000-32000  $\text{cm}^2/\text{g}$ .

The very dark grey powder is passed through magnetic separators to remove metallic iron. The alumina cement is considerably more expensive.

The pozzolana additives are not useful in cement made with H.A.C because it does not produce calcium hydroxide that could react with pozzolanas.

Its composition and properties are governed by IS 4952-1969. The approximate chemical analysis is as follows.



Alumina ( $Al_2O_3$ )	39 percent
Ferric Oxide ( $Fe_2O_3$ )	10 percent
Lime ( $CaO$ )	31 percent
Ferrous Oxide ( $FeO$ )	4 percent
Silica ( $SiO_2$ )	6 percent

→ During hydration of HAC initially monocalcium aluminate decahydrate ( $C_1AH_{10}$ ), dicalcium aluminate octahydrate ( $C_2AH_8$ ) and alumina gel ( $Al(OH)_3$ ) are formed. However, these compounds of hydration are metastable and at normal temperature convert gradually to a more stable tricalcium aluminate hexahydrate ( $C_3AH_6$ ).

→ This conversion is accompanied by a loss in strength and change in crystal form from hexagonal to cubical shape resulting in a increase in the porosity.

→ This increase in porosity enhances its vulnerability to chemical attack.

→ The rate of conversion increases with the rise in temperature.

→ The hydration and conversion process can be symbolically



→ High alumina cement concrete loses considerably strength when subjected to humid conditions and high temperature, which gives insignificant increase and has significant residual strength.

→ A completely degraded alumina cement has very high resistance to dry heat.

→ In contrast with the cement concrete

crushed finebricks as aggregate can withstand temperatures up to  $1350^{\circ}\text{C}$ .

→ A refractory concrete for withstanding temperature up to  $1800^{\circ}\text{C}$  may be produced by using aggregate such as dead-burnt magnesite, chromite, sillimanite etc. Some high alumina cement is also set but requires hardening under proportions of  $\text{CaO}$  may be added to reduce setting time.

→ Bithium salts have been effectively used as accelerators in high alumina cement to obtain high early strength cement.

→ This has resulted in strength as high as  $40$  in one hour,  $25 \text{ MPa}$  in three hours time and  $50 \text{ MPa}$  in 24 hours time.

## 2. Magnesium phosphate cement:-

→ A very high early strength mortar and concrete developed by  $\text{RGL}$  consists of a pre-packed mixture of dead-burnt magnesite and fine aggregate mixed with phosphate. It sets rapidly and yields durable high strength cement mortar.

→ The dead-burnt magnesite is obtained by calcining  $\text{MgCO}_3$  at an above  $1500^{\circ}\text{C}$  and grinding the product to fineness of  $30000 - 35000 \text{ mesh (B.S. units)}$ .

→ The ground dead-burnt magnesite is mixed with commercially available crystalline mono-ammonium phosphate after grinding it into a fine powder passing  $600 \text{ mesh}$  and other ingredients like sodium tri-polyphosphate in the form of fine powder, di-sodium tetraborate (borax), fine aggregate (crushed chromite sand) and water, mixed for 1-2 minutes.

→ After application in repair of road and subsequent curing the traffic can be opened in a short period of about four to five hours.

1. General purpose of port land cement:-  
Port land cement

① Grade 33:-

- It is high in workability compared to other grades.
- It is used mostly in plaster & masonry work.

Fineness =  $300 \text{ kg/m}^2$

Cube strength 3 days =  $16 \text{ N/mm}^2$

7 days =  $22 \text{ N/mm}^2$

28 days =  $33 \text{ N/mm}^2$

2. Grade 43:-

- It is generally used for construction of reinforced concrete (R.C.C).
- Also used for precast concrete & has good working capacity.

Fineness =  $225 \text{ kg/m}^2$

Cube strength 3 days =  $23 \text{ N/mm}^2$

7 days =  $33 \text{ N/mm}^2$

28 days =  $43 \text{ N/mm}^2$

3. Grade 53:-

- It is used for construction of precast concrete.
- Construction of factories buildings & concrete sleepers in railways.

fine ass = 225 kg/m<sup>2</sup>

Cube strength

3 days = 27 N/mm<sup>2</sup>

7 days = 37 N/mm<sup>2</sup>

28 days = 53 N/mm<sup>2</sup>

Note:-

1) For 33 Grade  $\rightarrow$  IS 239

2) For 43 Grade  $\rightarrow$  IS 8112

3) For 53 grade  $\rightarrow$  IS 12269

4) 53 grade cement releases heat of hydration at a much faster rate compared to the 33, 43 cement.

## Chapter 3 Aggregate

### Introduction:-

- Aggregates are generally cheaper than cement and impart greater volume stability and durability to concrete.
- The aggregate is used primarily for the purpose of providing bulk to the concrete. To increase the density of the resulting mix, the aggregate is frequently used in two or more sizes.
- The most important function of the fine aggregate assist in producing workability and uniformity in mixture.
- The fine aggregate also assist the cement paste to hold the coarse aggregate particles in suspension.
- This action promotes plasticity in the mixture and prevents the possible segregation of paste and coarse aggregate, particularly when it is necessary to transport the concrete some distance from the mixing plant to the point of placement.
- The aggregate provide about 75 percent of the body of the concrete and hence its influence is extremely important.
- They should be therefore meet certain requirements if the concrete is to be workable, strong, durable and economical.
- The aggregate must be of proper shape (either round or operationally cubical), clean, hard, strong and well graded.
- It should possess chemical stability and, in many cases, exhibit abrasion resistance and resistance to freezing and thawing.

## CLASSIFICATION OF AGGREGATES

The classification of the aggregates is generally based on their geological origin, size, shape, unit weight, etc.

### Classification According to Geological Origin :-

- The aggregates are usually derived from natural sources and may have been naturally reduced to size (e.g. gravel or shingle) or may have to be reduced by crushing.
- The suitability of the locally available aggregate depends upon the geological history of the region. Such an aggregate may further be divided into two categories, namely the natural aggregate and artificial aggregates.

#### Natural Aggregate :-

- These aggregates are generally obtained from natural deposits of sand and gravel, or from quarries by cutting rocks.
- The cheapest among them are the natural sand and gravel which have been reduced to their present size by natural agents such as water, wind and snow, etc.
- The river deposits are the most common and are of good quality. The second most commonly used source of aggregates is the quarried rock which is reduced to size by crushing.
- Crushed aggregate are made by breaking rocks into requisite graded particles by blasting, crushing and screening, etc. From the geological standpoint, the natural

in the mix in appropriate proportions.

→ The particle size distribution is called the grading of the aggregate. According to size the aggregate is classified as: fine aggregate, coarse aggregate and all-in-aggregate.

Fine Aggregate:-

Definition

→ It is aggregate material which passes through 4.75 mm sieve and contains only that much coarser material as is permitted by the specification.

→ Sand is generally considered to have a lower size limit of about 0.075 mm.

→ Material between 0.075 mm and 0.002 mm is classified as silt, and still smaller particles are called clay.

→ The soil deposit consisting of sand, silt and clay in about equal proportion is termed

loam.

→ The fine aggregate may be one of the following types:-

1. Natural sand; i.e., the fine aggregate resulting from natural disintegration of rock and/or that which has been deposited by stream and glacial agencies.

2. Crushed stone sand i.e., the fine aggregate produced by stream and gla

3. Crushed gravel sand; i.e., the fine aggregate produced by crushing natural gravel.

→ According to size, the fine aggregate may be classified as coarse, medium and fine sand.

→ Depending upon the particles size distribution, it is also further divided into fine aggregate

into four grading zones.  
→ The coarse aggregate may be one of the following types:-

### Coarse Aggregate:-

→ The aggregates most of which are retained on the 4.75 mm IS sieve and contain only that much of fine material as is permitted by the specifications are termed coarse aggregates.  
→ The coarse aggregate may be one of the following types

1. Crushed gravel or stone obtained by the crushing of gravel or hard stone.
2. Unwashed gravel or stone resulting from the natural disintegration of rock.
3. Partially crushed gravel or stone obtained as a product of the blending of the above two types.

→ The graded coarse aggregate is described by its nominal size, i.e. 14 mm, 20 mm, 10 mm, and 12.5 mm, etc.

→ For example, a graded aggregate of nominal size 12.5 mm means an aggregate most of which passes the 12.5 mm IS sieve.

→ Since the aggregates are formed either by natural disintegration of rocks or by the artificial crushing of rock or gravel, they derive many of their properties from the parent rock.

→ These properties are chemical and mineral composition, petrographic description, specific gravity, hardness, strength, physical



and chemical stability, pore structure, and colour.

→ Some other properties of the aggregates not possessed by the parent rocks are particle shape and size, surface texture, absorption, etc.

→ All these properties may have a considerable effect on the quality of concrete in fresh and hardened states.

All in aggregate:-

→ Sometimes combined aggregates are available in nature comprising different fractions of fine and coarse aggregates, which are known as all in aggregate.

→ In such cases, adjustments often become necessary to supplement the grading by addition of respective size fraction which may be deficient in the aggregate.

→ Like coarse aggregate, the all in aggregate is also described by its nominal size.

→ The all in aggregates are not generally used for making high quality concrete.

Single-size aggregate:-

Aggregates comprising particles falling essentially within a narrow limit of size fractions are called single-size aggregates.

→ For example: a 20mm single-size aggregate means an aggregate most of which passes through a 20mm sieve and the major portion of which is retained in a 10mm IS sieve.

## Classification according to shape:-

- The particle shapes of aggregates influence the properties of fresh concrete more than those of hardened concrete.
- Depending upon the particle shape, the aggregate may be classified as rounded, irregular or partly rounded; angular or flaky.

### Rounded Aggregate

- The aggregate with rounded particles (River or sea shore gravel) has minimum voids ranging from 22 to 33 percent.
- It gives minimum ratio of surface area to the volume, thus requiring minimum cement paste to make good concrete.
- The only disadvantage is that the interlocking between its particles is less and hence the development of the bond is poor, making it unsuitable for high strength concrete and pavements.

### Irregular Aggregate

- The aggregate having partly rounded particles (crushed and gravel) has higher percentage of voids ranging from 35 to 45.
- It requires more cement paste for a given workability.
- The interlocking between particles, though better than that obtained with the rounded aggregate, is inadequate for high strength.

## Angular Aggregate:-

- The aggregate with sharp, angular and rough particles (crushed rock) has a maximum percentage of voids ranging from 38 to 40.
- The interlocking between the particles is good thereby providing a good bond.
- The aggregate requires more cement paste to make workable concrete of high strength than that required by rounded particles.
- The angular aggregate is suitable for high strength concrete and pavements subjected to tension.

## Flaky and Elongated Aggregates:-

- An aggregate is termed flaky when its least dimension (thickness) is less than three-fifths of its mean dimension.
- The mean dimension of the aggregate is the average of the sieve sizes through which the particles pass and are retained respectively.
- The particle is said to be elongated when its greatest dimension (length) is greater than five-fifths of its mean dimension.
- The angularity of aggregate affects the workability or stability of the mix which depends on the interlocking of the particles.
- The elongated and flaky particles also adversely affect the durability of concrete as they tend to be oriented in one plane with water and air voids forming underneath.

- The presence of these particles should be restricted to 10 to 15 per cent.
- This requirement is particularly important crushed fine aggregate, since the material made this way contains more flat and elongated particles.
- The angularity of the aggregate can be estimated from the percentage of voids in a sample, computed as prescribed in IS: 2386 (Part - I) - 1970.
- The higher the angularity number, the more angular is the aggregate.
- The elongation index of an aggregate is defined as the percentage by weight of particles present in it whose greatest dimension (length) is greater than nine-fifth of their mean dimension, whereas the flakiness index is the percentage by weight of particles having least dimension (i.e., thickness) less than three-fifth of the mean dimension.
- The surface texture of the aggregate depends on the hardness, grain size and pore character, nature of the parent rock, as well as the type and magnitude of the disintegrating forces.
- Based on the surface characteristics, IS: 2386 classifies the aggregates as glassy, smooth, smooth, granular, crystalline, honeycombed, porous, etc.
- The shape and surface texture of aggregate influence the workability of fresh concrete and the compressive strength of hardened concrete, particularly in high strength concrete.

- The strength of concrete, especially the tensile strength, depends on the bond between the aggregate and cement paste.
- The bond is partly due to the interlocking of the aggregate and paste.
- A rough surface results in a better bond.
- The bond is also affected by the physical and chemical properties, mineralogical and chemical composition, and the electrostatic condition of the particle surface, e.g. a chemical bond may exist in the case of a limestone aggregate.

## Classification Based on unit weight

The aggregates can also be classified according to their unit weight as normal weight, heavy weight, and lightweight aggregates.

### Normal Aggregates:-

→ The commonly used aggregates, i.e. sand and gravels, crushed rocks such as granite, basalt, quartz, sandstone and limestone and brick ballast, etc. which have specific gravities between 2.5 and 2.7, produce concrete unit weight ranging from 23 to 25 kN/m<sup>3</sup> and crushing strength at 28 days between 15 to 40 MPa are termed normal-weight concrete.

→ The properties and the requirements of normal-weight aggregate will be discussed in detail in the succeeding sets.

### Heavyweight or High-Density Aggregates:-

→ Some heavy weight or high-density aggregates such as baryte (sg: 4.0-4.6), ferrous phosphorus (sg: 5.8-6.8), goethite (sg: 2.4-3.1), hematite (sg: 4.9-5.3), ilmenite (sg: 4.0-4.6), limonite (sg: 3.4-4.4), magnetite (sg: 4.2-5.2), de-greased scrap iron and iron shot (sg: 6.2-7.8) are used in the manufacture of heavy weight

concrete which is more effective as a radiation shield.

→ Concretes having unit weight of about 30, 31, 35, 38, 40, 47 and 57 kN/m<sup>3</sup> can be produced by using typical gneiss, Lignite, baryte, magnetic, hematite, iron-phosphorus and scrap iron, respectively.

→ Where high fixed-water content is desirable, serpentines which has a slightly higher density than normal-density aggregate or bauxite can be used.

→ The main drawback with these aggregates is that they are not suitably graded and hence it is difficult to have adequate workability without segregation.

→ In general, selection of an aggregate is determined by physical properties, availability and cost. High-density aggregates should be reasonably free of fine material, oil and foreign substances that may affect either the bond of paste to aggregate particle or the hydration of cement.

→ For good workability, maximum density, and economy, aggregates should be roughly cubical in shape and free excessive flat or elongated particles.

## Lightweight Aggregate :-

- The lightweight aggregates having unit weight up to  $12 \text{ kN/m}^3$  are used to manufacture the structural concrete and masonry blocks for reduction of the self-weight of the structure.
- These aggregates can be either natural such as diatomite, pumice, volcanic cinder etc. or manufactured, such as bloated clay, sintered fly ash or foamed blast-furnace-slag.
- In addition to reduction in the weight the concrete produced by using light weight aggregate provides better thermal insulation and improved fire resistance.
- The main requirement of the lightweight aggregate is its low density, some specifications limit the unit weight to  $12 \text{ kN/m}^3$  for fine aggregate and approximately  $10 \text{ kN/m}^3$  for coarse aggregates for the use in concrete. Because of high water absorption the workable concrete mixes become stiff within a few minutes of mixing thus requiring the wetting of the aggregates before mixing the mix.
- In the mixing operation, the required water and aggregate are usually premixed prior to the addition of cement.



- Approximately, six liters of extra water per cubic meter of light weight aggregate concrete is needed to enhance its workability by 25mm.
- To produce satisfactory strength of concrete, the cement content may be 35 kg/m<sup>3</sup> or more.
- Due to the increase of permeability and rapid carbonation of concrete, the cover to the reinforcement using lightweight aggregate in concrete should be increased.
- The other characteristics of concrete using lightweight aggregates are reduced workability, due to rough surface texture, lower tensile strength, lower modulus of elasticity (50 to 75 percent of that of normal concrete) and higher creep and shrinkage.

### Characteristics of aggregate:-

→ Characteristic of aggregate depends upon toughness, strength, hardness, particle size of aggregate.

→ Following are the properties of aggregate:-

1. Strength of aggregate:-

→ The strength of concrete cannot exceed that of the bulk of aggregate contained therein. Therefore, so long as the strength of aggregate is of an order of

magnitude stronger than that of the concrete with them, it is sufficient. However, in the case of high strength concrete, subjected to localized concentration leading to stresses higher than the overall strength of concrete, the strength of aggregate may become critical.

→ Generally three tests are prescribed for the determination of strength of aggregate, namely aggregate crushing value, aggregate impact value and 10 percent fines value. Of these, the

→ crushing value, aggregate impact value and 10 percent fines value. Of these, the crushing value test is more popular and the results are reproducible. However, the 10 percent fines from 12.5 mm to 10 mm particle is more reliable.

IS: 2383 - 1970 prescribes a 45 percent limit for the crushing value determined as per IS: 2383

- 1953 for the aggregate used for concrete

→ other than for wearing surfaces and 30 percent for concrete for wearing surfaces, such as runways, roads and pavements.

→ BS: 282 - 1953 prescribes a minimum value of 10 tonnes in the 10 percent fineness for aggregates to be used in wearing surfaces and five tonnes when used in other concretes.

→ The other related mechanical properties of aggregate which are important especially when the aggregate is subjected to high

wear are toughness and hardness.

→ The toughness of aggregate is subjected to high wear and the resistance of the aggregate to failure by impact determined

In accordance with IS-2386 (Part IV) 1963. Its crushing value may be used instead of its crushing value.

→ The aggregate impact value shall not exceed 45 per cent by weight for aggregate used for concrete other than those used for wearing surfaces and 30 per cent for concrete for wearing surfaces.

→ The hardness of the aggregate defined as its resistance to wear obtained in terms of aggregate abrasion value is determined by using the Los Angeles machine as described in IS-2386 (Part IV) 1963.

→ The method combines the test for attrition and abrasion.

→ A satisfactory aggregate should have an abrasion value of not more than 30 per cent for aggregates used for wearing surfaces and 50 per cent for aggregates used for non-wearing surface.

→ The strength of an aggregate is measured by its resistance to breaking and crushing is an important characteristic for a concrete exposed to severe weather.

- The resistance to freezing and thawing is related to its porosity, absorption, and structure. In a fully saturated aggregate there is not enough space available.
- \* ~~The strength of an aggregate is measured by its resistance to~~  
to accommodate the expansion due to freezing of water resulting in the failure of the particles.
- An aggregate with higher modulus of elasticity.
- The modulus of elasticity of aggregate also affects the magnitude of creep and shrinkage of concrete.

## 2) Particle shape and texture:

- Its physical characteristics such as shape, texture and roughness of aggregates significantly influence the mobility (i.e. the workability) of fresh concrete and the bond between the aggregate and the mortar phase.
- As described earlier, the aggregates are generally divided into four categories, namely; rounded, irregular, angular and flaky.
- The rounded aggregates are available in the form of river or beach sand or gravel which are fully waterworn or completely shaped by attrition, where

Irregular or partly rounded aggregate are available in the form of river pebbles, by attrition and have rounded edges.

→ The angular aggregate possessing well-defined edges formed at the intersection of roughly planar faces are obtained by crushing the rocks.

→ The angular aggregates obtained from laminated rocks having thickness smaller than the width and/or length are termed flaky.

→ The rounded aggregates require less amount of water and cement paste for a given workability.

→ The water content could be reduced by 5 to 10 percent, and the sand content by three to five percent by the use of rounded aggregate.

→ On the other hand, the use of crushed aggregate may result in 10 to 20 percent higher compressive strength due to the development of stronger aggregate mortar bond.

→ This increase in strength may be up to 30 percent for the concrete having a water-cement ratio below 0.4.

→ The elongated and flaky particles, having a high ratio of surface area to volume reduce the workability appreciably.

→ These particles tend to be oriented in one plane with water and cement.

underneath.

→ The thickness index of coarse aggregate is generally limited to 25 percent.

→ The surface texture is a measure of the smoothness or roughness of the aggregate.

→ Based on the visual examination of the specimen, the surface texture may be classified as glassy, smooth, granular, rough, crystalline, porous and honeycombed.

→ The strength of the bond between aggregate and cement paste depends upon the surface texture.

→ The bond is the development of mechanical anchorage and depends upon the surface roughness and surface porosity of the aggregate.

→ An aggregate with a rough porous texture is preferred to one with a smooth surface rough, as the former can increase the aggregate cement bond by 75 percent.

→ The surface pores help in the development of good bond on account of suction of paste into these pores.

→ This explains the fact that some aggregates which appear smooth still bond strongly than the one with rough surface texture.

→ The shape and surface texture of fine aggregate govern its void content and thus affect the water requirement of mixture.

→ The use of crushed or manufactured aggregate with requirement of ~~min~~ significant to proper shape, surface texture and grading has enabled production of highly workable mix with minimum void content.

### 2. Specific gravity:-

The specific gravity of an aggregate is defined as the ratio of the mass of solid in a given volume of sample to the mass of an equal volume of water at the same temperature. Since the aggregate generally contains voids, there are different types of specific gravities.

→ The absolute specific gravity refers to the volume of solid material excluding the voids and moisture. It is defined as the ratio of the mass of solid to the weight of an equal void-free volume of water at a stated temperature.

→ If the volume of aggregate included the voids, the ~~resulting~~ resulting specific gravity is called the apparent / bulk specific gravity.

→ As the aggregate generally contains both impermeable and capillary voids (voids between the particles), the apparent specific gravity refers to volume including impermeable voids only.

It is therefore the ratio of the mass of the aggregate placed in an oven at 100 to 110°C for 24 hours to the mass of the water occupying a volume equal to that of solids (including impermeable voids) at same.

→ The specific gravity most frequently and easily determined is based on the saturated surface dry condition of the aggregate because the water absorbed in the pores of the aggregate does not take part in the chemical reaction of the cement and can therefore be considered a part of the aggregate.

→ This specific gravity is required for the calculation of the yield of concrete or for the quantity of aggregate required for a given volume concrete.

→ The specific gravity of an aggregate gives valuable information on its quality and properties.

→ It is seen that the higher the specific gravity is above or below that which is normally assigned for a particular type of aggregate it may indicate that the shape and grading of the aggregate has changed.

→ The specific gravity is determined as described in IS: 2386 (Part 2) - 1963. The specific gravity is given by

$$\text{specific gravity} = \frac{C}{A-B}$$

and

$$\text{apparent specific gravity} = \frac{C}{C-B}$$

$$\text{Water absorption} = \left( \frac{a-c}{c} \right) \times 100 \text{ percent}$$

Where  $a$  = mass of saturated surface dry



b. mass of saturating surface dry aggregate in water and

c. mass of oven dry aggregate in air  
The average specific gravity of majority of natural aggregate is between 2.5 and 2.8

#### 4. Bulk density :-

- The bulk density of an aggregate is defined as the mass of the material in a given volume and is expressed in kilograms/litre.
- The bulk density of an aggregate depends on how densely the aggregate is packed in the measure.
- The other factors affecting the bulk density are the particle shape, size, the grading of the aggregate and the moisture content.
- The shape of the particles greatly affects the closeness of the packing that can be achieved.
- For a coarse aggregate of given specific gravity a higher bulk density indicates that there are fewer voids to be filled by sand and cement.
- The bulk density of an aggregate can be used for judging the quality of aggregate by comparing it with nominal density for that type of aggregate.
- It determines the type of concrete for which it may be used.
- The bulk density is also required for converting proportions by weight into the proportions by volume. The bulk density is determined as described in IS: 2386 Part IV 1963.

### 5- Voids :-

- The empty spaces between the aggregate particles are termed voids.
- It is the difference between the gross volume of aggregate mass and the volume occupied by the particles alone.
- The void ratio of an aggregate can be calculated from the specific gravity and bulk density of aggregate mass as follows:

$$\text{Void ratio} = 1 - \frac{\text{Bulk density}}{\text{Apparent specific gravity}}$$

### 6- Porosity and absorption of aggregates :-

- Due to the presence of air bubbles which are entrapped in a rock during its formation or on account of the decomposition of certain constituent minerals by atmospheric action, minute holes or cavities are formed in it which are commonly known as pores.
- The pores in the aggregate vary in size over a wide range, the largest being large enough to be seen under a microscope or even with the naked eye.
- They are distributed throughout the body of the material, some are wholly within the solid and the others are open to the surface of the particle.
- The porosity of some of the commonly used rocks varies from 0 to 25 percent. Since the aggregate constitutes about 75 percent of the concrete, the porosity of aggregate contributes to the overall porosity of concrete.

- The permeability and absorption affect the bond between the aggregate and the cement paste, the resistance of concrete to freezing and thawing, chemical stability, resistance to abrasion and the specific gravity of the aggregate.
- The pores may become reservoirs of free moisture inside the aggregate.
- The percentage of water absorbed by an aggregate.
- The aggregate which is saturated with water but contains no surface free moisture is termed the saturated surface dry aggregate.
- The method for determining the water absorption of an aggregate is described in IS: 2316 (Part III) - 1963.
- If the aggregate is previously dried in an oven at 105°C to a constant weight before being immersed in water for 24 hours, the absorption is referred to as oven dry basis.
- On the other hand, the percentage of water absorbed by an air dried aggregate when immersed in water for 24 hours is termed absorption of aggregate (air dry basis).
- The knowledge of the absorption of an aggregate is important for concrete mix design calculations.

## 7. Moisture content of aggregate

→ The surface moisture expressed as a percentage of the weight of the saturated surface dry aggregate is termed as moisture content. Since the absorption represents the water contained in the aggregate in the saturated surface dry condition and the moisture content is the water in excess of that, the total water content of a moist aggregate is equal to the sum of absorption and moisture content.

→ IS : 2386 (Part-III) - 1963 describes the method to determine the moisture content of concrete aggregate.

→ The determination of moisture content of an aggregate is necessary in order to determine the net water-cement ratio for a batch of concrete.

→ A high moisture content will increase the effective water-cement ratio to an appreciable extent and may make the concrete weak unless a suitable allowance is made. IS : 2386 (Part-III) - 1963 gives


two methods for its determination.

→ The first method, namely, the displacement method, gives the moisture content as a percentage by mass of the saturated surface dry sample whereas the second method namely the drying method will normally be the total moisture content due to free plus absorbed water.

→ The accuracy of the displacement method depends upon the accurate information of the specific gravity of the material in a saturated surface dry condition.

### 8 Bulking of fine aggregate:-

- The increase in the volume of given mass of fine aggregate caused by the presence of water is known as bulking.
- The bulking of fine aggregate is caused by the films of water which push the particles apart.
- The extent of bulking depends upon the percentage of moisture present in the sand and its fineness.
- It is seen that bulking increases gradually with moisture content up to a certain point and then begins to decrease with further addition of water due to the merging of films, until when the sand is inundated.
- At this stage, the bulking is practically nil.
- With ordinary sands, the bulking usually varies between 15 and 30 percent.
- The typical graphs give the variation of percent bulking with moisture content.
- Finer sand bulks considerably more and the maximum bulking is obtained at a higher water content than the coarse sand.
- In extremely fine sand, the bulking may be of the order of 40 percent at a moisture content of 10 percent but such a sand is unsuitable for concrete. In the case of most aggregate, the increase

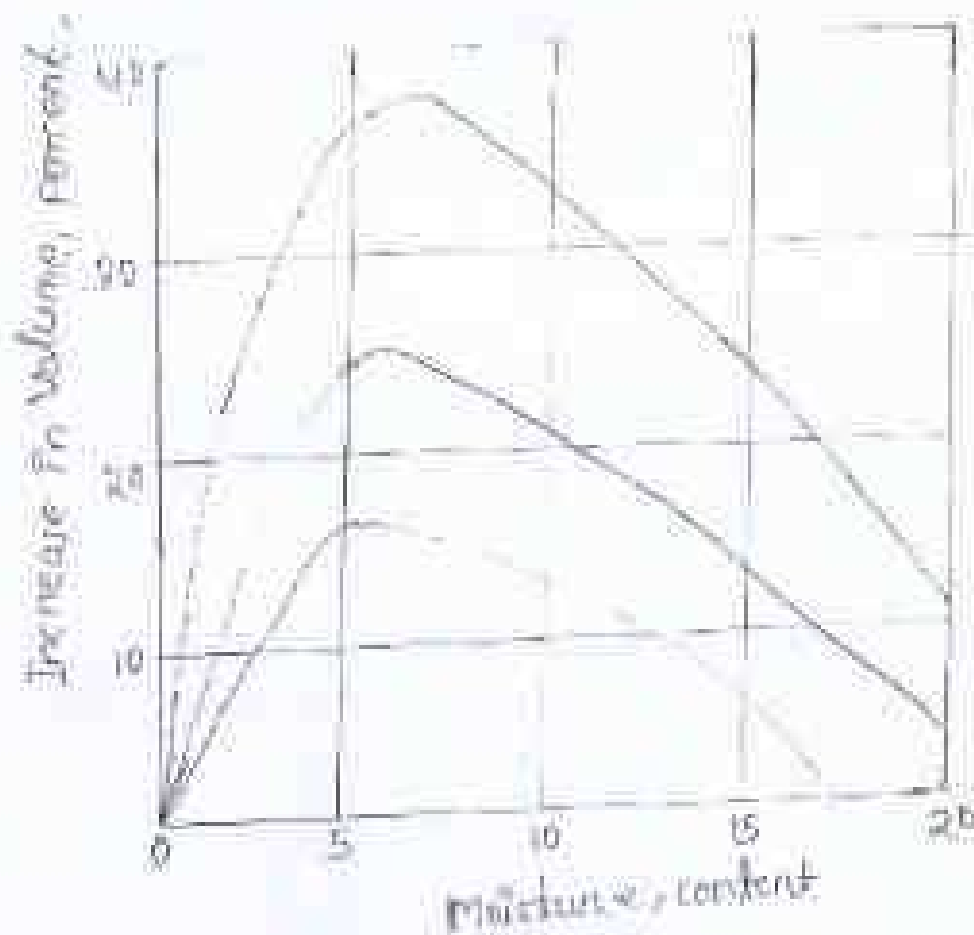

### Effect of moisture content on the bulking of sand

- Increase in volume is negligible due to the presence of free water as the thickness of the moisture film is very small as compared with particle size.
- The percentage bulking is obtained in accordance with BS 2386 (Part II) - 1963.
- If the sand is measured by volume and no allowance is made for bulking, the mix will be richer than that specified because for a given mass, moist sand occupies a considerably larger volume than the same mass of the dry sand.
- This results in a mix deficient in sand increasing the chance of the segregation and honey-combing of concrete.

- The yield of concrete will also be reduced.
- It is necessary, in such a case, to increase the measuring volume of the sand by the percentage bulking, in order that the amount of sand put into concrete be amount intended for the nominal mix used (based on dry sand).
- If no allowance is made for the bulking of sand a nominal concrete mix 1:2:4, for example, will correspond to 1.21:1.41:4 for a bulking of 15 percent.
- An increase in bulking from 15 to 30 percent will result in an increase in the concrete strength by as much as 14 percent.
- If no allowance is made for bulking the concrete strength may vary by as much as 25 percent.

### Fineness modulus

- The fineness modulus is a numerical index of fineness, giving some idea of the mean size of the particles present in the entire body of the aggregate.
- The determination of the fineness modulus consists in dividing a sample of aggregate into fractions of different sizes by sieving through a set of standard test sieves taken in order.
- Each fraction contains particles between definite limits.
- The limits being the opening sizes of standard test sieves above.
- The material retained on each sieve after sieving represents the fraction of aggregate coarser than the sieve in question but finer than the sieve above.

→ The sum of the cumulative percentage retained on the sieves divided by 100 give the fineness modulus of the aggregate (curve), fine or all-in aggregate for concrete as per IS: 2386 (Part-1)-1963, are 80mm, 40mm, 20mm, 10mm, 4.75mm, 2.36mm, 1.18mm, 600  $\mu$ m, 300  $\mu$ m and 75  $\mu$ m.

→ The fineness modulus can be regarded as a weight of average size of a sieve on which material is retained and the sieves being counted from the finest.

→ For example, a fineness modulus of 6.0 can be interpreted to mean that the sixth sieve, i.e. 4.75 mm is the average size.

→ The value of fineness modulus of higher for coarser aggregate.

→ For the aggregates commonly used, the fineness modulus of fine aggregate varies between 2.0 and 2.5 for coarse aggregate it varies between 5.5 and 8.0 and from 3.5 to 6.5 for all-in aggregate.

→ The object of finding fineness modulus is to grade the given aggregate for the most economical mix for the required strength and workability with minimum quantity of cement.

→ If the test aggregate gives higher fineness modulus, the mix will be harsh and it, on the other hand, gives a lower fineness modulus it will produce an uneconomical mix.

→ For workability, a coarser aggregate requires less water-cement ratio.



→ The fineness modulus is also important for measuring the slight variations in the aggregate from the same source.

Grading and surface area of aggregate:-

→ The particle size distribution of an aggregate determined by sieve analysis is termed as grade of aggregate.

→ If all the particles of an aggregate are of uniform size, the compacted mass containing more voids.

→ whereas particles of various sizes will give a mass containing lesser voids.

→ The particle size distribution of a mass of aggregate should be such that the smallest particles fill the voids between the larger particles.

→ The proper grading of aggregate produces dense concrete and needs less quantity of fine aggregate and cement.

→ It is therefore essential that the coarse and fine aggregate be well graded to produce quality concrete.



Well graded



Poorly graded



Gap graded

- The grading of an aggregate is expressed in terms of percentage by weight retained on or passing through a series of sieves taken in order, 4.75 mm, 7.5 mm, 15 mm, 30 mm, 4.75 mm, 7.5 mm, 15 mm, 30 mm, 600 microns, 800 microns and 150 microns for fine aggregate, as follows:
- The sieves are arranged in such an order that the square openings are half for each succeeding smaller size.
  - The curve showing the cumulative percentage of the material passing the sieves represented on the ordinate with the sieve opening, to the logarithmic scale represented on the abscissa is termed the grading curve.
  - The grading curve indicates whether the grading of a given sample conforms to that specified or is too coarse or too fine, or deficient in a particular size.
1. In case the actual grading curve is lower than the specified grading curve the aggregate is coarser and segregation of mix might take place.
  2. In case the actual grading curve lies well above the specified curve, the aggregate is finer and more water will be required thus increasing the quality of cement for a constant water-cement ratio. Hence, this is uneconomical.
  3. If the actual grading curve is steeper than the specified, it indicates an excess of middle size particles and leads to harsh mix.
  4. If the actual grading curve is flatter than the specified grading curve, the aggregate will be deficient in middle size particles.

→ The grading of the aggregate affects the workability which in turn, controls the water and cement requirements, segregation, and influences the placement and finishing of concrete.

→ These factors represent the important characteristics of fresh concrete and affect its properties in the hardened state.

→ The main factors governing the desired aggregate grading are: the surface area of aggregate, the relative volume occupied by the aggregate, the workability of the mix, and the tendency to segregate.

→ The surface area is affected by the maximum size of aggregates. If a sphere of diameter  $d$  is taken as representative of the shape of aggregates.

~~If a sphere of diameter~~

→ The ratio of surface area to the volume is  $6/d$ .

→ This ratio of surface of the particles to their volume is called specific surface.

→ The surface area will vary with the shape but is inversely proportional to the particle unit volume.

→ The aim must, therefore, be to have as large a maximum aggregate size as possible and to grade it down in such a way that the voids in the concrete are filled with the minimum amount of fine aggregate.

→ This arrangement, however, cannot be carried too far as aggregate graded in this way would be too harsh and a slight excess of fine is necessary to prevent this.

The greatest contribution to this total surface area is made by the smaller size aggregate and therefore particular attention should be paid to the proportion and grading of the aggregate.

→ The mortars consisting of fine aggregate and cement should be slightly in excess of that just required to fill the voids in the coarse aggregate.

→ Too coarse a fine aggregate results in harshness, bleeding and segregation and too fine an aggregate requires too large a water-cement ratio for adequate workability.



→ The surface area of aggregate also influences the amount of mixing water and cement required.

→ Generally, the water-cement ratio for adequate workability.

→ The surface area of aggregate also influences the amount of mixing water and cement required.

→ Generally, the water-cement ratio is fixed for strength considerations. However, the amount of cement paste should be sufficient to cover the surface of all the particles for proper workability and bond.

→ The drying shrinkage is less with a smaller amount of mixing water, and the temperature rise due to hydration and, therefore, cracking on subsequent cooling is less with the smaller proportions of cement in the mix.

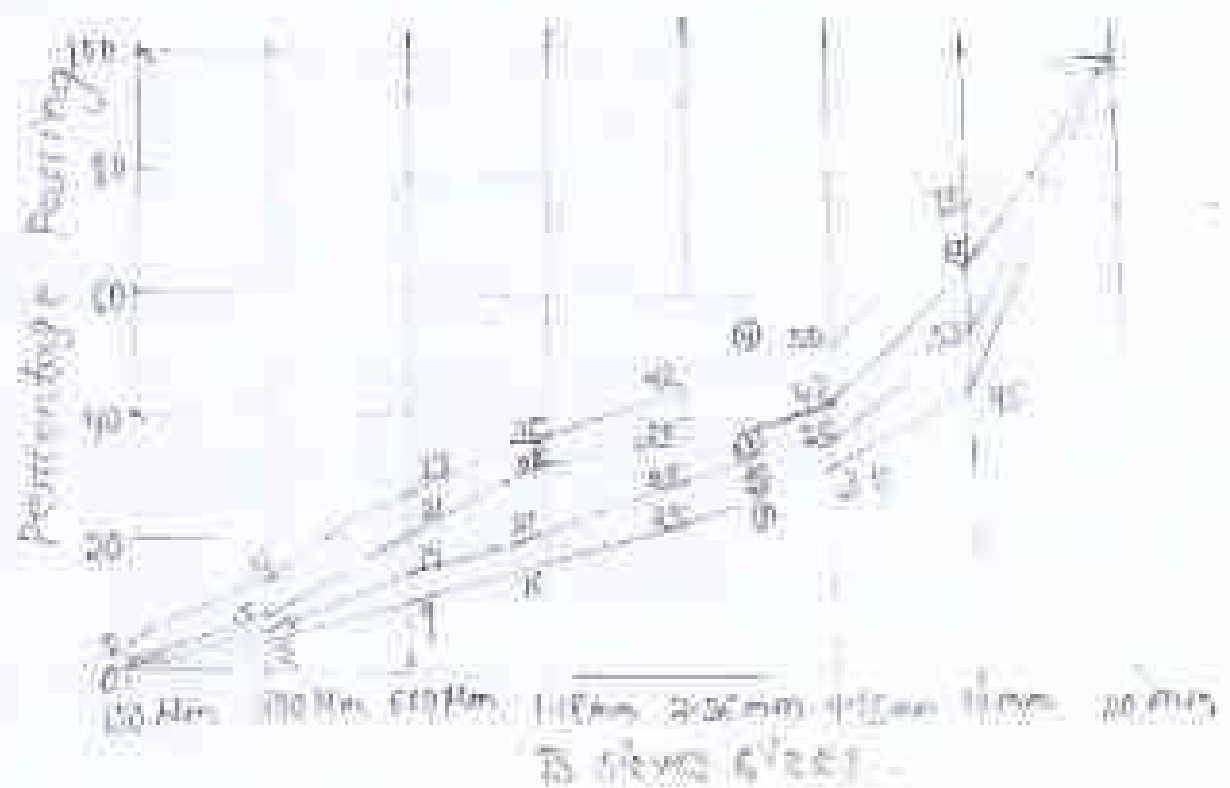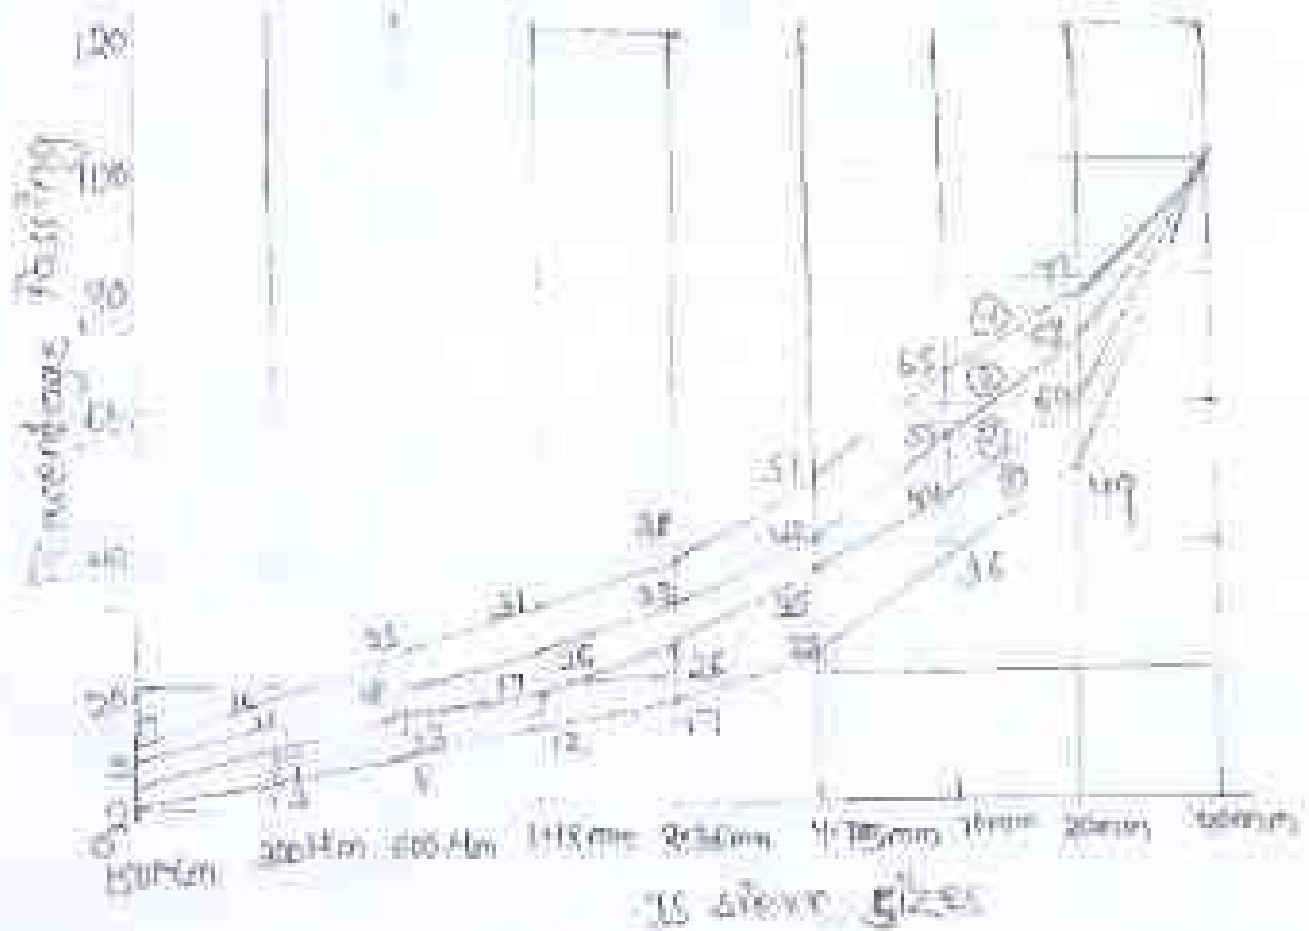

Notes $\rightarrow \frac{1}{\lambda} = 0.3 \text{ } \mu\text{m}^{-1}$  minimum

100% = workability

04-27-2003

11/11/11

grade of concrete measure of aggregate, workability

Water is the most important & least expansion ingredient of concrete.

→ A part of mixing water is utilized in the hydration of cement to form the binding matrix which the ~~is the~~ ~~hydration of cement~~ ~~is~~ inert aggregates are held in suspension until the matrix has hardened.

Generally current requires about three-fourth of the weight of water for hydration.

→ Hence the minimum water-cement ratio required is 0.35

→ Hence the minimum water-cement ratio is influenced by the grade of concrete.

→ The water-cement ratio is influenced by the nature & type of aggregate, the workability & durability.

3. If too much water is added to concrete, the excess water along with cement comes to the surface by capillary action - this creates a thin layer of

of action - water molecule forms a thin layer of this cement water molecule known as hydration sheath.

→ the distance prevents bond formation between successive layers of carbon & forms a place of weakness.  $\therefore$  can also look through the joint

Excess water may also leak through the joints of formwork & make the concrete more compact. The percentage of water the stronger

7. the smaller the percentage of water the stronger is the concrete.

## \* Quality of mixing water:-

→ The water used for mixing & curing of concrete should be free from injurious amounts of deleterious material.

→ The mixing & curing of water should not be inappropriate quality that causes concrete leading to distress.

→ In case of doubt of suitability of water, particularly by in normal circumstances when water is derived from sources not normally utilized for domestic purposes, then water should be tested.

## \* Effects of Impurities in water on properties of concrete:-

→ The strength & durability of concrete is reduced due to presence of impurities in the mixing water.

→ The effects are mainly expressed in terms of delay in the setting time of Portland cement mixes containing prepared mixing water as compared to distilled water.

→ A difference in 28 days compressive strength up to 4% of control test is generally considered to be a satisfactory measure of the quality of mixing water.

→ BS 5480 prescribes a difference in initial setting time of  $\pm 30$  minutes with initial setting time not less than 30 mins.

→ The effluents from sewage plant, gas work & from paint, fertilizer, sugar & fertilizer industry are harmful for concrete.

→ The test shows that water containing excess amount of dissolved salt reduces compressive strength by 10 to 30 percent.

→ In addition water containing large quantities of chlorides tends to cause dampness surface of concrete & increases the corrosion of reinforcing steel.  
→ The effects of various impurities on properties of concrete are summarized below:-

### 1) Suspended Particles:-

\* The presence of suspended particles of clay & silt in the mixing water, upto 0.2% by weight of water does not affect the properties of concrete.

→ Even higher percentage can be tolerated so far as strength is concerned but other properties of concrete are affected.

→ IS 456:2000 allows 2000 mg/litre of suspended matter.

### 2) Miscellaneous Inorganic salts:-

\* The presence of salts like magnesium chloride, copper & lead in water causes reduction in the strength of concrete.

→ The zinc chloride retarded the setting of concrete to such an extent that no strength available at 28 days.

→ The effect of lead nitrate is completely destructive.  
→ Some other salts like sodium iodate, sodium phosphate, sodium arsenate & sodium borate reduce the initial strength of concrete to very low.

→ The carbonates of sodium & potassium may cause extremely rapid setting & reduce the concrete strength.

→ Presence of calcium chloride accelerates setting & hardening.



→ the quantity of calcium chloride is reduced to 15% by weight of cement.

### CURING WATER

→ The use of water in curing the concrete is intended to penetrate the concrete.

→ If steps are taken to prevent loss of water from the concrete, no added water will be needed as a part of curing process except in the circumstances in which the water-cement ratio is less than 0.40, or when the concrete is produced using expansive cement.

→ Even at a water-cement ratio of one, empty capillary pores exist, however, there is enough water in the mixture for hydration to proceed to completion, but it is necessary for the water to be uniformly distributed throughout the mass of concrete.

→ In structural members, there is ~~less~~ inevitably some loss of water by evaporation from the surface.

→ Consequently, hydration may effectively succeed in the interior of the member but near the surface, there is an inadequate amount of water in the capillaries so that penetration by curing water is highly desirable.

→ However, if the water used for curing is seawater, chloride ions enter the surface zone and from there move inward by diffusion.

→ From the standpoint of durability, it is the water surface zone that is much more important than the concrete in the interior of the member, many times

→ problems still at the surface on through attack progressing from the surface inwards.

→ In the case of major structures cast on land but destined for immersion in the sea, the risk of contamination of seawater is high, unless thorough curing with fresh water has been done previously.

→ The water which is satisfactory for minor concrete can also be used for curing it. Salt should not produce any objectionable stain or unsightly deposit on the surface.

→ Iron and organic matter in the water are chiefly responsible for staining on discoloured concrete, especially when concrete is subjected to prolonged wetting, even a very low concentration of these can cause staining.

→ According to BS: 45-2008, the presence of ferric acid or iron compounds in curing water is objectionable.

→ It is generally recommended that the seawater should not be used as mixing water for hydraulic cement concrete with ordinary portable embedded ferrous metals, particularly in the tropics.

→ However, under unavoidable circumstances it may be used for curing and curing in plain concrete after due evaluation of possible disadvantages and consideration of the use of appropriate cement system.

### Salts in seawater:-

→ Seawater generally contains 35 percent of dissolved salts.

→ The chemical composition of seawater throughout the world is remarkably uniform and all the chloride is associated with sodium except for very small

amount with potassium and all the sulfate is removed  
from the magnesium.

The approximate percentages of various salts in the  
the salts in concrete are: chlorides 0.1%,  
sulfate 0.1%, calcium 2.5%, magnesium 0.1%,  
potassium 0.1%, sodium 0.1%, the total amount being  
very small.

For a given mass of concrete in contact with the  
moisture of any given soil is proportional to the surface  
area of that concrete.

From the standpoint of various effects of salts  
in the concrete, the sulfate is the most  
common which is problematic, hence the need for  
sulfate-resisting concrete.

To remove the ~~moisture~~ ~~need~~ is greatly  
reduced by employing concrete of low water content  
ratio.

The salts present in concrete produce the effect  
strength of concrete.

The reduction in strength of concrete under  
the action of moisture is about 20 percent.

In case the concrete is the type of concrete  
resisting steel due to chlorides.

In general, the rate of corrosion of steel is more  
when the reinforcement concrete member is exposed to  
air than when it is continuously submerged in water.

The presence of chloride, sulfate is also reduced  
by the presence of potassium.

It is advantageous to use cement with as much  
as possible without increasing  
sulfate attack in concrete containing moisture  
and steel.

→ the more is the  $Ca$  in the cement, the more  $Cl^-$  is a ion will be intercepted by aluminates (resisting) as non-detrimental calcium chlorides, making longer for the ions to build up at the surface of the steel.

→ there are two reasons for the presence of chloride ion in the concrete. The first is calcium chloride added as an accelerating admixture and the second one is the intentional use of seawater as mixing water.

→ For normal cements that are not highly sulfate-resisting, the use of cements requires the sulfate-resistance, but not when approximate sulfate-resisting cement is employed.

→ The use of cements as an accelerator can be permitted in cold weather with sulfate-resisting cement to the same limited extent as with ordinary cements.

→ However, the codes forbidding the use of calcium chloride when sulfate-resisting cement is being used.

→ Under some variable circumstances, it may be used for plain concrete when it is constantly submerged in water.

### Acids and Alkalies:

→ The industrial waste water containing acids or alkalies is usually unsuitable for concrete construction. With reference to acidity, the water having pH value higher than 6 can be used.

→ However, the pH value may not be a satisfactory measure of the amount of acid.

→ The effect of acidity in water is best judged on the basis of total acidity, the extent of which should satisfy the following requirement

→ The amount of 0.02 normal NaOH required to neutralize 100 ml sample of water using phenolphthalein as indicator should not be more than 5 ml.

→ This acidity is equivalent to 17 ppm of  $H_2SO_4$  or 33 ppm of  $HCl$ .

### Algae

→ Algae may be present in mixing water on the surface of aggregate particles.

→ It combines with cement and reduces the bond between aggregates and cement paste.

→ The water containing algae has the effect of entraining large quantities of air in concrete and thus lowering the strength of concrete.

### Sugar

→ If the amount of sugar present in the mixing water is less than 0.5 percent by weight of water there is no adverse effect on the strength of concrete.

→ Small amounts of sugar up to 0.5 percent by weight of cement retard the setting of concrete and the early strength may be reduced whereas the 28 days strength may be improved when the quantity of sugar is increased to 0.25 percent by weight of cement, setting is retarded.

→ When quantity is further increased, rapid

setting may result and as dry strength is reduced  
oil contamination:-

- Mineral oils not mixed with animal or vegetable oils have no adverse effect on the strength of concrete.
- If the concentration of mineral oil is up to two percent by weight of cement, a significant increase in strength has been noticed. For a percentage of mineral oil (more than eight percent), the strength is slightly reduced.
- The vegetable oils have detrimental effect on the strength of concrete particularly at later ages.

★

## Admixture

- 7 Admixtures are the chemical compounds in concrete other than hydraulic cement (opc), water, aggregate & mineral additives that are added to the concrete.
- 7 Admixture is added & mix immediately before (or) during mixing to modify one (or) more of the specific properties of concrete.
- 7 The use of admixture should offer an improvement not economically by adjusting the proportions of water, cement & aggregates / should not be adversely affect the performance of the concrete.
- 7 The admixtures have formulated chemical compounds or special chemical actions one way to modify certain properties of concrete.
- 7 they are primarily used to reduce the cost of concrete, to modify the performance of hardened concrete, to ensure the quality of concrete during mixing, transporting, placing, compacting & curing & to overcome certain emergencies during concreting operation.
- 7 The properties that are commonly modified are setting time, workability, rate of hydration, strength etc.
- 7 The effectiveness of an admixture depends on several factors including types & quantity of cement, water content, mixing time, slump, temperature of concrete & air.

## \* Function of admixture:-

→ Following are the functions of admixture:-

- (a) To accelerate the initial set of concrete i.e. to speed up the rate of hydration & development of strength at early ages.
- (b) To retard the initial set i.e. to keep concrete workable for a longer time for placement.
- (c) To enhance the workability.
- (d) To increase the durability of concrete i.e. to enhance the resistance to special conditions of exposure.
- (e) To increase the resistance to chemical attack.
- (f) To reduce the heat of hydration.
- (g) To increase the bond between new & old concrete surfaces.
- (h) To enhance the bond of concrete to the steel reinforcement.
- (i) To increase the strength of concrete, by reducing the water content in concrete.
- (j) To reduce the segregation in concrete mix.
- (k) To improve the penetration in concrete.
- (l) To produce coloured concrete (or) coloured mortar surface.
- (m) To produce concrete with fungicidal, germicidal & insecticidal properties.



## 4. Classification of Admixture:-

General purpose	Speciality category
a) air-entraining admixture	a) grouting admixture
b) Retarding admixture	b) air-deaerating
c) air-entraining	c) gel-forming
d) water-reducing	d) corrosion inhibiting
	e) shrinkage reducing
	f) viscosity (or) pumpability
	g) permeability reducing admixture
	h) bonding admixture
	i) concrete surface hardening admixture
	j) coloring admixture (or) pigments
	k) antifungal, germicidal, insecticidal admixture

### (a) Accelerating admixture:-

- An admixture is used to speed up the initial set of concrete is called an accelerator.
- These are added to concrete either
  - 1) to increase the rate of hydration of hydraulic cement hence increasing the strength.
  - 2) to shorten the setting time.
- An increase in the rate of early strength development may help in:

- (i) earlier removal of forms
- (ii) Reduction of required period of curing
- (iii) better placement of structure in service.

→ Accelerating admixtures are also used when the concrete is to be placed at low temperature.

The benefit of reduced time of setting may include

→ Early finishing of surface

(Reduction of pressure on forms) (iv) period of time during which the forms are subjected to hydraulic pressure.

(v) More effective against leaks due to hydraulic pressure.

→ With the availability of powerful accelerators, the underwater concreting, the placement within freezing operations, the repair works of underwater structures in the tidal zone become easy.

The general action of accelerator is to cause a more rapid dissolution of compounds of cement particularly tricalcium silicate in water & hence facilitates more rapid hydration of these compounds.

→ The most widely used accelerator is calcium chloride ( $\text{CaCl}_2$ )

→  $\text{CaCl}_2$  can generally be used 2 percent by mass of cement.

→ According to BS: 201 (part-1) - 1981 recommend a maximum of 1% of  $\text{CaCl}_2$  in concrete in form of admixture.

$\text{CaCl}_2$  should not be used in concrete which will be subjected to alkali-silica reaction (iii) exposure of concrete containing sulphates in contact with the lowering of the resistance of concrete.

to accelerate attack.

- The use of  $\text{CaCl}_2$  at  $100 \text{ kg/m}^3$  early age concrete can reduce the setting time by 1 hour & increase the (1-7) days compressive strength by (20-30) MPa.
- An increase of flexural strength of (40-50)% of one day & 4 to 12% at 28 days is obtained.
- Large doses of early result in flash set of concrete & also increase the shrinkage.
- The other commonly used accelerators are  $\text{NaOH}$ ,  $\text{NaOH}$ ,  $\text{Na}_2\text{CO}_3$ ,  $\text{CaCl}_2$ ,  $\text{KOH}$ ,  $\text{K}_2\text{SO}_4$ .

Note:-  $\text{NaOH}$  &  $\text{KOH}$  + concrete  $\rightarrow$  Rapid hardening of concrete  
Excess of both

### (B) Retarder admixture:-

→ The admixture admixture slows down the initial & initial rate of hydration of concrete (to prolong the setting of concrete paste in concrete).

- They are used primarily to (1) slow the acceleration & delaying effect at high temperature & to keep concrete workable during hot & arid placing conditions which should be sufficiently long so that the concrete can be placed without the development of cold joints. (2) discontinuous cast structures.
- They are also used to prevent oil well.
- The slowing of hydration means that the concrete for its hydration uses some of the water readily available to provide workability.

→ high temperature, low humidity & wind cause a rapid evaporation of water from the concrete during summer.

→ the drying of concrete leads to the cracking of the surface.

→ Retarders delay setting of cement either by forming a thin coating on the cement particles & thus slowing down their dissolution in reaction with water or by increasing the inter-molecular distance of reacting silicates & aluminates from water molecules by forming certain compounds in the system.

→ Retarding admixture hold back the hydration process, leaving more water for workability & allowing concrete to be finished & protected before drying out.

→ Some of the retarding admixture also reduce the water requirement of the mixture making further reduction in water-cement ratio.

→ Retarders do not affect the final setting time & the compressive strength that is come out in 28 days.

→ The material used as water reducing & set controlling admixture generally called retarding plasticizer. Following are the groups include in this category.


(i) Soluble carbohydrate derivatives:-



## (iii) Inorganic Retarder:-



## (iv) Air-entraining admixture:-

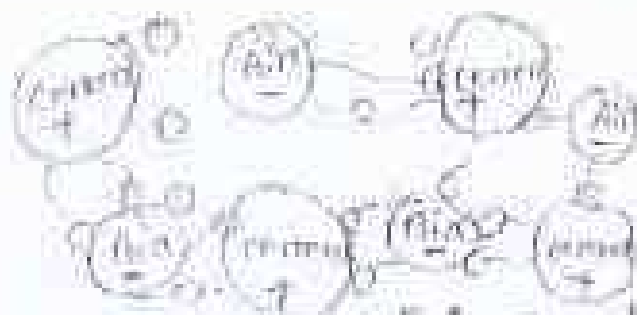

→ An air-entraining admixture helps to incorporate a controlled amount of air in the form of millions of minute bubbles distributed throughout the body of concrete during mixing, without significantly altering the setting or rate of hardening of concrete.

→ It is generally recognized that a proper amount of entrained air results in improved properties of plastic concrete like workability, easier placing & finishing, increased durability, better resistance to frost action & reduction in pore bleeding & segregation.

→ The entrained air bubbles ranging approximately from 0.05 to 0.25 mm diameter & spaced 0.03 mm apart reduce the capillary forces in concrete.

→ The air voids present in concrete are classified as entrained air & entrapped air.

→ Entrapped air is unintentionally incorporated in the form of minute bubbles.

→ Whereas the entrapped air is the former voids in the concrete due to insufficient space

compaction.

- Entrapped air may be of any shape & size & not uniformly distributed in the concrete.
- Entrapped air size is large & range vary from 0.01 to 10mm & more.




Entraining concrete



Entrapped concrete

- An entraining admixture increases the durability & plasticity, but there is decrease in strength of concrete.
- This type of admixture creates minute bubble in concrete which has flexibility due to which it has strong bond with cement, which increases its plasticity.
- Compacting process is done during the construction of concrete for removing the air from concrete & after completion of concrete there is certain percentage of concrete is present & the rate also evaporated from concrete due to temperature which creates small voids in concrete & when the concrete comes to the contract which atmospheric moisture content again these voids absorb those moisture & due to temperature again evaporation happens in concrete.
- The above process is known as freezing (make concrete hardened) / thawing process.

- 7 By adding air entraining admixture freezing & thawing process can be reduced & ductility which durability is increased.

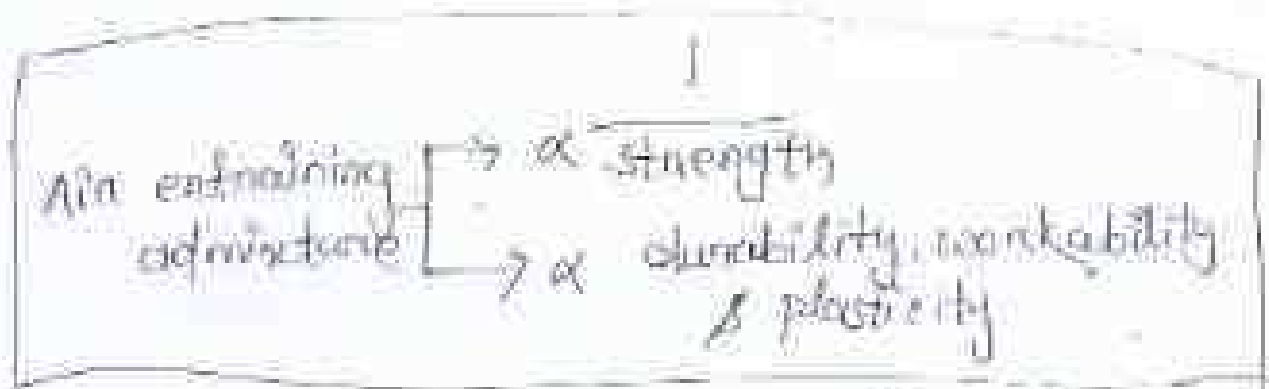

- For each percent increase in air content the compressive strength reduces approximately 1.4 MPa.
- Within the normal range of air content, the minimum reduction in compressive & flexural strength rarely exceeds 15% to 20%.
- The reduction of water-cement ratio & sand content made possible by air entrainment for the given workability.
- The beneficial amount of entrained air depends upon the type & quantity of air-entraining agent, water-cement ratio of the mix, grading & maximum size of aggregate & type of cement.

Maximum size of aggregate (mm)	Indicatively entrained	Optimal total
(i) Sand - cement mortar	4.0	14 ± 2
(ii) 10	3.0	8 ± 1.5
(iii) 12.5	2.5	7.5 ± 1.5
(iv) 20	2.0	7.0 ± 1.5
(v) 25	1.5	6 ± 1.5
	1.0	5.5 ± 1.5

vii) 50	0.5	$4.0 \pm 1.0$
viii) 70	0.3	$3.5 \pm 1.0$
ix) 150	0.2	$2.0 \pm 0.5$

→ In a minute bubble trail are generated due to air entraining agents act like flexible ball bearing help in to increase the mobility of concrete by reducing the friction between the particles. <sup>the</sup> they modify the properties of fresh concrete with regard to its workability, avoid the segregation & bleeding due to improved cohesion & finishing quality of concrete.

Effect of permeability:-

→ Greater uniformity of air entrained concrete due to enhanced air content, modified pore structure, reduced water channels due to reduction in bleeding are the some of reason for the improvement of its permeability.

Effect on chemical resistance:-

→ In view of the lower permeability & absorption the air entrained concrete has greater resistance to chemical attack than normal concrete.

→ It has been reported that air-entrainment reduces the alkali aggregate reaction.

Unit weight:-


→ For the same workability & strength the air entrained concrete contains approximately 5% less <sup>solid content</sup> material, hence has lower density. <sup>solid content</sup>



7. Usually, the desirable entrained air content in concrete is (3-6)%. Ex - Vinsol resin

(b) Water Reducing Admixture :-

Plasticizer

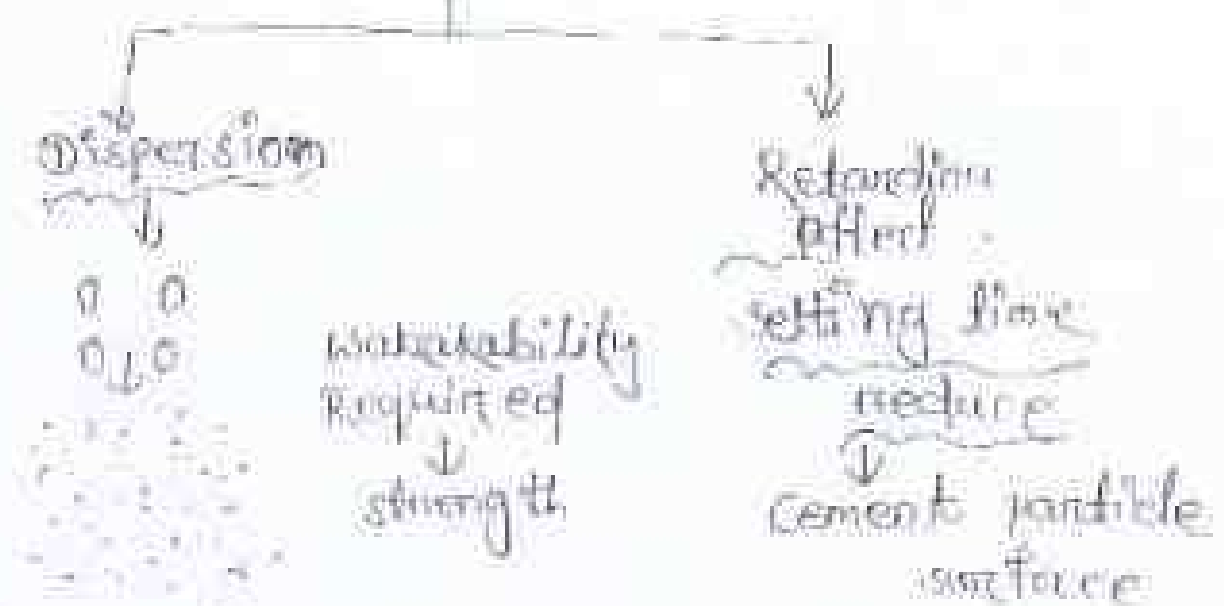

7. When water is added to a concrete, mortar, plaster, the cement & other fines in the mix such as fly ash, stone dust, silica fume flocculate (or) clump together.

7. The flocculated fines cause an increase in viscosity by entrapping a part of the water & by physically resisting the flow.

7. To reduce the viscosity to the desired level, it may be necessary to add more water.

7. Water is added upto a certain point, beyond which the intended plastic & hardened physical properties of the mixture are compromised.

2. To achieve the desired workability & hardened physical properties of the mixture, it is necessary

(iii) to add a water reduce to disperse (or) deflocculate

(iv) the system & reduce the addition of water.

→ The organic @ combination of organic & inorganic substances to achieve these objectives are termed as plasticizing admixture.

→ Water-reducing admixtures enable a given fresh concrete mix to be higher workability without increasing the water content which results in faster rate of concrete placement.

→ Benefits of water reduction in hardened state of concrete are increased strength, density, durability, volume stability, abrasion resistance, reduced permeability & cracking.

→ A good plasticizer is different from air entraining agents.

→ A good plasticizer does not contain air more than (1@2) % maximum.

Action of plasticizer:-

Dispersion

Retarding effect

(i) Dispersion:-

→ Portland cement, being in fine state will have a tendency to flocculate in wet concrete.

→ This flocculation entraps certain amount of water use in the mix and hence by all the water is not freely available to fluidify the mix.

→ When plasticizers are added, they get adsorbing on the cement particles.

→ The adsorption of charged polymer on the cement particles create repulsive forces between particles.

which overcome the attractive forces.

→ This repulsive force is known as zeta potential which depends on the solid content and quality of plasticizer.

→ The overall result is that the cement particles are deflocculated and dispersed.

→ When cement particles are deflocculated the water trapped inside the flocs gets released and becomes available to fluidify the mix.

→ Moreover, in the deflocculated state there is no particle friction between particles and flocs and floc and floc.

(ii) Retarding effect:-

a) Reduction in surface tension of water.

b) Lubricating film between cement particles.

c) Dispersion of cement grains releasing water trapped within cement flocs.

d) Induced etc.

Generally an admixture capable of reducing water requirements by more than five percent is classified as water reducer or plasticizer.

→ Depending upon the degree of water reduction, the water reducers are categorized as normal water reducer, mid-range water reducer and high-range water reducer or superplasticizer.

→ The normal water reducer reduces water content by 5 to 10 percent. The mid-range water reducers reduce water content by

about 10 to 15 percent and tend to be more stable over a wider range of temperature.

→ Mid-range water reducers provide more consistent setting times than normal water reducers. Higher water reductions by incorporating large amounts of these admixtures, result in undesirable effects on setting, air content, segregation, bleeding and hardening.

→ A new class of water reducers, chemically different from the normal and mid-range water reducers and capable of reducing water content by about 20 to 40 percent has been developed.

→ The admixture belonging to this class are popularly known as high-range water reducers (HRWR) or superplasticizers. These can be added to a concrete mix having a low-to-normal slump and water-cement ratio to produce high-slump flowing concrete.

→ Flowing concrete is a highly fluid but workable cohesive concrete that can be placed homogeneously with little or no vibration or no compaction.

→ The effect of superplasticizers lasts only from 30 to 60 minutes, depending on its composition and dosage, and is followed by a rapid loss in workability. As a result of this slump loss, superplasticizers are usually added to concrete at the job site.

## Mid-range water Reducer

The mid-range water-reducing admixtures can be categorized as

a. ~~Top~~

1. Derivatives of Lignosulfonic acids and their salts (e.g. Ca, Na, NH<sub>4</sub> salts)
2. Hydroxylated carboxylic acids and their salts.
3. Modifications and derivatives of hydroxylated carboxylic acids and their salts.
4. Processed carbohydrates.

→ The Ligno-sulfonates and carboxylic acids derivatives and their salts are water reducing and set-retarding admixtures, and they are known to reduce setting times by two to four hours and water requirement by 8 to 15 percent.

→ The compressive strength at two to four hours and at 28 days is usually equal to, or little higher than that of corresponding concrete without the admixture and the strength at 28 days on later may be 10 to 20 percent higher. These may be used with accelerating or retarding admixtures.

→ Calcium sulfate (gypsum), sugar and carbohydrates also retard the set.

→ The carbohydrate derivatives and calcium lignosulfonate are used in fractions of a percent by mass of the cement.

7 The dosage of hydroxylated carboxylic acid derivatives range from 0.1 to 0.2 percent by mass of cement.

→ These admixtures are more effective than lignosulfonates in mixes of higher cement contents (say in excess of  $250 \text{ kg/m}^3$ ). They are fairly insensitive to variation in cement composition. On the other hand, modified lignosulfonates are more effective in concrete with relatively low-cement contents and dosage would vary from 0.1 to 0.2 percent for sodium lignosulfonate and 0.2 to 0.5 percent for calcium lignosulfonate.

High-range water Reducers or superplasticizers

→ These admixtures are principally surface active agents (surfactants). They confer negative charge on individual cement particles (and also its hydrated particles) such that they are kept in dispersed or suspended state due to inter-particle repulsion. Thus they confer high resistance to the particles.

→ superplasticizers enable the optimization of water content or water-cement ratio and workability. Both the functional effects - providing enhanced plastic and hardened physical properties - are achieved simultaneously by the use of superplasticizer.

→ An ideal superplasticizer is most effective and reliable dispersant which produces a cohesive low-viscosity rheology without inducing tendency to segregate, bleed and foam, with little interference with hydration, and compatible with different cement types and with

other commonly used chemical and mineral add  
→ A simple way of utilizing the superplastic  
is to proportion the ingredient of the mixer  
to produce the required hardened physical  
properties and then and sufficient super-  
plasticize to achieve required consistency &  
workability.

### Specialty category Admixtures:-

#### (i) Grouting admixtures:-

→ Grouting has become one of the most important  
operations in civil

→ Grouting below the base part (or) machine fun-  
ctions grouting of foundation both holes in in-  
sulated structures, grouting of prestressed con-  
crete ducts, grouting in anchoring and rock bol-  
ing systems, grouting of curtain walls, grouting  
of fractured rocks below dam foundations, grouting  
the body of the newly constructed dam itself  
grouting of deteriorated concrete (or) face of  
of structure for strengthening and rehabilitation  
grouting of oil wells are some of the few situa-  
tions where grouting is extremely used.

→ The grout material should have high early or  
ultimate strength, should be free flowing even  
at low water content, should develop good  
bond with previously set (or) hardened concrete  
essentially it should be non-shrink in nature

→ The grouting materials can be broadly classified  
into two categories one is free flow grout for use

machine foundations, foundation belts and string crane rails.

→ The second category of grout is mixed for injection grouting to fill up small cracks and is normally accomplished under pressure.

→ Some retarders are especially useful in cement grout slurries particularly where grouting is prolonged (a) in the cases where the grout must be pumped for a considerable distance (b) where hot water, high temperature & surrounding are under ground.

→ Cement grouts containing pozzolanic materials are often used in cement paste and oil wells.

→ Admixtures are also used to prevent the rapid loss of water from cement paste.

→ Some of the grouting admixtures are gels, lumps pregelatinized starch, methyl cellulose.

## 2) Air-detraining Admixture:-

→ These materials are used to:-

(i) dissipate excess air (ii) other gases.

(iii) Remove a part of entrained air from a concrete mixture.

→ Air detraining admixture is tributyl phosphite, tributyl phosphite, water insoluble alcohols & silicons.

→ mostly used air detraining admixture is tributyl phosphite.



## 2. Non-contraction Admixtures:-

### 3) Gas-forming Admixtures:-

(Concrete) @ mortar

Hydroxide

Minute bubble of hydrogen  
0.1 to 1mm.

→ These admixtures when added to mortar @ concrete mixture react chemically with hydroxide present in the cement & form minute bubble of hydrogen gas of size ranging from 0.1 to 1mm, throughout the cement-water matrix.

→ This action is when properly controlled causes a slight expansion in plastic concrete @ mortar and thus negates @ eliminates voids caused by normal settlement that occur during the placement of concrete.

→ It also forms around the minute bubble which prevents the concrete from bleeding.

→ Larger amount of water increases the expansion appreciably resulting in a gas-filled light weight low strength concrete.

→ These are also called foamed concrete @ aerated concrete @ cellular concrete.

→ These concrete are light weight and used for thermal insulation.

#### 4) Corrosion Inhibiting Admixture:-

- Corrosion inhibiting admixtures are used to slow down corrosion of steel reinforcement in concrete etc.
- They are used as a defensive strategy for concrete structures constructed in marine facilities, highway bridges, industrial environment where reinforced cement concrete is exposed to high concentration of chloride.
- Compounds such as sodium benzoate, sodium nitrate etc. can be used as corrosion inhibiting admixture.
- A 2 percent benzoate solution is mixing with water may be used to prevent corrosion of reinforcement, sodium nitrate has been found to be effective in preventing corrosion of steel in concrete containing calcium chloride.

#### 5) Shrinkage reducing Admixture:-

- The shrinkage reducing admixture, also called "expansion-producing admixture", either expands themselves or react with other constituents of concrete resulting in expansion.
- This expansion may be of about the same magnitude as the drying shrinkage at later ages or may be little greater.
- This concept has been used in the development of non-shrinking cement wherein the expansion producing compound is mixed with cement in

appropriate proportion to get the desired expansion or shrinkage compensation.

→ Higher proportion of expansion-producing admixture is employed to produce self-stressing cement.

→ shrinkage compensating type expansive cement is capable of developing 0.03 to 0.10 percent restrained concrete expansion.

→ The high expansion self-stressing cement is generally capable of developing up to 0.25 percent restrained concrete expansion and can attain stress levels up to 7 MPa.

→ This will be adequate to produce prestressed (precast) concrete members.

→ Expansive cements have greater water demand than OPC. Larger water content gives enhanced workability to fresh concrete, better pumpability and easier finishing characteristics. However, to compensate for serious slump loss in hot weather a small dosage (0.05 percent) of citric acid can be used as a retarder.

→ A number of expansion producing agents have been reported, such as granulation iron chemicals, and anhydrous sulfatolumina, etc. Granulated iron and chemicals promote oxidation of iron resulting in the formation of iron oxide, which occupies an increased solid volume.

These admixtures are employed in laying heavy machine foundations, patching, production of shrinkage compensating concrete which is free from shrinkage cracks, and production of self-stressing and pre-stressed concretes, grouting the ducts of post-tensioned members, grouting foundation holes, cast-in-situ joints of precast construction, and also introducing self-stress in the concrete. Shrinkage compensating expansive cements are particularly useful in avoiding cracking in large surface area concrete structures such as runways, continuous bridge decks, large parking areas, large slabs etc.

#### (6) Water (or) Damp proofing Admixtures:-

→ Water under pressure and in contact with one surface of concrete, can be forced through channels between the two surfaces. The water passing in this manner is a measure of the permeability of concrete.

→ Water can also pass through concrete by the action of capillary forces. The materials used to reduce the water flow by the first method are termed permeability reducers, whereas the materials used to reduce second type of flow are more properly called damp-proofers.

→ A concrete having proper mix proportions, low water-cement ratio and sand aggregate will be

impervious and need no additives. However, the resistance of concrete to the penetration of moisture can be improved by adding chemically active water-repelling agents like soda and potash-soaps to which are sometimes added lime or calcium chloride.

→ These admixtures prevent the water penetration of dry concrete, or stop the passage of water through unsaturated concrete. The water proofing admixture may be grouped into the following four categories.

### 1. Chemicals which react with hydration products of cement

→ These admixtures react with hydration products of cement and form thin hydrophobic layer within pores and voids and on surface of the concrete.

→ This type of admixture is based on liquid fatty acids present in vegetable and animal fats.

→ They may be in the emulsified form or pre-mixed with ~~fat~~ inert fillers such as talc or silica flour for uniform dispersion in the concrete mix.

### 2. Chemical which coalesce on contact with hydration product

→ These are finely divided wax emulsions which break down on coming in contact with alkaline environment in cement concrete and form hydrophobic layers in pores, voids and on

the surfaces.

### 3. Finely divided hydrophobic materials:-

Calcium stearate and aluminium stearate for hydrophobic layers in the concrete pores and widely used in precast industry.

### 4. Finely divided fillers:-

Mineral additives such as pozzolana, silica fume, kaolinite when added in lean concrete mix improves water tightness by pozzolanic action and with physical filler effect.

### 7. Bonding Admixture:-

When fresh concrete is placed over a concrete surface already wet and at least partially cured, the fresh concrete shrinks while setting which makes the new concrete pull away from the old surface.

Due to this reason, the old surfaces are usually prepared so that the aggregates are exposed on clean which makes the cement paste in the freshly placed concrete bond the aggregate in the same way as it bonds the aggregate in the new mix.

Cement paste slurry is often applied to the prepared old surface immediately prior to pouring new concrete to increase the amount of paste available at the surface for bonding purpose.

In situation where such a treatment cannot be applied, the bonding admixtures can be used to join two surfaces.

These admixtures increase the bond strength between the old and new concrete.

→ The major application includes overlay on an existing pavement, provision of screed over mat for waterproofing, repair work, etc.

→ There are two types of bonding admixtures in use. In the first type, the bonding is accomplished by a metallic aggregate and in the other synthetic emulsions are used.

→ The metallic aggregate type of admixture consists of fine cut iron particles to which is added a chemical that causes them to oxidize rapidly when mixed with Portland cement and water.

→ The rapid oxidation of the iron particles in the cement slurry applied over the old concrete surface results in the expansion of iron particles.

→ They form fingers that thrust out into both the old and the new concrete, bind them together.

→ This admixture can also be used as waterproofing by applying additional coats - successive coats build up a thin but dense watertight film over the surface.

→ There are a number of types of synthetic latex bonding admixtures, which essentially consist of highly polymerized synthetic organic resins dispersed in water. The commonly used polymer bonding admixtures are made from natural rubbers, synthetic rubber or any of a large number of organic polymers or copolymers.

→ The polymers include polyvinyl chloride, polyvinyl acetate, acrylics and butadiene styrene copolymers.

→ These admixtures are water emulsions, which are

generally added to the mixture in proportions not to 5 to 20 percent by mass of cement depending on

### B. Concrete Surface -hardening Admixture :-

→ The plain concrete surfaces subjected to heavy traffic on the industrial buildings continuously subjected to wear and tear deteriorate after a period of time.

→ The factory floor, on account of movement of materials, iron tyred trollies, vibrations caused by running machines is likely to suffer damages. Wear resistant and chemical resistant floor must be provided in the beginning. Replacing and repairing of old floors will interfere with the productivity and prove to be costly.

→ The hardener commonly used to prevent the destruction of the surface can be divided into two groups, namely, the chemical hardeners and fine metallic aggregates.

→ The hardeners commonly used to prevent the destruction of the surface can be divided into two groups, namely, the chemical hardeners and fine metallic aggregates. The liquid chemical hardeners consist of silicate solvents or fluoboric acid and a wetting agent.

→ The latter reduces the surface tension of liquid and allows it to penetrate the pores of the concrete more easily. The chemicals combine with free lime and calcium carbonate present in concrete to bind the fine particles into highly wear resistant hard like topping.

→ On the other hand, the metallic hardeners consisting of specially prepared grade iron particles are dry mixed with Portland cement which is spread evenly over to freshly finished concrete surface and are worked



into concrete by floating. This gives highly wear resistant and less brittle concrete topping.

Sometimes abrasive materials like fine particles of flint, aluminum oxide, silicon, corundum, or emery are used in the topping applied as dry shake to obtain water-resistant non-slip surfaces.

#### 9. Concrete Coloring Admixtures or Pigments.

Pigments are the admixtures added to concrete color cements. One of the methods of producing colored concrete surfaces in modern construction is to use concrete paint to be applied after the concrete surface has been neutralized, either through exposure or by using a neutralizing agent like zinc sulfate.

The other most commonly used method involves integrating color into the surface of concrete while it is still fresh. This can be accomplished by mixing natural metallic oxides of cobalt, chromium, and iron, called pigments into the topping mix. This is the best way of distributing the color evenly throughout the concrete.

The coloring admixture mixes with synthetic oxides mixed with one or more additional coloring ingredients are also available. But the pigments used must be permanent and should not react with free lime in concrete. To obtain a good coloring effect, the pigments should be ground with the cement in a ball mill. Sometimes they are mixed with fillers, like chalk, but the excessive use of fillers may affect strength of concrete. The chief pigments used in concrete are as follows.

1. Black:- The best permanent black pigment is carbon black, but manganese black gives a brown tint whereas magnetic iron oxide has a grey-blue tint.
2. Blue:- The materials used are barium manganate and ultramarine. Sulfur fumes in paint & atmosphere adversely affect the former. Ultramarine is used for concrete used in non-wearing surface.
3. Brown:- Raw umbers or burnt umbers form satisfactory brown pigments.
4. Green:- Artificially produced chromium oxide and chromium hydroxide are suitable.
5. Red:- The most commonly used material is the naturally occurring red oxide of iron.
6. Yellow:- Hydroxides of iron give yellow color.

#### 10. Fungicidal, Germicidal and Insecticidal Admix-

7. Certain materials like polyhalogenated phenols, iodine emulsions and copper compounds when added as admixtures impart fungicidal, germicidal or insecticidal properties to the hardened cement pastes, mortars or concretes.

into concrete  
residual and  
sometimes  
fine, and  
can be washed  
off with water.

Black pigment is often  
by a brown fine  
with water.

Light  
Tough  
Stiff

## Workability

- The diverse requirement of mixability, stability, transportability, placeability, mobility, compactability, finishability of fresh concrete mentioned above are composite property.

→ Workability is that property of freshly mixed concrete @ mortar which determines the ease homogeneity with which it can be placed, compacted & finished.

→ Workability of a fresh mix concrete is a complex system of two critical parameters consistency & homogeneity.

→ A mixture could have a fluid consistency of fresh concrete varies from situation to situation. It may be very placeable, if it segregates it would not be considered to have good consistency & homogeneity.

→ Thus for optimal purpose @ performance the consistency & homogeneity must be balanced.

→ A concrete may not be workable when compacted by hand but may be satisfactory when vibration is used.

## Consistency

→ Consistency is relative mobility or ability of a freshly mixed concrete to flow to and the usual requirements are slump test concrete, flow for mortar or grout and penetration resistance for neat cement paste.


→ It is thus a measurement of one dimension of workability. It does not indicate whether

or not a low viscosity mix has the cohesion to be placed without segregation and bleeding.

- ✓ Different concrete mixed with the same consistency can have different workability characteristics. Major factors affecting consistency are:
  - water content: cement content and its characteristics, plasticity of the cement paste, aggregate content and its characteristics, air content, temperature, mixing conditions, chemical admixtures and mineral admixtures used.

✓ Addition of superplasticizer improves consistency by dispersing the cement particles and reducing the viscosity of the cement paste.

- ✓ Increasing the water content will also improve consistency and can be resorted to if the negative effects of extra water represented by bleeding, segregation and lower strength can be tolerated.

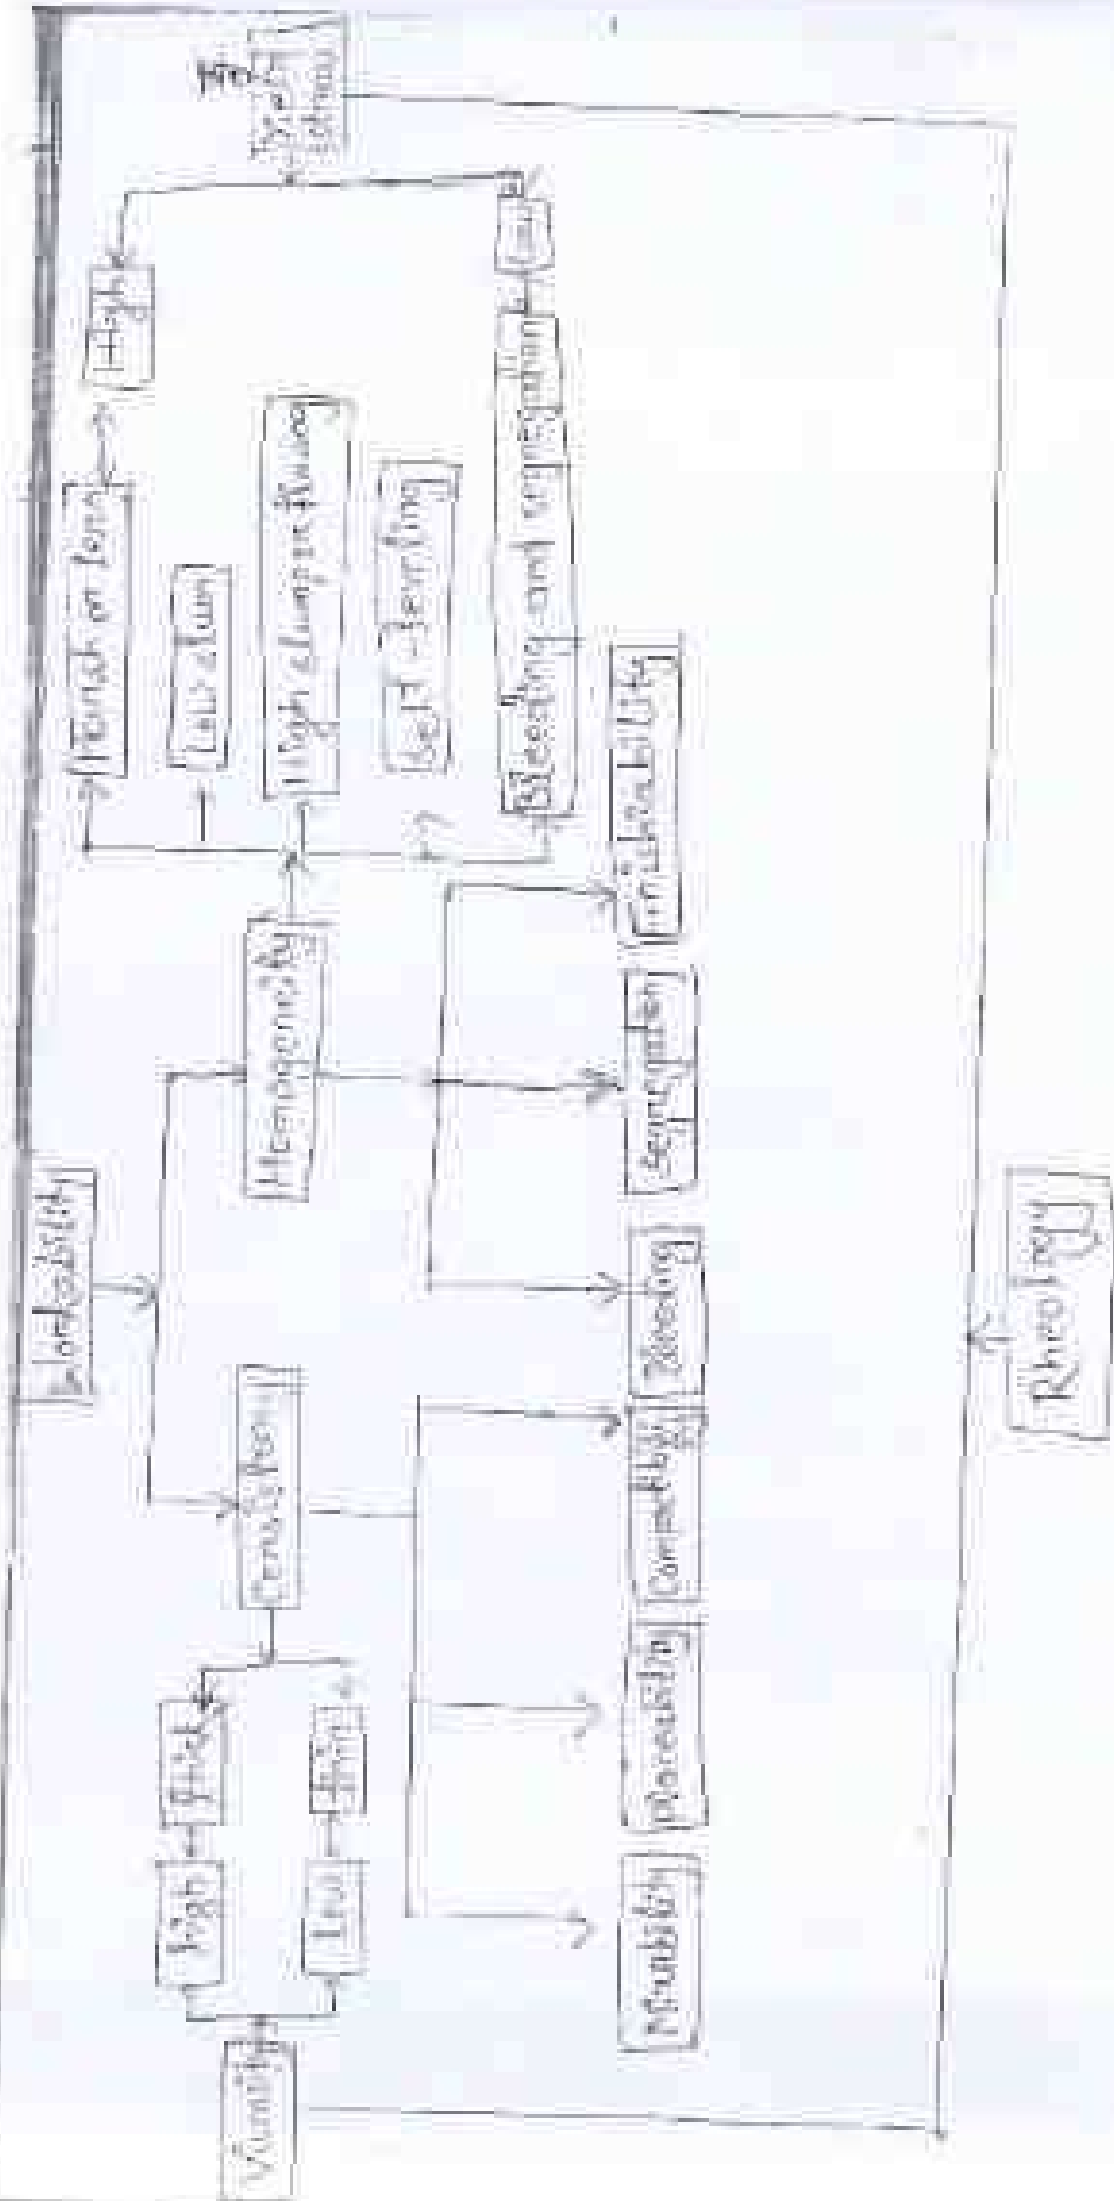

## Homogeneity

which means uniform and stable distribution of cement, aggregate and water, and moisture. Segregation is a critical physical property of plastic concrete.

→ This property does not have standardized test method for its measurement. The standardized tests for measurement of workability, namely flow spread and slump tests, measure consistency, not the homogeneity. To measure the homogeneity property it is necessary to use a rheometer instrument that measures yield stress and plastic viscosity.

→ A reduction in viscosity increases flow and improves consistency. Low viscosity mortar with superplasticizer has relatively high stress and high plastic viscosity and therefore is more resistant to segregation and bleeding.

→ Low viscosity is essential for ease of placement with cohesion. It should be noted that viscosity and plastic viscosity are different properties.

→ The presence of excess mixing water, undermixing and overmixing are common cause of many problems related to physical properties of concrete in plastic and hardened states.

→ The addition of superplasticizer improves the setting and workability of the concrete mix. It reduces yield stress which means less mixing energy and time are required. It improves homogeneity of the various mineral additives and admixtures.

## \* Measurement of workability:-

- The quantitative assessment describing concrete as being of high or low workability on a scale of 1 to 10 or plastic, etc. may mean different things to different people.
- The commonly - used practice of defining this physical property by a numerical scale based on the empirical tests for its measurement has been found to be unsatisfactory in many subjects. A more reliable assessment rather than on empirical tests.
- A number of different empirical tests are available for measuring the workability of fresh concrete but none of them is wholly satisfactory. Each test measures only a particular aspect of it and there is really no unique method which measures the workability of concrete in its totality.
- However, by checking and controlling the uniformity of the workability, it is easier to ensure a uniform quality of concrete and hence uniform strength in particular jobs. The empirical tests widely used are:

1. Slump test
2. Compacting Factor test
3. Vee-Bee consistency test
4. Flow test

→ A typical test apparatus of these four tests, the slump test is perhaps the most widely used, primarily because of the simplicity of the apparatus required and the test procedure.



7 The slump test indicates the behavior of a concrete cone under the action of gravitational forces.

7 The test is carried out with a mold called the slump cone. The slump cone is placed on a horizontal and non-absorbent surface and filled in three equal layers of fresh concrete, each layer being tamped 25 times with a standard tamping rod.

7 The top layer is struck off level and the mold is lifted vertically without disturbing the concrete cone. The subsidence of concrete in millimeters is termed the slump. The concrete tapers called true slump.

7 In the case of very lean concrete, one-half of the cone may slide down the other which is called a shear slump. or it may collapse in case of very wet concrete.


7 The slump test is essentially a measure of consistency or the wetness of the mix. The test is suitable only for concretes of medium to high workability (i.e., having slump values 25 mm to 125 mm) for very stiff mixes having zero slump, the slump test does not indicate any difference in concretes of different workability.

7 It must be appreciated that the different concretes of the same slump may, indeed have different workabilities under the site conditions.

7 However, the slump test has been found to be useful in ensuring the uniformity among different batches of specially ordered concrete under field conditions.

7 The slump test is limited to concretes with maximum size of aggregate less than 38 mm.

- 7 The compacting factor test gives the behavior of fresh concrete under the action of external force.
- It measures the compactability of concrete which is an important aspect of workability, by measuring the amount of compaction achieved for a given amount of work.
- The compacting factor concrete mixes of medium and low workabilities i.e. compacting factor of 0.9 to 0.8, because the test is more sensitive and gives for concrete of very low workabilities of order of 0.30 or below, the test is not suitable, because this concrete cannot be fully compacted for comparison in the manner described in the test.

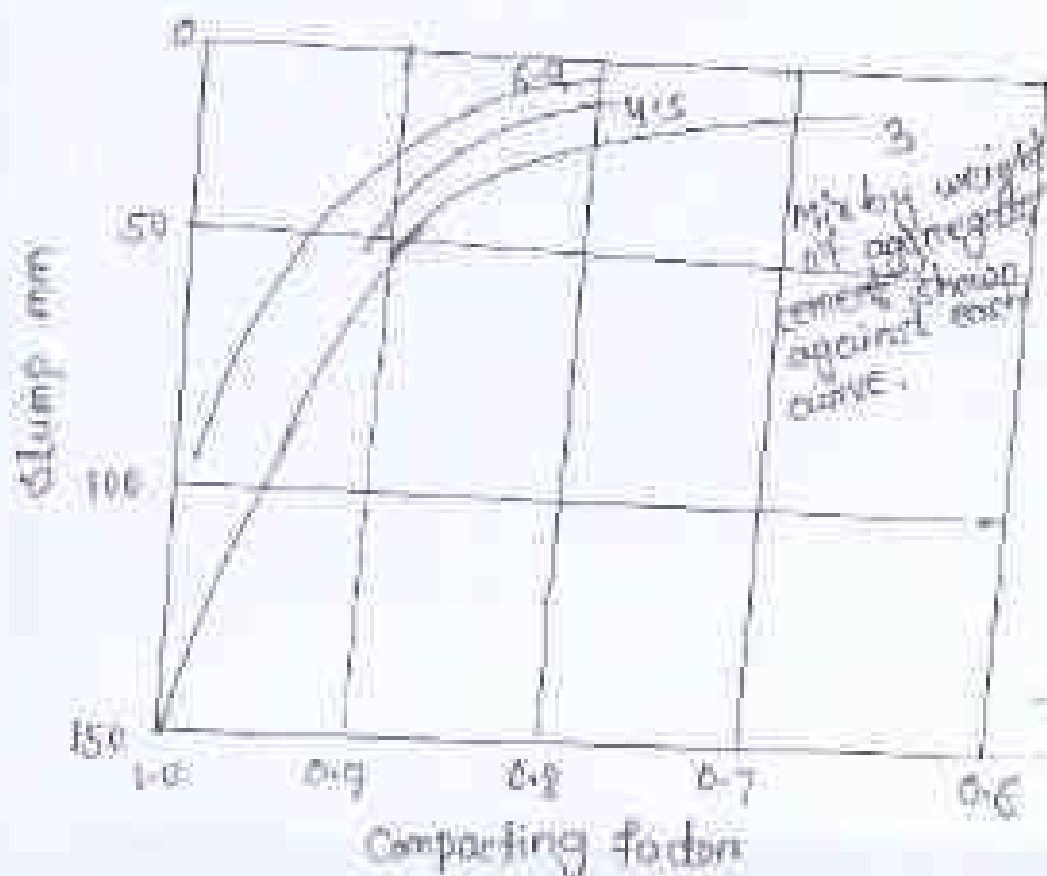

having low and very low workability.

7 Compared to the slump test and compacting factor test, the vee-bee test has an advantage that the concrete in the test receives a similar treatment as it would in actual practice.

7 The test consists in molding a fresh concrete cone in a cylindrical container mounted on a vibrating table.

7 The concrete cone when subjected to vibration ~~falls~~ by starting the vibration starts to occupy the cylindrical container by the way of getting re-molded.

7 The remolding is considered complete when the concrete surface becomes horizontal.

7 The time required for complete remolding in second is considered as a measure of workability and is expressed as the number of vee-bee rings.

7 Since the end point of the test when the concrete surface becomes horizontal is to be ascertained visually, it introduces a source of error which is more pronounced for concrete mixes of high workability and consequently records low vee-bee time for concrete of slump in excess of 125 mm measured.

7 The test is therefore, not suitable for concrete of higher workability that is slump less than 75 mm or above.

7 This test gives the satisfactory performance for concrete of the consistency for which slump


can be used.

The test consists of mounding a fresh concrete core on the top of the platform of flow table, and then giving 15 falls of 125 mm magnitudes.

→ The spread of the concrete, measured as the maximum diameter of core.

→ It is taken as a measure of the flow or consistency of the concrete.

→ The test suffers from the drawback that the concrete may scatter on the flow table with a tendency towards segregation.

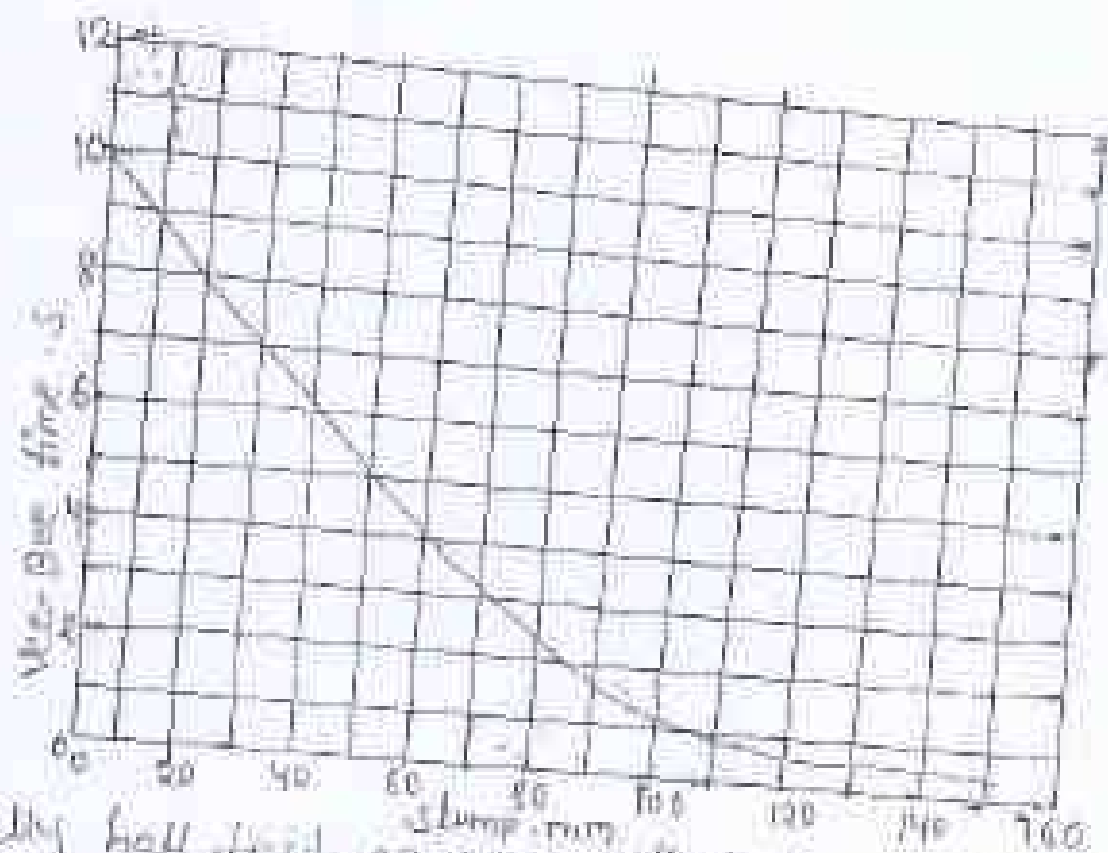

→ Kelly ball test, or ATM method, is a simple field method for measuring the consistency of plastic concrete.

→ The apparatus is a simple portable metal ball that penetrates the surface of concrete.

→ It can be performed on the in-place concrete.

much faster and accurately.

7 Test results are accurate, reliable and compare favourably with results obtained through the more commonly known and used slump test.

7 The Kelly ball test device consists of a cylindrical metal plunger with a hemispherically shaped metal ball of 150 mm diameter and 45 mm height at the bottom and a handle at the top.

7 The total assembly weight is 10 kg.

7 A stirrup frame guides the plunger and acts as reference for measuring the depth of penetration.

7 The plunger is graduated for notice the penetration.

7 The semicircular bearing plates at each foot of the frame serve to prevent the frame from tilting.

7 There is movable pinch clamp which makes it easier to measure the depth of penetration.

7 This clamp is attached to the top of the plunger where it remains until the ball has penetrated the concrete.

7 Then the clamp is lowered until it comes in contact with the frame.

7 When the entire apparatus is removed from the concrete the position of the clamp on the handle gives the depth of penetration of ball.

7 The apparatus can be mounted on a simple wooden base with a bin can for holding water for wiping the ball clean just.

In addition to carrying the apparatus, it acts as a hand board for the person testing the wet concrete. The test can be performed quickly and easily at the job site either directly in the fresh concrete or in a separate container.

The ball is held vertically by the handle and brought in light contact with the concrete surface. The zero mark on the rod should appear at the level of the frame.

(2) The handle is released and the ball is allowed to sink freely into the concrete. The depth of the penetration is indicated by the reading on the plunger which has slipped up through the frame from the zero mark. It is not necessary to make any adjustment for the slight sinking of the bearing plates into the concrete.

(3) At least three separate measurements of penetration are obtained for each batch. Each test is performed with the foot of the frame at least 150mm away from the place where it rested in the previous test. The consistency is based on an average of first three penetration readings. A penetration of 250mm

measured by the Kelly ball method approximately can  
penetrate about 20mm of slump.

→ The following precautions should be taken.

(a) If the test is performed at the site the pres-  
sure should be measured at least 225mm away  
from the nearest face of any form or wall in case  
of pavement concrete test. The horizontal distance  
of 225mm is between the penetration point on the  
subgrade and the form edge of the finished lower  
section of concrete.

(b) The minimum depth of concrete to be tested with  
Kelly should be more than the largest of 50mm  
or there fines the maximum size of the aggregate  
used.

(c) The surface of concrete to be tested for consist-  
ency should be smooth and level. The disturbance of the  
concrete caused by the ball should be limited to  
as small an area as possible.

→ The major advantage of the Kelly test is that  
it can be performed at the job site thus eliminat-  
ing the time and effort required to prepare sam-  
ples to be used in the laboratory.

→ Three or more Kelly ball tests can be made in  
a time less than it takes to make one slump test,  
thus eliminating any delay in finishing operations.

→ The Kelly ball test device is easy to carry to the  
job site and can be used for further test simply  
by cleaning the ball with an oily rag.

→ The Kelly ball device can be used for measuring  
the consistency of stiff mixture of concrete with

7. The ~~test results~~ of ~~concreting~~ the ~~approximate~~ concrete are a fair basis for the present position and concrete.
- Large size coarse aggregate as long as adequate depth is available for penetration.
7. Lightweight concrete and mass concrete containing aggregate as large as 150mm can be tested in the areas free from these large stones.
- As each of the above tests measures only a particular aspect of workability there is no right correlation between the workability of concrete as measured by different test methods.
7. In the absence of definite correlations between different measures of workability under different conditions, it has been recommended that, for a given concrete, the appropriate test method be decided by ~~the~~ hand and workability be expressed in terms of such a test only, rather than than be interpreted from the results of other tests.
7. In addition to the specific faults inherent to each test, the major drawbacks are summarized below:
- (1) The tests are quite arbitrary and empirical as far as the measurement of workability is concerned because each of these test is a single point test measuring a single quantity which at times may classify two such concrete identical which may behave quite different by on the job.
- (2) The results from these tests are influenced by minor variations in technique of carrying out the test.



## Properties of fresh concrete :-

### ① Strength :-

- Concrete has good strength against compression. It is moderately weak in tension & bending.
- Compressive strength of concrete is ~~also~~ mainly defined by the amount of cement applied, but it is also influenced by the ratio of water to cement, mixing & placing as well as the stability & range of hydration & curing.
- Tensile strength generally varies from 7 to 8% of compressive strength and raised with the addition of steel & fibre reinforcements.

### ② Durability :-

- Durability means the capacity to retain strength & performance over an extended service life.
- Concrete uncovered on the outside of a building should have good resistance capacity against weathering, freezing & thawing.

### ③ Volume stability :-

- All materials are enlarged & contracted with variations in temperature & as the concrete is a porous material, it also enlarged & contracted with variations in moisture content.
- Concrete based product like concrete, concrete, concrete, etc. are undergoing shrinkage by evaporation of moisture.
- Extreme shrinkage can lead to cracks as a result the moisture enters into concrete.

### (4) Workability:-

- Workability belongs to the relative ease with which a fresh concrete mix is placed, arranged, compacted & finished devoid of segregation or separation of the materials.
- Proper workability is necessary to form inexpensive & superior quality concrete.
- Fresh concrete contains strong workability if it can be developed, compacted & finished to its final shape.

### (5) Consistency:-

- Consistency stands for the aspect of workability associated with the flow characteristics of fresh concrete.
- It signifies the fluidity or wetness of a mix & is computed with slump test.
- A high-slump concrete mix is very fluid, whereas a lower slump concrete is drier & more harsh.

### (6) Cohesiveness:-

- Cohesiveness means the element of workability which specifies whether a mix is harsh, sticky or plastic.
- Harshness may occur by an excess of rough, angular, flat or elongated aggregate particles.

## Requirements of workability:-

~~concrete should be such~~

- The workability of fresh concrete should be such that it can be placed in the form work and compacted with minimum effort, without causing segregation and bleeding.
- The choice of workability depends upon the type of compacting equipment available, the size of the section and concentration of rebar reinforcement.
- Compaction by hand using rodding and tamping is not possible when compacting factor is less than 0.85.
- Ordinary techniques of vibration are not applicable if the compacting factor falls below 0.70.
- In such cases, techniques like vibro-pressing have to be adopted.
- Heavily reinforced sections or when the sections are narrow or contain in a recessed parts or when the spacing of reinforcement makes the placing and compaction difficult, the workability should be high to achieve full compaction with reasonable amount of effort.
- The equipments of workability generally require for different conditions of placement of concrete.
- The range of values indicates not considered suitable for concretes having aggregate of a nominal maximum size of 20mm.
- The value of workability will generally increase

with the increase in the size aggregate and will be somewhat lower for aggregate of smaller size than indicates.

→ The workability should be assessed depending upon the situation at hand.

→ The aim should have the minimum possible workability consistent with satisfactory placement and compaction of concrete.

→ An insufficient workability may result in improper compaction, resulting there by severely affecting the strength, durability and surface finish of concrete and may indeed prove to be uneconomical in the long run.

Segregation and Bleeding:-

Minimum The stability of a concrete mix requires that

it should not segregate and bleed during transport and placing.

→ Segregation can be defined as separating out of the ingredients of concrete mix so that the mix is no longer in a homogeneous condition.

→ Only a stable homogeneous mix can be fully compacted.

→ Two types of segregation can occur.

(i) The separating of coarse particles from the mix, termed segregation.

(ii) Segregation of cement paste from the mix in the case of lean and wet mixes termed bleeding.

→ The segregation depends upon handling and placing operations.

→ The tendency to segregate increases with the maximum size of the aggregate, amount of coarse aggregate and with the increased slump.

→ The tendency to segregate can be minimized by

(i) Reducing the height of drop of concrete

(ii) Not using vibration as a means of spreading a heap of concrete into level mass over a large area and.

(iii) Reducing the continued vibration over a longer time, as the coarse aggregate tends to settle to the bottom and the slum rises to the surface (i.e., formation of skins termed laitance).

→ The segregation of coarse particles in a lean dry mix may be corrected by the addition of a small quantity of water which improves cohesion of the mix.

→ Bleeding is due to rise of water in the mix to the surface because of the inability of the solid particles in the mix to hold all the mixing water during the setting of the particles under the effect of compaction.

→ Bleeding causes the formation of a porous weak and non-durable concrete layer at the top of place of concrete.

→ In case of lean mixes bleeding may create capillary channels in causing the permeability of concrete.

- When concrete is placed in different layers and each layer is compacted after allowing certain time to lapse before the next layer is laid, bleeding may also result in a plane of weakness between layers.
- Any laitance formed should be removed by brushing and washing before a new layer is added.
- Even compacting the surface should be avoided.

### Factors Affecting Workability:

- The workability of fresh concrete depends primarily on the properties of constituent materials, mix proportions, and environmental conditions.
- Workable concrete exhibits very little internal friction between particles and overcomes the frictional resistance offered by the formwork surface on reinforcement contained in the concrete with an appropriate amount of compacting efforts.

### Influence of mix proportions:-

- In the concrete comprising a cement aggregate-water system, the aggregate occupies approximately 70 to 75% of the total volume of economy demands that the volume of aggregates should be as large as possible.

→ The total specific area of aggregate is to be minimized to the extent possible by proper choice of size, shape and proportions of fine and coarse aggregate.

→ In a well-graded aggregate, different size fractions are so chosen as to minimize the void content and such a mixture will need more water for lubricating effects to overcome the interlocking in mobility due to dense packing of particles.

→ However, when the total voids are less, for the given amount of paste the mixture becomes cohesive and fatty which prevents segregation of particles and lubricated aggregate particles settle as well as fill the voids in the aggregate.

→ In a lean concrete, i.e., a concrete with high aggregate-cement ratio, less quantity of cement paste per unit surface area of aggregate is available for providing lubrication, and hence the mobility of aggregate is restrained. On the other hand, in case of rich concrete with low aggregate-cement ratio, more paste is available to make the mix cohesive and fatty to give better workability.

### Influence of Aggregate Properties:-

→ The effect of aggregate properties on the workability of fresh concrete can be summarized as follows:

1. For the same volume of aggregate in concrete, the use of coarse aggregate of larger size and/or rounded aggregate gives higher workability because of reduction in total specific surface area and hence less water-cement ratio.

The lesser the surface area the lesser will be the amount of water required for wetting the surface and consequently lesser cement paste will be required for lubricating the surface of aggregates to reduce internal friction.

The influence of surface texture on workability is due to the fact that the total surface area of rough textured aggregate is more than the surface area of smooth rounded aggregate of same volume.

7 The use of angular, elongated or flaky aggregate results in low workability, primarily due to increased

in the void content and inter-particle interference

7 This explains the reasons why river sand and gravel provide greater workability ~~primarily due to~~ ~~to increase in the void content and inter-particle interference.~~

7 This explains the reasons why river sand and gravel provide greater workability. The texture of crushed sand and aggregate. The size and shape of the aggregate is of paramount importance in the case of present day high strength and high performance concretes where very low water-cement ratios of the order of about 0.25 are used.

2. The use of finer sand increases the specific surface area, thereby increasing the water demand for the same workability. In other words for the same void content, the use of finer sand decreases workability.


3. Because of the greater contribution to the total specific surface area, the grading of fine aggregate is more critical than the grading of coarse aggregate.



nevertheless, the proportion of fines to coarse aggregate should be so chosen as neither to limit the total specific surface area (by excess of fine aggregate) nor to increase the particle interference (due to deficiency in fine aggregate) - An

unavailable choice of overall grading can make honeycombing or segregation in normal range of mixes through an increase in fines content reduces workability. In practice, there is an optimum fines content for maximum workability such that either an increase or decrease of fines reduces workability.

4. Generally, the mixes with higher water-cement ratio would require a somewhat finer grading and for mixes with low water-cement ratio (as in case of high strength concrete) a coarser grading is preferred. The effect of water content and aggregate size

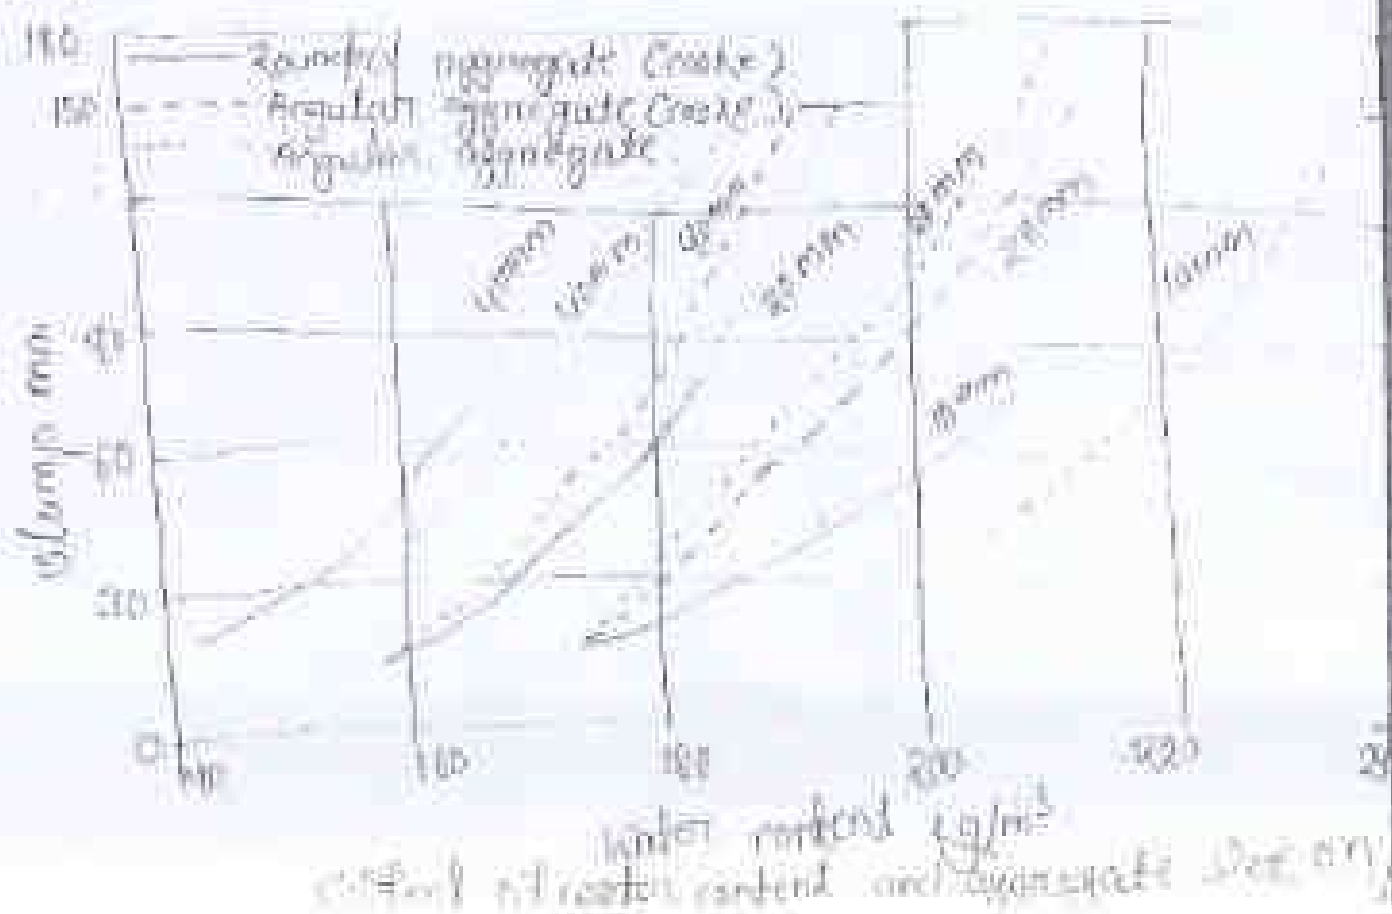

for workability of concrete.

5. The workability is also affected by the physical and chemical properties of cement, but to a much lesser extent than that by the aggregate properties. The influence of cement properties may have to be taken into account especially for higher grades of rapid-hardening cement will have reduced workability as compared to ordinary Portland cement ~~and~~ <sup>also</sup> ~~have~~ <sup>because of its</sup> higher specific surface and the fact that it hydrates more rapidly, and also the fineness of cement has an influence on bleeding.

### Influence of Admixtures

The presence and nature of admixtures and mineral additives affect the workability considerably. As described in chapter 5, the plasticizers and super plasticizers improve the workability many fold. It is to be noted that initial slump of concrete mix, also called the slump of reference mix should be about 20-30 mm to enhance the slump manyfold at a minimum dosage.

- Use of air-entraining agents which are normally surface-active, reduces the internal friction between the particles. The air bubbles may be considered as artificial fine aggregates of very smooth surface.
- They also act as a sort of ball bearing between the particles to slide past each other and give easy mobility to the particles. Similarly, the fine glassy pozzolanic materials, in spite of increasing the surface area, offer better lubricating effects for giving better workability.

## Effect of environmental conditions

The workability of a concrete mix is also affected by the temperature. On a hot day it becomes necessary to increase the water content of the concrete mix in order to maintain the desired workability. The amount of mixing water required to bring about a certain change in workability also increases with temperature.

## Effect to Time

The fresh concrete loses workability with time mainly because of the loss of moisture due to evaporation. A part of mixing water is absorbed by aggregate or lost by evaporation in the presence of sun and wind, and part of it is utilized in the chemical reaction of hydration of cement.

→ The loss of workability varies with the type of cement, the concrete mix proportions, the initial workability and the temperature of the concrete.

For an average 1:2.5:4 mix concrete may lose about 50 mm slump in the first one hour.

→ The workability in terms of compaction factor decreases by about one during the period of an hour from the time of mixing.

→ The decrease in workability with time after mixing may be more pronounced in concrete with admixtures like plasticizers. For same proportion, total time after mixing, the loss in the strength of hardened concrete simply by adding extra water.

Workability~~very~~ very Low

Low

Medium

High

Compaction Factor


0.78

0.85

0.92

0.95

Work Description	Workability Measurement		Vibration time (seconds)
	slump (mm)	Compaction Factor	
Moist earth	—	—	40 to 25
Very dry	—	0.70	20 to 15-10
Dry	0-25	0.75	10 to 7-5
Plastic	25-50	0.85	6 to 4-3
Semi-fluid	75-100	0.90	3 to 2-1
Fluid	150-175	0.95	more fluid than 1

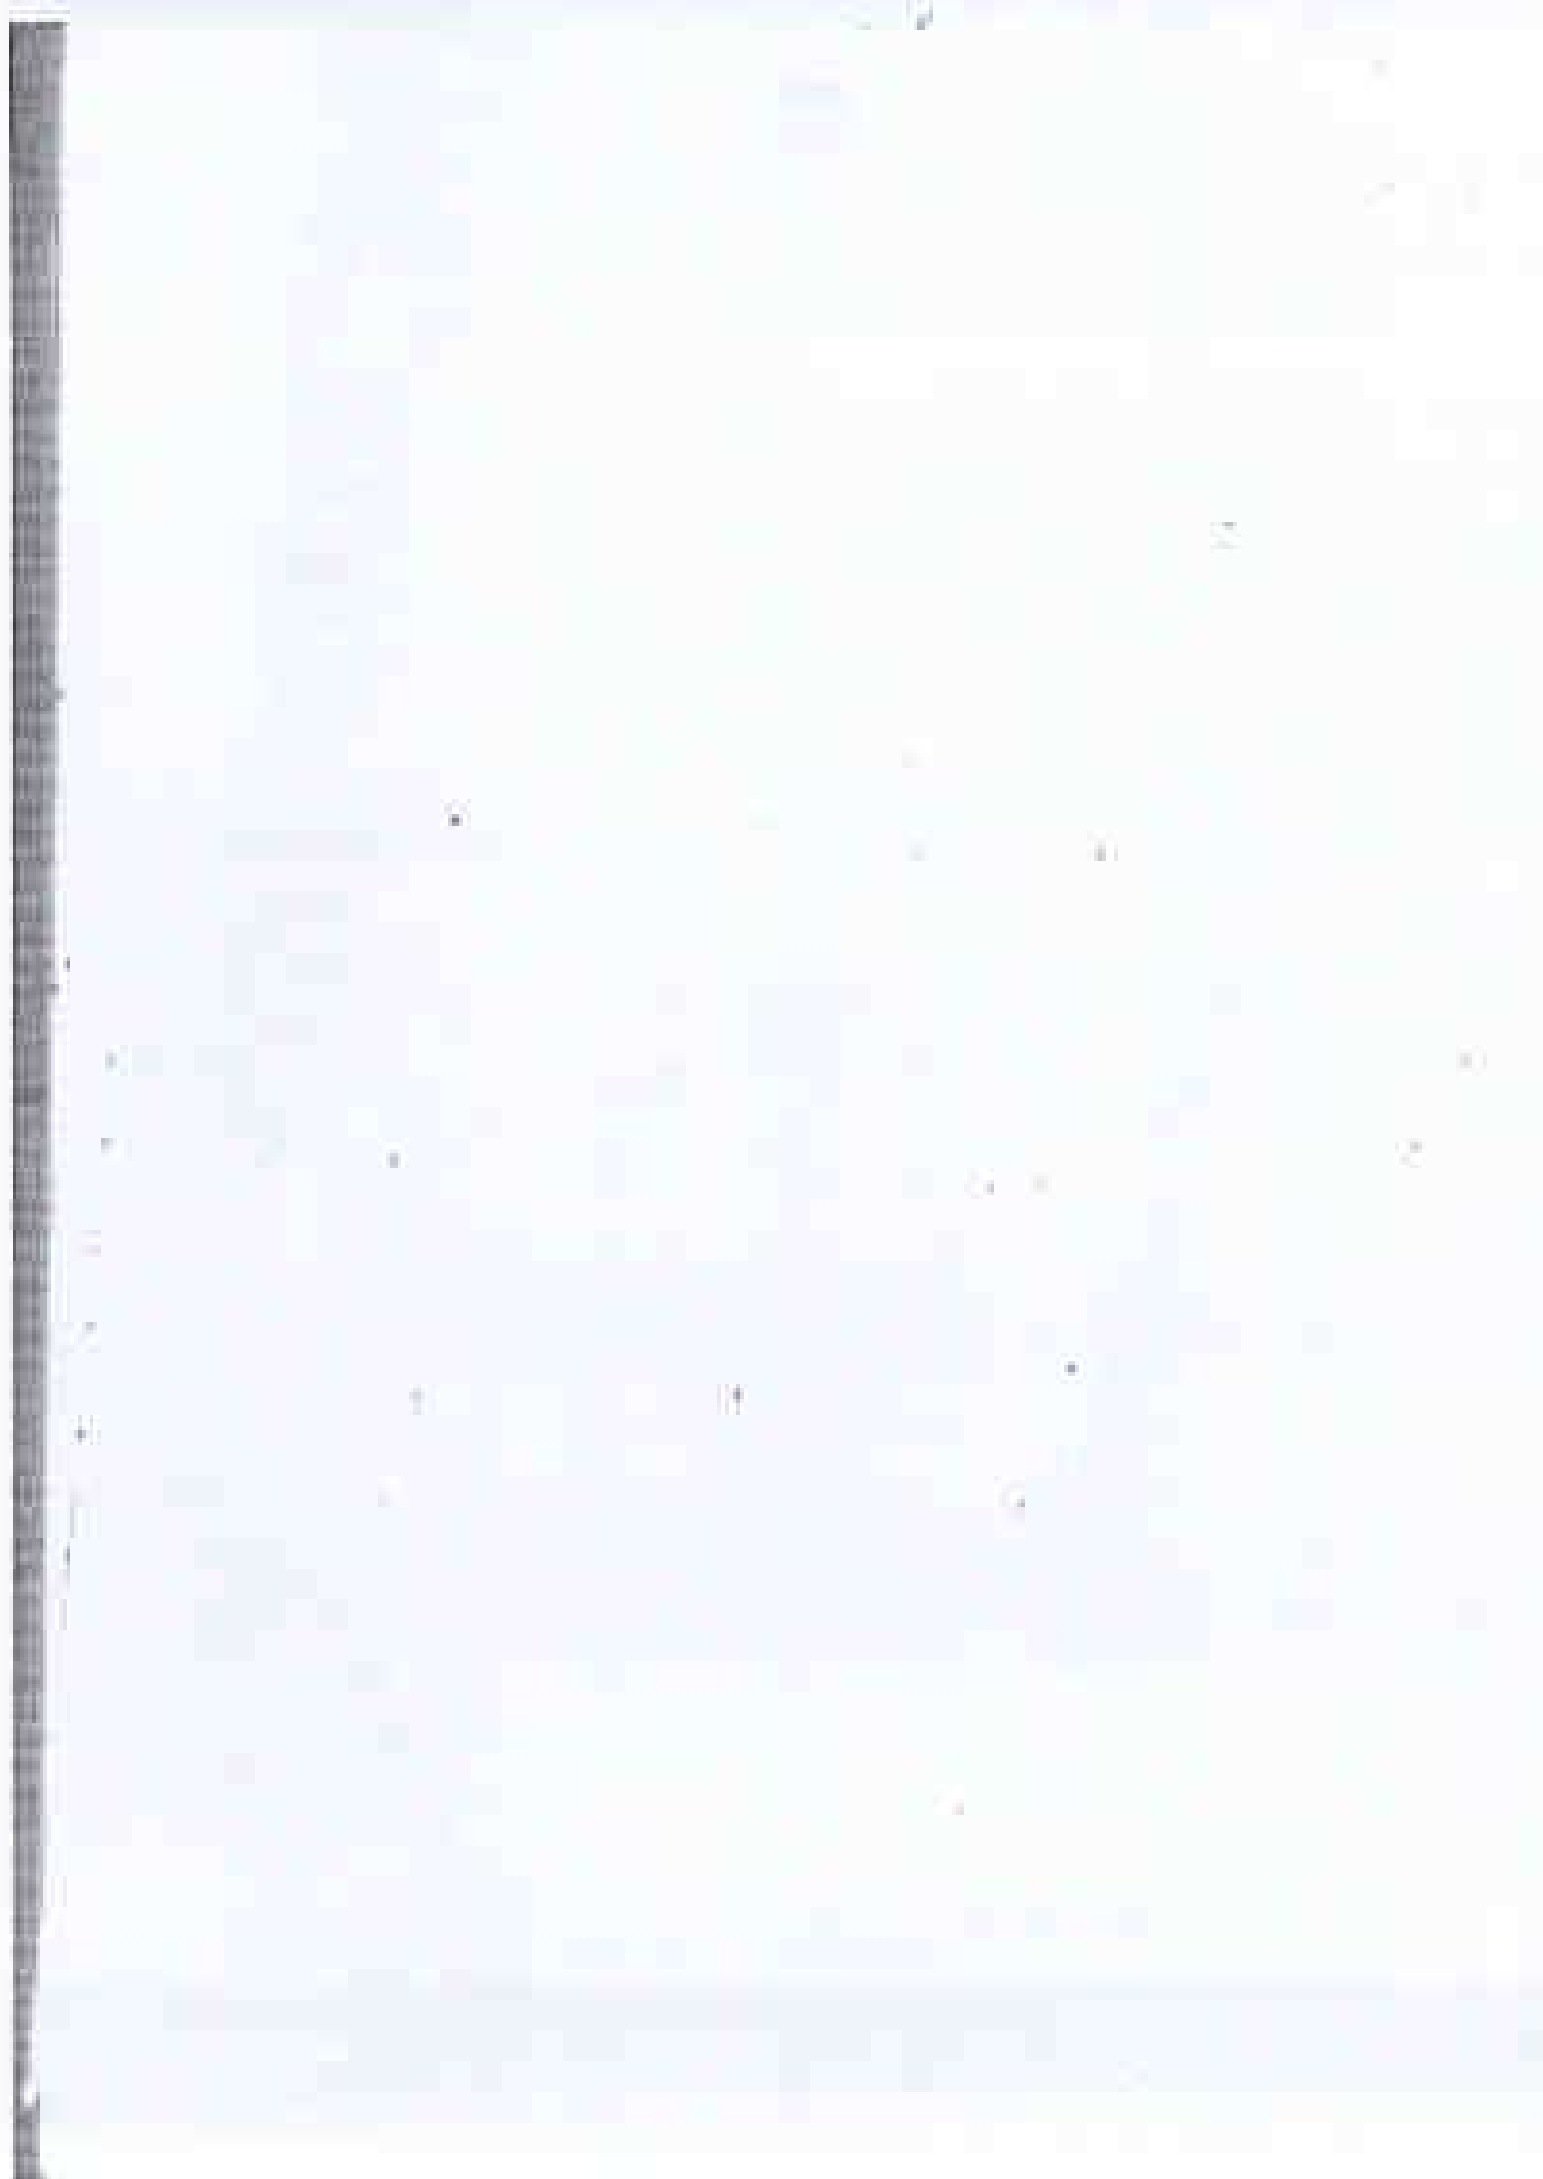

1.06.07.21

# Properties of hardened concrete New Chapter

- The principal properties of hardened concrete which are of practical importance are those concerning its strength, stress-strain characteristics, shrinkage & other deformations, response to temperature variation, permeability & durability.
- The strength of concrete at a given age under given curing conditions is assumed to depend mainly on water-cement ratio & degree of compaction.
- Absolute water-cement law in this connection is well known.
- Probable it is more correct to relate the strength of concrete to the concentration of the solid products of hydration of cement in the space available for these products.
- The voids present in concrete mixes have been found to influence greatly the strength of concrete.

## \* \* Strength of concrete :-

### (i) Compressive strength :-

#### (a) Flexural strength

→ Of the various strength of concrete, the determination of compressive strength has done by either


#### (ii) Cylinder

→ The cube one usually of 150 mm (ii) 150 mm dia. the cylinder one is 150 mm diameter by 300 mm height.

7 The specimens are cast, cured & tested as per standards prescribed for each test.

7 While cylinders are used, they have to be capped before the test.

7 The compressive strength given by different specimens for the same concrete mix are different.

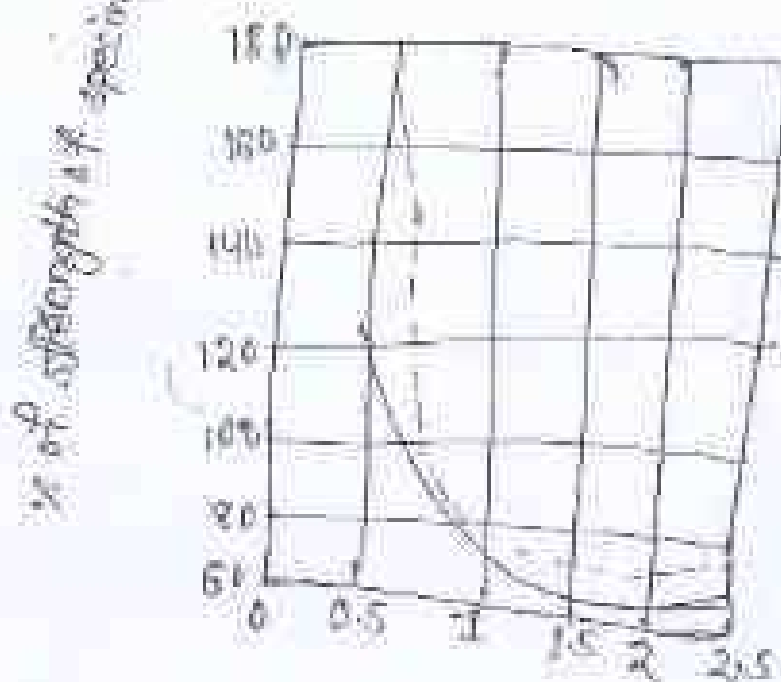

$H/D$  = Ratio of height of specimen to the lateral dimension

2) Flexural strength :-

7 The determination of flexural tensile strength is essential to estimate the load at which the concrete may crack.

7 As it is difficult to determine the tensile strength of concrete by conducting a direct tension test, it is computed by flexure testing.

7 The flexural tensile strength at failure @ the modulus of rupture is thus determined & used when necessary.

7 It is useful for designing of pavement slabs.  
7 On field runway is flexural strength @ tension.

is critical in these cases

→ The modulus of rupture is determined by testing standard test specimens of  $150\text{mm} \times 150\text{mm} \times 700\text{mm}$  over a span of  $600\text{mm}$  or  $100\text{mm} \times 100\text{mm} \times 500\text{mm}$  over a span of  $400\text{mm}$ , under symmetrical two-point loading.

→ The modulus of rupture is determined from the moment of failure as  $[f_r = \frac{M}{I}]$

→ Thus, the computation of  $f_r$  assumes a linear behavior of the material up to failure which is only a rough estimation.

→ The results are affected by the size of specimen, casting curing and moisture conditions, manner of loading, rate of loading.

→ The test is conducted & the strength is determined according to the prescribed standards.

→ The strength estimated by flexure test is higher than the tensile strength of concrete because of the assumption of the linear behavior of material up to failure in the computation of  $f_r$ .

→ The accidental eccentricity in the direct tension test may also lower the apparent tensile strength.

→ In the direct tension test, as the entire volume of specimen is under maximum stress, the probability of weak element occurring in the body of specimen is ~~higher~~ high.



3) Tensile strength :-

✓ Apart from flexural test, the other methods used to determine the tensile strength of concrete can broadly be classified as direct and indirect methods.

✓ The direct methods suffer from a number of difficulties related to holding the specimen properly to the testing machine without inducing stress concentration and to the application of uniaxial tensile load which is free from eccentricity to the specimen.

✓ Even a very small eccentricity of load will induce bending and axial force conditions and the concrete fails at apparent tensile stress other than the tensile strength.

✓ Because of the difficulties involved in conducting the direct tension test, number of indirect methods have been developed to determine the tensile strength. In these tests, in general, a compressive force is applied to a concrete specimen in such a way that the specimen fails due to tensile stress induced in the specimen.

✓ The tensile stress at which failure occurs is the tensile strength of concrete.

✓ The splitting test are well-known indirect tests used for determining the tensile strength of concrete, sometimes referred as the splitting tensile strength of concrete.




7 The test consists of applying compressive line loads along the opposite generators of a concrete cylinder placed with its axis horizontal between the platens as shown. Induced line loading is fairly uniform tensile stress is induced over nearly two-thirds of the loaded diameter as obtained from an elastic analysis.

7 The magnitude of this tensile stress (acting in a direction perpendicular to the line of action of applied compression) is given by  $\frac{2P}{\pi d L} = 0.637 P / \pi d L$ , where  $P$  is the applied load and  $d$  and  $L$  are the diameter and length of the cylinder respectively.


7 Due to this tensile stress, the specimen fails finally by splitting along the loaded diameter and knowing  $P$  at failure the tensile strength can be determined.

7 The test can also be performed on cube by splitting either (i) along its middle parallel to the edges by applying two opposite compressive forces through 15 mm square bars of sufficient length run along one of the diagonal planes by applying compressive forces along two opposite edges.

7 In the case of side-splitting of the cubes the tensile strength is determined from  $0.692 P / s^2$  and in diagonal splitting it is determined from  $0.5187 P / s^2$ , where  $P$  is the load at failure and  $s$  is the

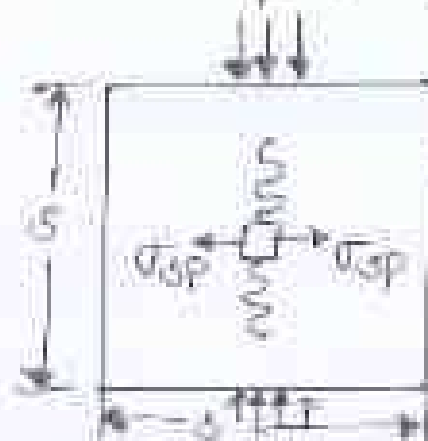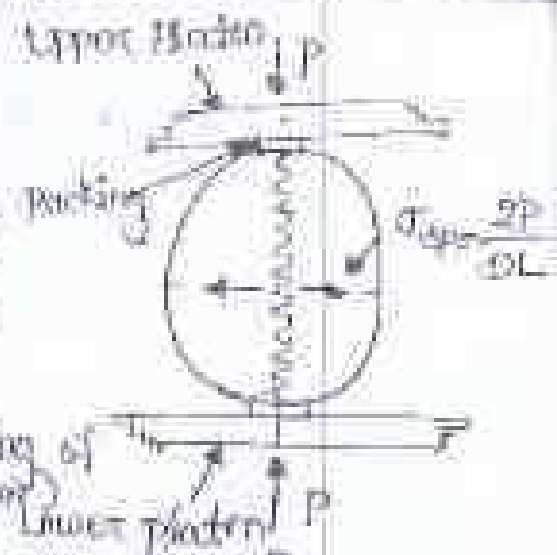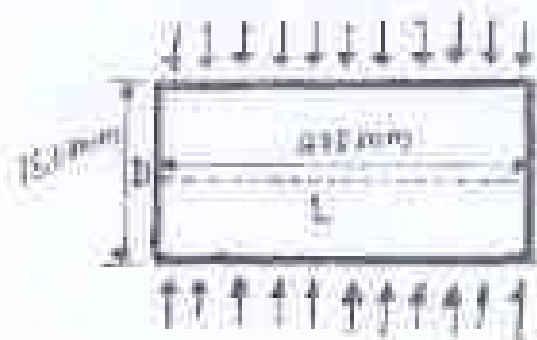

$$\sigma_{sp} = 0.518 P / \sqrt{A}$$

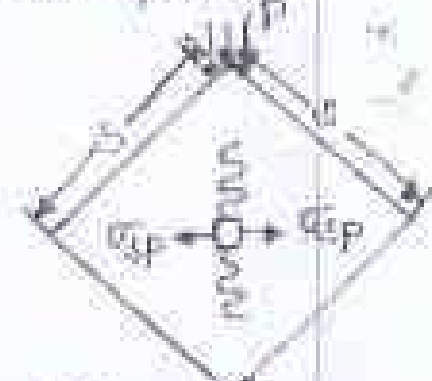

(b) Split strength testing of cubes

The relationships between compressive strength and split tensile strength, and flexural strength and split tensile strength are given in respectively.

Advantages of the splitting test for determining the tensile strength are as follows.

1. The test is simple to perform and gives more uniform results than other tension tests.
2. The strength determined is closer to the actual tensile strength of the concrete than that given by the modulus of rupture test.
3. The same molds can be used for casting specimens for both compression and tension tests.

The splitting tests have also been performed on pillars, i.e. on one-half of the specimen.

left after performing the modulus of rupture or splitting-type tests have also been done on the ring specimens to determine tensile strength. Mortar and concrete rings have been tested by subjecting them to internal pressure.

7 The double punch test is another test performed on concrete cylinders to determine the tensile strength.

\* Stress-strain characteristics of concrete:

A type 7 The relation is fairly linear in the initial stages but subsequently becomes non-linear reaching a maximum value and then a descending portion is obtained before.

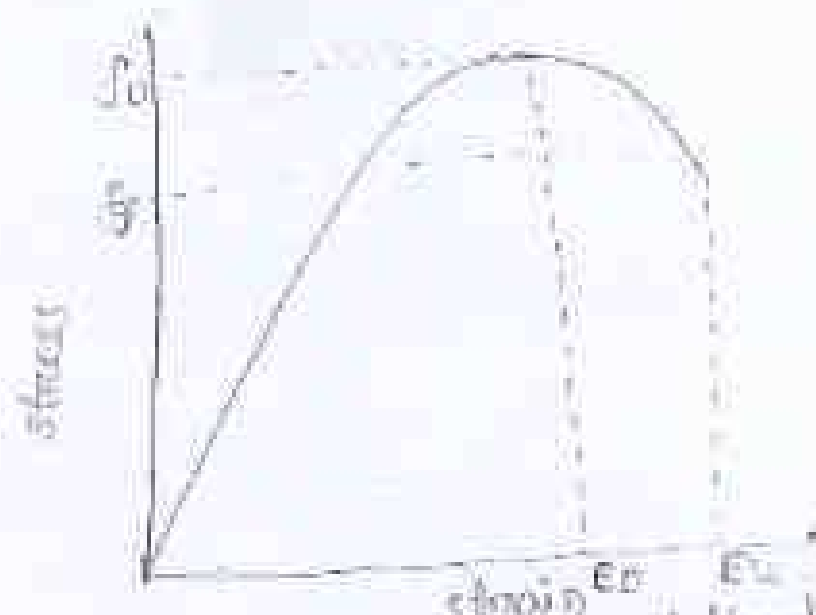


Fig 1

(Stress-strain relationship for concrete)

7 Concrete finally fails. The curve is usually obtained by testing a cylinder with a height-to-diameter ratio of at least 2. The test being conducted under uniform rate of strain. If a uniform rate of stress is adopted, it will not be possible to obtain the descending portion of stress and strain curve. Beyond the

maximum stress.

→ An equation representing the stress-strain curve completely should satisfy the following conditions.

(i) at  $f = 0$ ,  $\epsilon = 0$  and  $\frac{df}{d\epsilon} = E_c$

(ii) at  $f = f_0$ ,  $\epsilon = \epsilon_0$  and  $\frac{df}{d\epsilon} = 0$

(iii) at  $f = f_1$ ,  $\epsilon = \epsilon_u$


→ The equation satisfying all these conditions is used in the limit state design method. In another case, some simplifying assumptions are made.

→ One of the major assumptions is made in approximating the stress-strain curve to a straight line, i.e., treating the concrete as linearly elastic material.

→ This approximation is used in working stress method of design of structural concrete without much loss of accuracy up to about 50 percent of  $f_0$ .

→ Concrete is not strictly elastic in the sense that if it is unloaded after being stressed to 0.5  $f_0$  or less, a permanent set is noticed. However, the magnitude of the permanent set gradually decreases with more cycles of loading and unloading (within 0.5  $f_0$ ) and the stress-strain curve tends to become a straight line.

→ The creep deformation of concrete also varies linearly with the sustained stress up to a value of 0.5  $f_0$ . Hence, for all practical purposes, the concrete could be considered as a linear elastic material when stress does not exceed 0.5  $f_0$ .

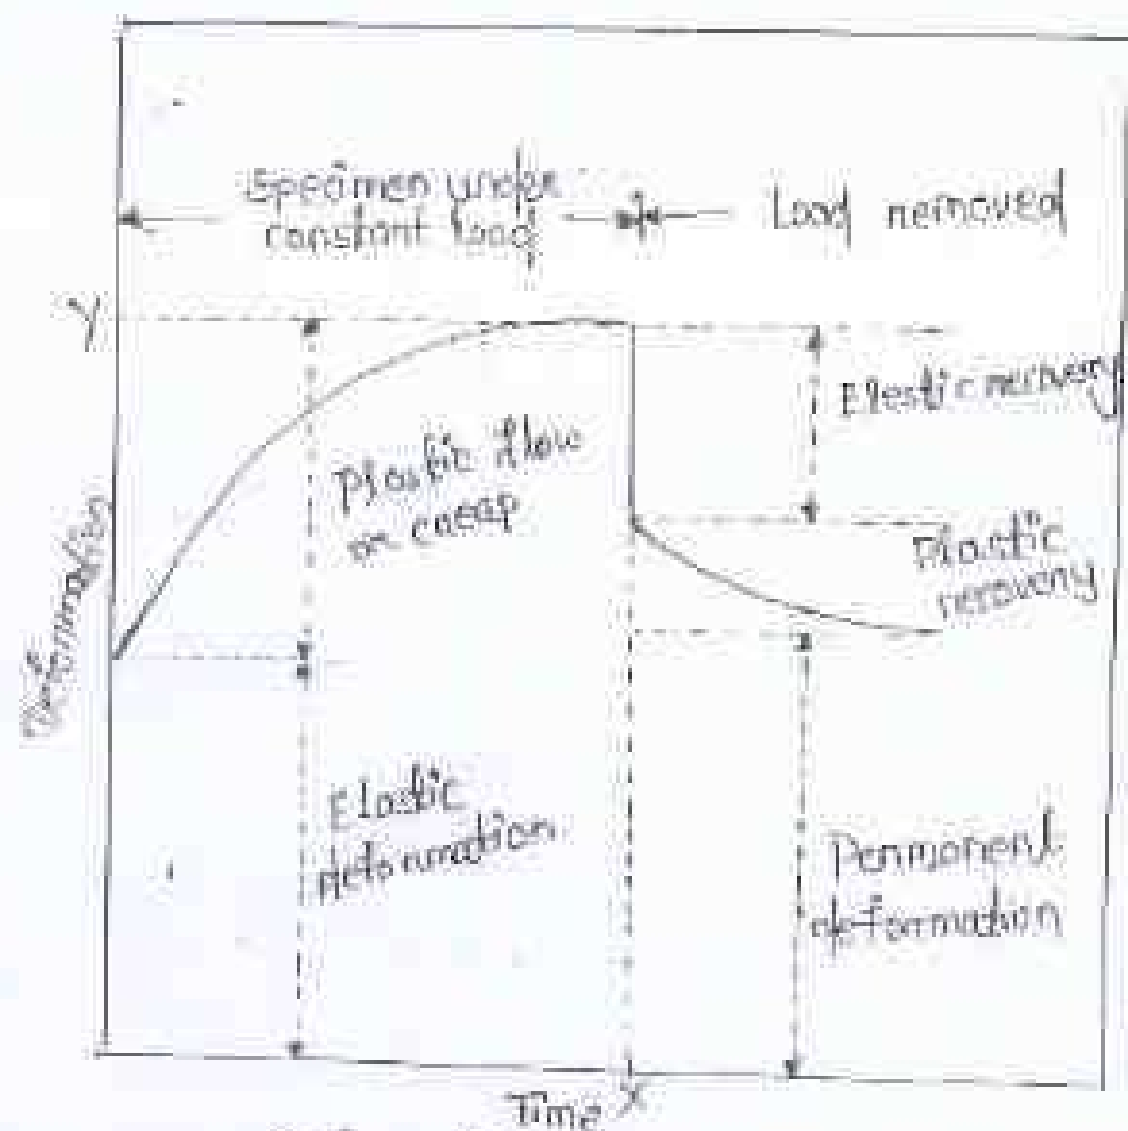


Deformation of hardened concrete under load

### Modulus of Elasticity

- The modulus of elasticity of concrete would be a property for the case when the material is treated as elastic.
- If we consider the stress-strain curve of the first cycle, the modulus could be defined as initial tangent modulus, secant modulus, tangent modulus or chord modulus.
- In the laboratory determination of the modulus of elasticity of concrete, a cylinder is loaded and unloaded (stress not exceeding one-third of  $f_c$ ) for three or four cycles, the stress-strain curve is plotted. The residual strain has become almost

negligible and the average slope of stress-strain curve is taken.

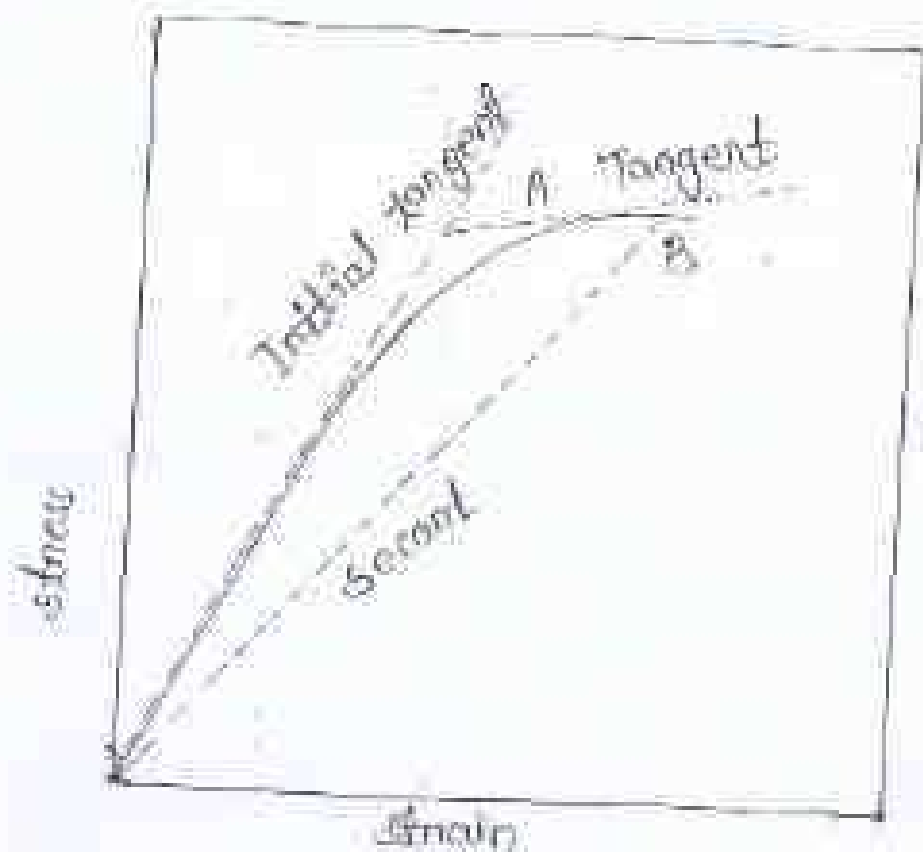

different moduli of elasticity

- The above modulus of elasticity is sometimes termed the static (secant) modulus of elasticity in comparison with dynamic modulus of elasticity obtained by vibration tests of concrete prisms or cylinders.
- The latter is approximately equal to the initial tangent modulus and hence greater than the static or secant modulus.
- Non-destructive test (NDT) procedure using electronic test system can be used to determine the dynamic modulus of elasticity of the concrete.
- In this method, pulses of compression waves are generated by an electro-acoustical transducer that is held in contact with one surface of the prismatic or cylindrical concrete specimen.
- After traversing through the concrete, the pulses

were received and converted into electrical energy by a second transducer located at a distance  $L$  from the transmitting transducer.

→ The pulse velocity  $V = L/T$  is related to the physical properties of a solid by the equation

$$V^2 = \frac{E_d}{\rho} \quad \text{or} \quad E_d = \frac{\rho V^2}{k}$$

where:

$L$ : distance between transducers, m

$T$ : transit time, seconds

$E_d$ : the dynamic modulus of elasticity, Pa (N/m<sup>2</sup>)

$\rho$ : Pulse velocity, m/s

$\rho$ : the mass density, kg/m<sup>3</sup>

$k = 1$  (for a cylindrical specimen)

In an alternative procedure, the concrete specimen is subjected to longitudinal vibration and the resonant frequency of the specimen is determined. The dynamic modulus of elasticity can be calculated from the relation:

$$E_d = k f_n^2 L^2$$

If  $L$  and  $f_n$  measured in millimeters and  $\rho$  in kg/m<sup>3</sup> then:

$$E_d = (430^2 L^2) \times 10^{-15} \text{ GPa}$$

→ The test method does not apply to the propagation of other types of vibrations within the concrete.

→ The approximate relationship between the static and dynamic moduli of elasticity is expressed by



## Dimensional stability - shrinkage and creep:

- Dimensional stability of a construction material refers to its dimensional change over a long period of time.
- If the change is so small that it will not cause any structural problems, the material is dimensionally stable. For concrete, drying shrinkage and creep are two phenomena, additional to the deformation due to loads, which compromise its dimensional stability.
  - Creep is the deformation suffered by concrete when it is subjected to a sustained load, and shrinkage, a contraction suffered by concrete even in the absence of load.
  - The relative magnitudes of shrinkage, creep and elastic strains are of the similar order.
  - The term volume change is often used to refer to the change in volume that occurs due to the shrinkage, creep, temperature and possibly chemical disintegration.
  - Shrinkage and creep are often discussed together because they are both governed by the deformation of hydrated cement paste within concrete.
  - The aggregate in concrete does not shrink or creep, and they serve to restrain the deformation.
  - Two types of shrinkage strains are recognised namely, plastic and drying shrinkage.

### Plastic shrinkage:

- The hydration of cement causes a reduction in the volume of the system of cement plus water to an extent of about one percent of the volume of dry cement.

For normal weight concrete  $E_c = 1.25 E_s - 19$   
For light weight concrete:  $E_c = 1.05 E_s - 4$

### Poisson's Ratio

- It is determined as the ratio of lateral to longitudinal strain in compression test and may vary from 0.15 to 0.21.
- The poisson's ratio can also be determined from the fundamental resonant frequency of longitudinal vibration of concrete specimen using ultrasonic pulse velocity method. The poisson's ratio  $\mu$  can be determined from

$$\text{Where } \left( \frac{V^2}{2nL} \right) = \frac{1-\mu}{(1-2\mu) E_s / H}$$

$V$  - Pulse velocity - m/s

$n$  - resonant frequency of longitudinal vibration in Hz

$L$  - distance between transducers in mm

The value of Poisson's ratio as determined by dynamic tests is slightly higher and ranges from 0.20 to 0.25.

### Plastic shrinkage

- The ~~de~~ hydration of cement cause - a reduction in the volume of the system of cement plus water to an extent of about one percent of the volume of dry cement. This contraction is plastic strain and is a gradual ~~of~~ due to loss of water by evaporation from the surface of concrete, particularly under hot climates and high winds. This can result in surface cracking.

7 This contraction is plastic strain and is aggravated due to loss of water by evaporation from the surface of concrete, particularly under hot climate and high winds. This can result in surface cracking.

### Drying shrinkage:-

7 The shrinkage that takes place after the concrete has set and hardened is called drying shrinkage and most of it takes place in the first few months (it also coincides with the period of active creep and thus the two are inextricably related).


7 With removal of water from concrete stored in unsaturated air voids causes drying shrinkage.

7 A part of this shrinkage is recovered on immersion of concrete in water.

7 It is termed moisture movement. In the absence of other reliable data, the shrinkage can be estimated from Schreder's formula.

$$E_s = 0.00025 (0.90 - h)$$

where  $E_s$  is shrinkage strain and  $h$  represents relative humidity expressed as a fraction. In an environment of average humidity of 50 percent  $h = 0.5$ ,  $E_s = 0.0005$  and it may be noticed that in fully saturated condition ( $h = 1.0$ )  $E_s = -0.00025$  which indicates swelling.

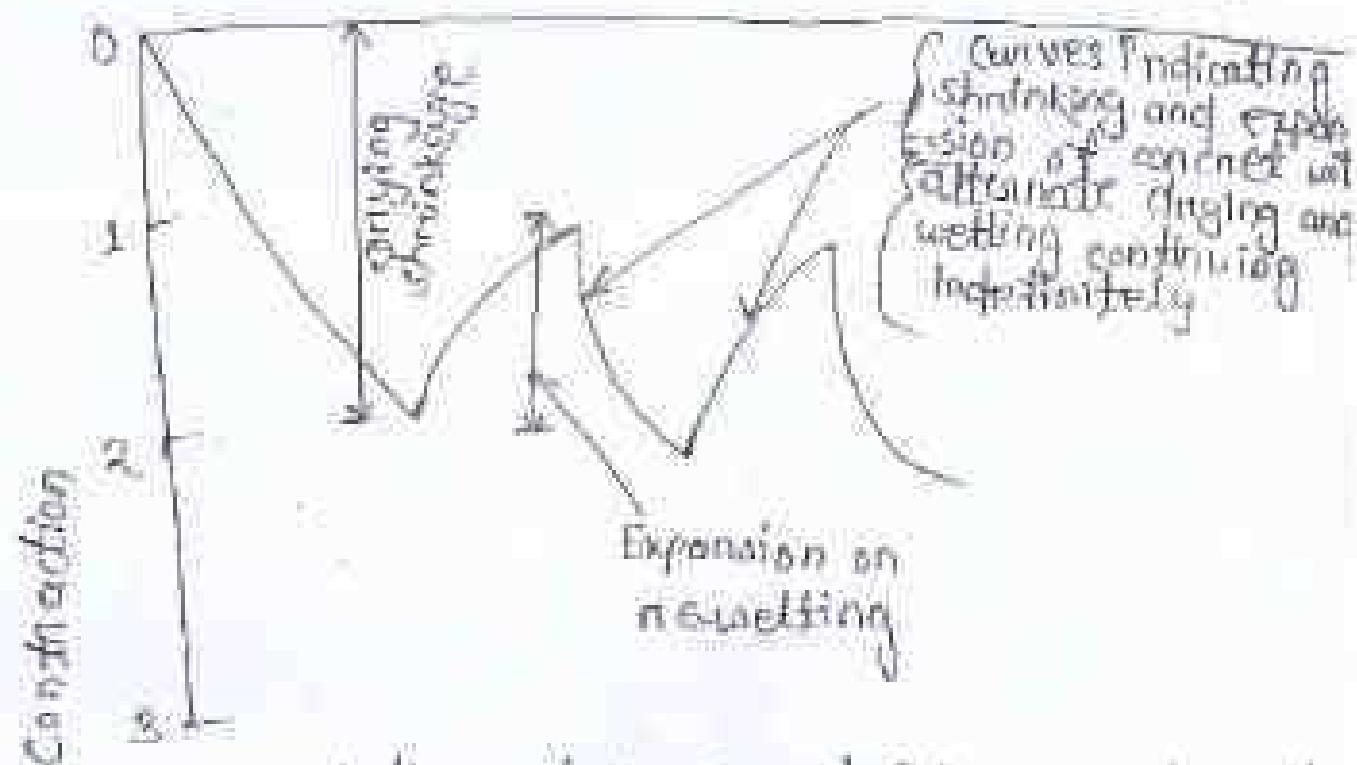

variation of drying shrinkage and moisture movement with alternate drying and wetting

The shrinkage is affected by-

1. Water-cement ratio:- The shrinkage increases with the increase in the water-cement ratio.

2. cement content:-

The shrinkage increases with cement content but is inter-related to water-cement ratio because of the necessity to maintain workability. It is not much affected by the cement content if the water content per unit volume is constant.

3. Ambient humidity:-

The shrinkage increases with the decrease in humidity and the immersion in water causes expansion.


4. Type of aggregate:- The aggregate which exhibit moisture movement themselves and have low elastic modulus cause large shrinkage.

## Creep of concrete :-

- The increase of strain in concrete with time under sustained stress is termed creep.
- The shrinkage and creep occur simultaneously and they are assumed to be additive for simplicity.
- When the sustained load is removed, the strain decreases immediately by an amount equal to the elastic strain at the given age.
- This instantaneous recovery is then followed by a gradual decrease in strain, called creep recovery which is a part of total creep strain suffered by the concrete.
- If a loaded concrete specimen is viewed as being subjected to a constant strain, the creep decreases the stress progressively with time. This is called relaxation.
- The rate of creep decreases with time and the creep strains attained at a period of five years are usually taken as terminal values. While as to 85 percent shrinkage strains occur in six months only about 75 percent of creep strains occur in 12 months. All the factors which influence shrinkage influence creep also in a similar way.
- The types of aggregate, cement, and admixtures, entrained air, mix proportions, mixing time and consolidation, age of concrete, level of sustained stress, ambient humidity, temperature, and the size of the specimen are among the important factors influencing creep.

## Permeability of concrete.

- When excess water in concrete evaporates, it leaves voids inside the concrete element creating capillaries which are directly related to the concrete porosity and permeability.
- The volume of moisture which may pass through the concrete depends on its permeability. Permeability is governed by porosity, which in turn is a direct consequence of the water-cement ratio of the concrete mix.

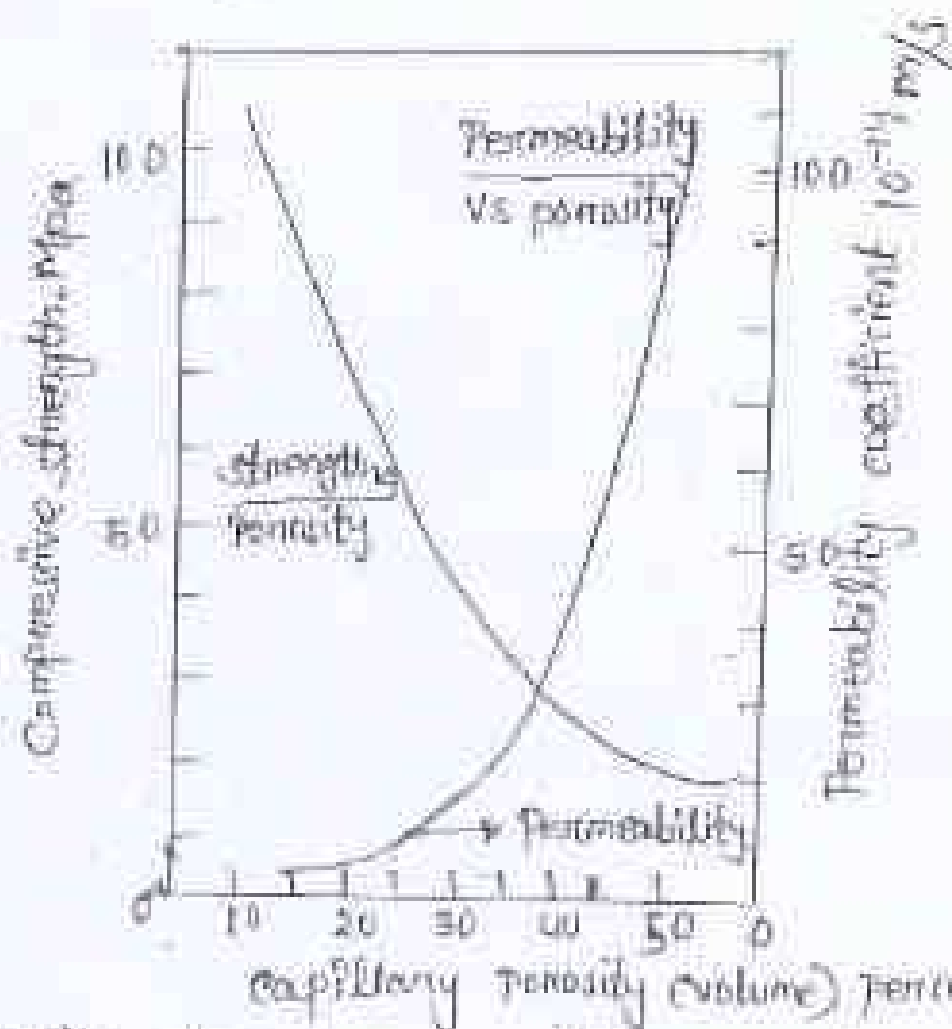

Compressive strength vs. capillary porosity and permeability coefficient vs. capillary porosity.

By proper selection of ingredients and mix proportions and following the good construction practices almost impervious concrete can be obtained.

→ The magnified image of a slice of concrete indicates a well-graded aggregate mix is locked into a matrix of hardened cement paste.

→ The well-packed aggregate has reduced the amount of space to be filled by water and cement paste.

→ This has helped to improve the pore structure of concrete and hence, its permeability.

The study of permeability of concrete is important for the following reasons.

1. The penetration by materials in solution may adversely affect the durability of concrete, e.g.,  $\text{Ca}(\text{OH})_2$  leaches out and the aggressive liquid attack the concrete.

2. In case of reinforced concrete, ingress of moisture and air will result in corrosion of steel and to cracking and spalling of concrete cover.

3. The moisture penetration depends on permeability and if the concrete can become saturated with water it is more vulnerable to frost action.

4. The permeability is also of interest in connection with water tightness of liquid retaining structures and the problem of hydrostatic pressure in the interior of the dams.

The flow of water through concrete is similar to flow through any porous body. The pores in concrete

route consist of gel-pores and capillary pores is connected as a result of incomplete compaction, the voids of larger size which give a honeycomb structure leading to concrete of low strength.

→ Such pores are not considered here. Since the capillary pores are larger in size than gel pores, and the cement paste is 20 to 30 times more permeable than the gel itself, the permeability of cement paste is controlled by the capillary porosity of the paste.

→ In rocks, the pores are fewer in number, but being of large size they lead to higher permeability.

→ The permeability of cement paste also varies with the age of concrete or with the degree of hydration. With age, the permeability decreases because gel gradually fills the original water filled space.

→ For the pastes hydrated to the same degree, the permeability is lower with lower water-cement ratio or higher cement content.

→ For the same water-cement ratio, the permeability of paste with coarser cement particles is higher than that with finer cement. In general, the higher the strength of cement paste, the lower will be the permeability.

→ A durable concrete should be relatively impervious. Permeability can be measured by a simple test, by measuring the quantity of water flowing through a given thickness of concrete in a given time. The drop in the hydraulic head using Darcy's equation is

$$\frac{dq}{dt} \times \frac{1}{A} = K \times \frac{\Delta h}{L}$$

where  $(dq/dt)$  is the rate of flow (ml/s),  $A$  the cross-sectional area ( $\text{cm}^2$ ),  $\Delta h$  the drop in hydraulic head (mm),  $L$  the thickness of the sample in millimetres and  $K$  the coefficient of permeability (mm/s).



## Durability of concrete:-

- A durable concrete is one that performs satisfactorily under anticipated exposure (working) conditions during its service life span.
- The materials and mix proportions used shall be such as to maintain its integrity and, if applicable, to protect embedded metal from corrosion.
- Even though concrete is a durable material requiring a little or no maintenance in normal environments but when subjected to highly aggressive or harsh environments it has been found to deteriorate resulting in premature failure of structures or reach a state requiring costly repairs.
- One of the main characteristics influencing the durability of concrete is its permeability to the ingress of water, oxygen, carbon dioxide, chlorides, sulfate and other potentially deleterious substances.
- As discussed in the previous section the permeability of concrete depends upon micro and macro-cracks, and voids developed during production or service.
- Most of the durability problems in the concrete can be attributed to the volume change in the concrete.
- Volume change in concrete is caused by many factors. The entire hydration process is nothing but an internal volume change, the effect of heat of hydration, the pozzolanic action, the sulfate attack, the carbonation, the moisture movement, all types of shrinkages, the effect of chlorides, corrosion of steel reinforcement and other aspects come under the preview of volume

change in concrete.

- The internal or external restraints to volume change in concrete results in the cracks.
- It is the crack that promotes permeability and thus it becomes a part of cyclic action, till such time that concrete deteriorates, degrades, disrupts and eventually fails.

### Sulfate Attack:-

- Sulfate are generally found in ground water and sub-soil. Sea water also contains large quantity of sulfates.
- Sulfates can be naturally occurring or could be as a consequence of industrial waste disposal. Calcium, sodium, magnesium and ammonium sulfates (in order of hazard) are harmful to concrete as they can lead to increase in the concrete volume or consequent cracking.
- Calcium sulfate reacts with calcium aluminate present in cement hydrates forming an expansive ettringite.
- Sodium sulfate reacts with calcium hydroxide and forms expansive gypsum in presence of aluminates and may in turn lead to the formation of ettringite.
- Magnesium sulfate reacts with cement compounds decomposing the cement itself and subsequently producing gypsum and ettringite.

### Selection of cement:

For minimizing the danger of sulfate attack, low  $C_3A$  content are recommended. Sulfate-resisting cement with very low  $C_3A$  content is most

suitable. However, if chlorides are also present in the ground water and sub-soil in addition to sulfates, then it is not recommended for their use in view of the vulnerability of low  $C_3A$  cement pastes to chloride ion diffusion.

→ Blended cements are most preferred when both sulfates and chlorides are present in an environment at the same time.

→ Blended cement have low  $C_3A$  content and also enable production of pastes retaining small amount of calcium hydroxide. The pozzolana cements have also shown high sulfate resistance which is probably due to the composition and the structure of the pores in hydrated pastes.

→ The resistance of cement to sulfate attack can be tested by storing the specimens in a solution of sodium or magnesium sulfate or in a mixture of these two.

Type of cement	Chemical resistance of sulfates		
	Moderate	High	Very high
	Limits of compounds percent		
Ordinary Portland cement	$C_3A < 8$	$C_3A < 5$ ( $C_3A + C_4AF$ ) $< 25$ or ( $C_4AF + C_3F$ ) $< 25$	$C_3A = 0$ $C_4AF < 20$ or ( $C_4AF + C_3F$ ) $< 2$
Pozzolana cement	No special prescription	$C_3A < 5$	$C_3A < 2.5$
Slag cement	slag $> 35$	slag $> 70$	slag $> 70$ or $C_3A < 2$

## Chloride Attacks on concrete structures!

1. Chloride ion ( $Cl^-$ ) is form when the element chlorine gains an electron or when a compound such as hydrogen chloride is dissolved in water.

2. High concentrations of chloride ions in concrete can be very problematic. Chloride ions break down the passive layer of non-ferrous steel without the need to drop the pH level.

3. Corrosion takes place as the chloride ions react with the steel and the surrounding passive material to produce a chemical process which forms hydrochloric acid. The hydrochloric acid eats away at the steel reinforcement and thus leads to concrete cracking, spalling and eventually failure.

4. There are two main sources of chloride ions, one from the concrete mix components, and the other from the surrounding environment. The first chloride ions come from unwashed aggregate and sand, rock dust and even from the use of seawater in the concrete processing.

5. The second comes mainly from being exposed to marine environment such as sea wall spray, de-icing salts, wetting, when concrete is in contact with soils rich with chlorides deposits, or it can come from de-icing salts and use of chemicals. It is by the process of diffusion that chlorides penetrate the concrete.

## Damages associated with chloride attack

- The main problem involving the corrosion of the steel is the spalling of the concrete cover. The oxide results from the reaction in very porous and takes up to 10 times the volume of the steel which causes the break up of the concrete.
- There are two types of corner cracks that can be observed. Horizontal cracks occur in the nodules. Indentations due to the oxide formation and leads to loss of the concrete cover. Vertical cracks occur when the tensile strength of the steel is exceeded. Also, if they are large enough, the cracks may accelerate the corrosion process by allowing access of corrosion agents.
- If rust stains are observed around cracks and spalls these are indicative of chloride attack. When inspecting an exposed corroded reinforcement, it will typically show black colored rusting and pitting of the steel where the aggressive hydrochloric acid has eaten away the reinforcement.

## Prevention of chloride attack

For new structures, there are several methods of prevent to reduce chloride attack.

- + Increase concrete cover (min 50mm)
- + Use epoxy coated rebars.
- + Use stainless steel rebars.
- + Cathodic protection.
- + Use low water/cement ratio.
- + Apply of anti-carbonation concrete coating.

ion existing structure suffering from chloride attack the following repair methods can be applied.

- \* Apply of anti-carbonation concrete coating to slow down the corrosion process.
- \* Use of corrosion inhibitors.
- \* Install a cathodic protection system.
- \* In the case of extensive spalling of section i.e. a comprehensive concrete repair or a section replacement will be required.

### Fire resistance

→ In general, concrete has good properties with respect to fire resistance, i.e. the period of time under fire during which concrete continues to perform satisfactorily is relatively high and no toxic fumes are emitted.

→ The length of time over which the structural concrete preserves structural action is known as fire rating. Under sustained exposure to temperature in excess of  $25^{\circ}\text{C}$  along with the condition that a considerable loss of moisture from concrete is allowed, leads to decrease in strength and in modulus of elasticity. The loss of strength and in modulus of elasticity is greater in concrete of higher temperature.

→ Excessive moisture at the time of fire is the primary cause of spalling. In general, moisture content of concrete is the most important factor determining the structural behaviour at higher temperatures.

→ Concrete curves appear to suffer a relatively lower loss of strength than rich ones. Flexural strength

7 The loss of strength is considerably lower when the aggregate does not contain silica, e.g., concrete made with limestone, crushed brick and blast-furnace slag aggregate etc.

7 Low conductivity of concrete improves its fire resistance and hence a lightweight concrete is more fire resistant than ordinary concrete.

7 The calcined material aggregate having a low density leads to a good fire resistance of concrete. Due to endothermic nature of ~~the~~ carbonate aggregate during calcination at high temperature heat is absorbed and further temperature rise is delayed. For example, dolomite gravel leads to a good fire resistance of concrete.

## Concrete Mix design

1st New chapter

Concrete of different qualities can be obtained by using its constituents, namely cement, water, fine and coarse aggregate, and mineral additives, in different proportions. Also, the ingredients of widely varying characteristics can be used to produce concrete of acceptable quality.

The common method of expressing the proportions of the materials in a concrete mix is in the form of parts, or ratios of cement, the fine and coarse aggregate with cement being taken as unity. For example, a 1:2:4 mix consists of one part of cement, two parts of fine aggregate and four parts of coarse aggregate.

The amount of water, entrained air and admixtures, if any, are expressed separately. The proportions should indicate whether it is by volume or by mass. The water-cement ratio is generally expressed by mass.

The amount of entrapped air in concrete is expressed as a percentage of the volume of concrete. The amounts of admixtures are expressed as a percentage of the volume of concrete. The amounts of admixtures are expressed relative to the weight of cement.

Other forms of expressing the proportions will be ratios of cement to the sum of fine and coarse aggregate, or aggregate-cement ratio.



and by weight factor or number of bags of cement per cubic meter of concrete.

→ The wide use of concrete as construction material has led to the use of mixes of fixed proportions which ensure adequate strength. These mixes are known as nominal mixes.

→ These offer simplicity and under normal circumstances, have a margin of strength above that specified. However, they do not account for the varying characteristics of the constituents and may result in under or over rich mixes. Generally, a nominal mix is expressed in terms of aggregate-cement ratio.

→ Nominal mix concrete may be used for concrete of grade M20 or lower. The proportions of materials in these mixes called standard mixes are by definition conservative, but are useful as off the shelf sets of proportions that allow the desired concrete to be produced with minimum preparatory work.

→ For example, for M15 grade concrete the proportion is 1:2:4 for the ordinary concrete from which quite unimpressive performance is expected, the nominal or standard mixes may be used.


→ The concrete making materials being essentially variable result in the production of mixes of variable quality. In such a situation, for high performance concrete, the most rational approach of mix proportions is to select proportions with

specific order, in mind which gives more or less unique characteristics. This will ensure the concrete with the appropriate properties to be produced, most economically. Other factors like workability, durability, cost etc. also influence the choice of the mix proportions.

→ The mix proportion so arrived at is called design mix. However, the method does not guarantee the correct mix for the designed strength, thereby necessitating the use of trial mixes.

→ In the process of mix proportioning, a number of subjective decisions are required on which hinge the important ramifications for the correct.

→ The designed mix serves only as a guide. For many works it is desirable to go through the process of mix design, for example, where a large volume of concrete is required, a minimization of the cement content may reduce the cost appreciably, or where for technical reasons the type of concrete required necessitates careful selection and proportioning of ingredients.

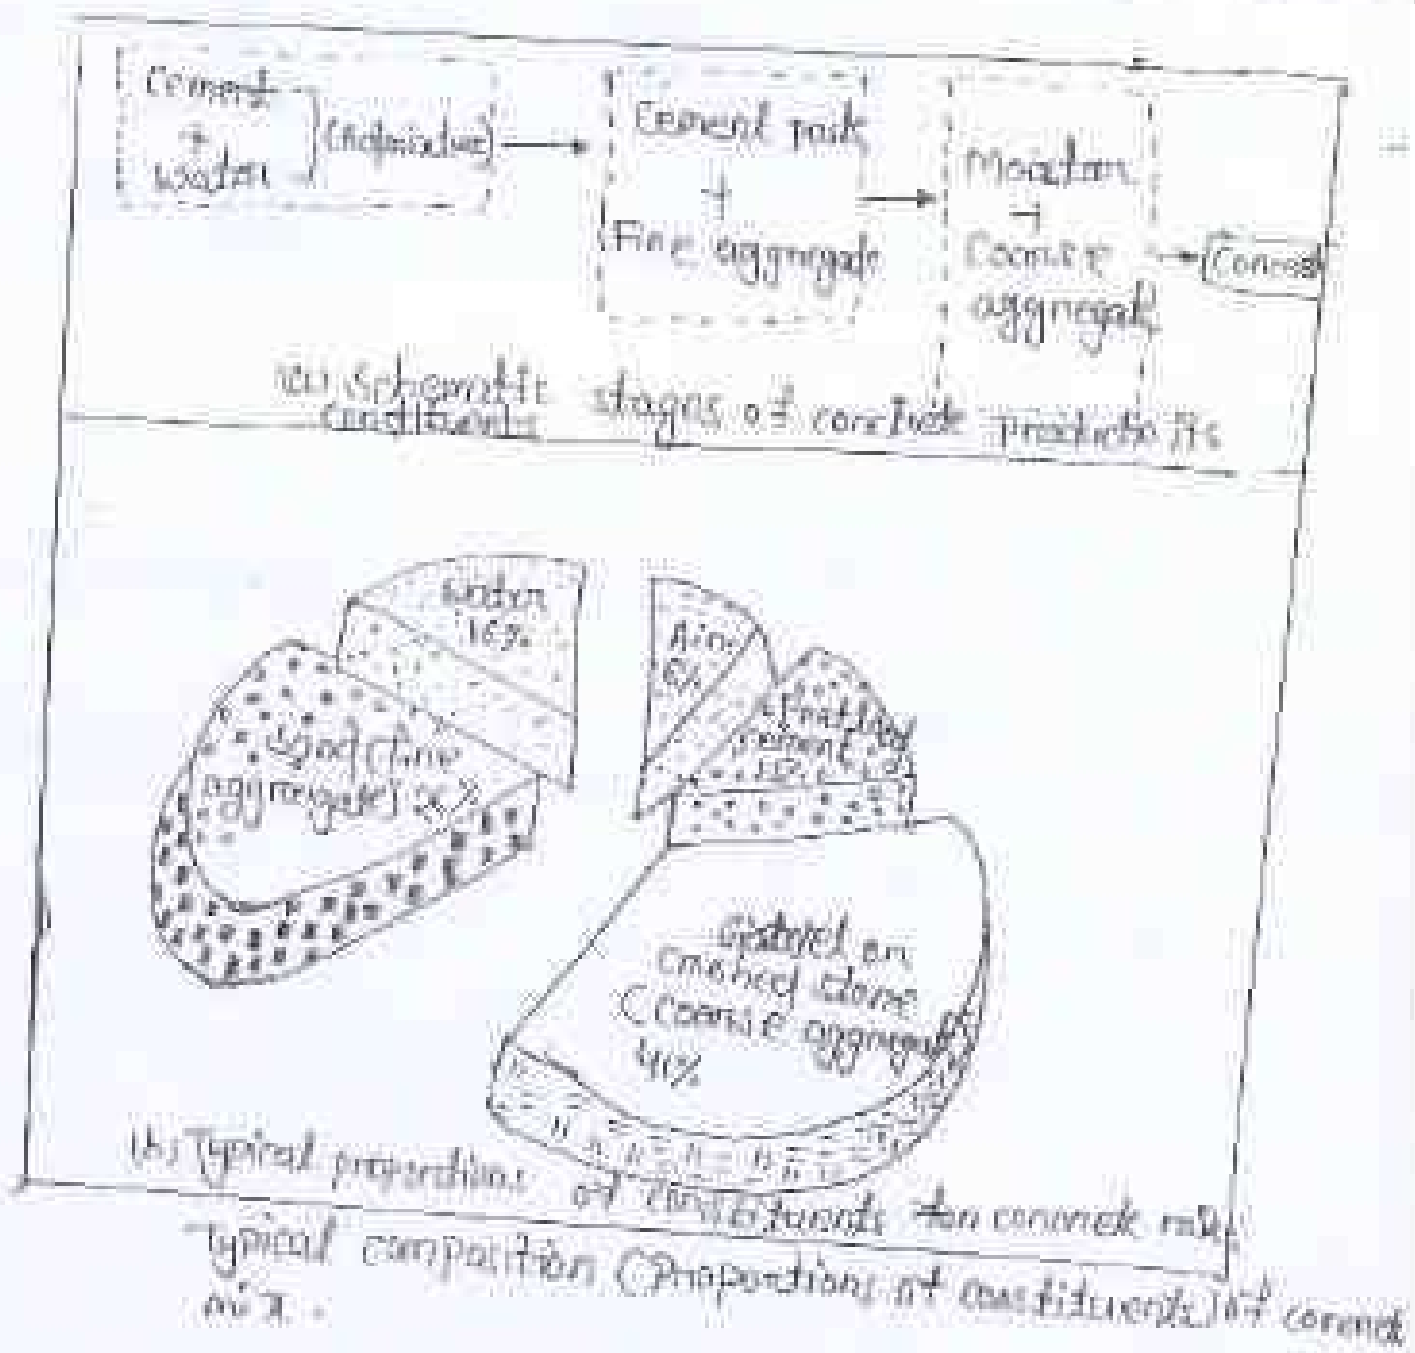

### Proportions of nominal mix concrete

Grade of concrete	Total quantity of dry aggregate per bag of cement of 50 kg (112 lb)	Maximum water content per bag of cement of 50 kg (112 lb)	Proportions of fine aggregate to coarse aggregate by mass
M10	480	34	Generally 1:2 with upper
M15	350	32	Limit as 1:1.5 and lower
M20	250	30	Limit as 1:2:3

Basic considerations for concrete mix design:-

→ The concrete mix design is a process of selecting suitable ingredients for concrete and determining their proportions which would produce, as economically as possible, a concrete that satisfies the job requirements, i.e. concrete having a certain minimum compressive strength, workability and durability.

→ The proportioning of the ingredients of concrete is an important phase of concrete technology as it ensures quality and economy.

→ The proportioning of concrete mixes is accomplished by the use of certain empirical relations which afford a reasonably accurate guide to select the best combination of the ingredients so as to achieve the desired properties. The design of plastic concrete of medium strength can be based on the following assumptions:-

1. The compressive strength of concrete is governed by its water-cement ratio.

2. For the given aggregate characteristics, the workability of concrete is governed by its water content.

• For high-strength or high-performance concrete mixes of low workability, considerable interaction exists between the above two criteria and the validity of such assumptions may become limited.

→ Moreover, there are various factors which affect the properties of concrete, e.g. the quality and quantity of cement, water and aggregate, techniques used for batching, mixing, placing, compaction and curing etc.

Therefore, the specific relationships used for batching, placing, compaction and curing etc. in the proportioning of a concrete mix should be considered only as a basis for making an initial guess at the optimum combination of the ingredients and the final mix proportion is obtained only on the basis of such trial mixes.

Factors influencing the choice of mix proportions:-

According to IS: 456-2000 and IS: 1843-1980, the design of concrete mix should be based on the following factors:

1. Grade designation
2. Type and grade of cement
3. Maximum nominal size of aggregates.
4. Grading of combined aggregates.
5. Water-cement ratio.
6. Workability.
7. Durability.
8. Quality control.

Grade designation:-

The grade designation gives characteristic compressive strength requirements of the concrete.

As per IS: 456-2000, the characteristic compressive strength is defined as that value below which not more than five percent of the test results are expected to fall.

It is the major factor influencing the mix design, depending upon the degree of control available at the site, the concrete mix has to be designed for a target mean compressive strength which is somewhat higher than the characteristic strength.

## Type and Grade of cement :-

The type of cement is important mainly through its influence on the rate of development of compressive strength of concrete.

The choice of type of cement depends upon the requirements of performance at hand.

For requirements of performance at hand, where very high compressive strength is required, e.g., in prestressed concrete railway sleepers,

Portland cement of grades 43 and 53 conforming to IS: 802-1989 and IS: 8029-1987, respectively, will be found suitable.

In situations where an early strength development is required, rapid-hardening Portland cement conforming to IS: 8041-1990 is preferable and for mass concrete construction, low-heat Portland cement conforming to IS: 12600-1989 is preferred.

The blended cements such as Portland-pozzolana cement and Portland slag cement are permitted for use in reinforced concrete construction.

While Portland slag cement is also permitted for prestressed concrete construction, the rate of development of early strength may be somewhat slower with blended cements.

A cement of consistent quality which exhibits minimum variation i.e., minimum standard deviation in the quality expressed in terms of its compressive strength makes it easier to determine the proportion of cement required to obtain a particular grade concrete mix only by changing the ratio of fine to coarse aggregates.

The currently available good brands of cement have been reported to maintain standard deviation as low as 2.5, 1.8 and 1.0 MPa, respectively for 28, 43

and 52 grades of cement. Since in the quality of cement IS: 10262-1982 has not classified the cement grade-wise into six continuous ranges designated A to F, depending upon the 28 days compressive strength of the cement, A (32.5-37.5 MPa), B (37.5-42.5 MPa), C (42.5-47.5 MPa), D (47.5-52.5 MPa), E (52.5-57.5 MPa) and F (57.5-62.5 MPa).

∴ This classification covers the entire spectrum of strength. The strength of cement to be used in min design computations is not the mean strength of certain number of test results (say 9) together but the characteristic strength  $f_{ck}$ .

$$f_{ck} = \bar{f}_m - k s$$

where  $k$  is probability factor, a statistical parameter for not more than five percent test results to fall below the characteristic strength  $f_{ck}$  and  $s$  is standard deviation. For example, if the mean of  $n$  compressive strength test results of a cement is 55, the cement would be apparently a grade 52 cement categorized as E (52.5-57.5 MPa).

∴ However, if the standard deviation of this particular cement is 4.0 MPa, the characteristic strength could be:

$$f_{ck} = 55.0 - (1.65 \times 4.0) = 48.4 \text{ MPa}$$

∴ Thus the cement actually comes under grade 48.4 or a D category (47.5-52.5 MPa).

It is of prime importance to control the variation in quality of cement to the lowest minimum so that cement can be classified for highest grade.

∴ If the 28-day compressive strength of cement is

considered as an additional parameter influencing the relationship between water-cement ratio and 28-day compressive strength of concrete, the curves of  $f_{cu}$  can be used to make more precise estimate of water-cement ratio for the given grade of cement.

Maximum Nominal size of coarse Aggregate:-

- 1. The maximum nominal size of the coarse aggregate is determined by sieve analysis and is designated by the sieve size higher than the largest size on which 15 percent or more of the aggregate is retained.
- 2. The maximum nominal size of the aggregate to be used in concrete is governed by the size of the section and the spacing of the reinforcement.
- 3. According to IS: 456-2000 and IS: 1343-1980, the maximum nominal size of the aggregate should not be more than one-fourth of the minimum thickness of the member, and it should be restricted if smaller than the minimum clear distance between the main bars, or smaller than the minimum clear cover to the reinforcement or smaller than the spacing between the prestressing cables.
- 4. Within these limits, the nominal maximum size of the aggregate may be as large as possible, because larger ~~and~~ the maximum size of aggregate, smaller is the cement requirement for a particular water-cement ratio.
- 5. The sustainability also increases with an increase in the maximum size of the aggregate.



- However, the smaller  $\frac{1}{2}$ "-aggregates provide a large surface area for bonding with the matrix material which increases the compressive strength and reduces the stress concentration in the mortar-aggregate interface.
- For the concrete with higher water-cement ratio, the larger maximum size of aggregate may be beneficial whereas for high strength concrete, 10-20 mm size of aggregate is preferable.

Grading of combined aggregate :-

- The relative proportions of the fine and coarse aggregates in a concrete mix is one of the important factors affecting the workability and strength of concrete.
- For dense concrete, it is essential that the coarse and fine aggregates be well graded.
- Continuous range of size of aggregate used in concrete.
- In the concrete produced by using a well-graded aggregate, smaller size particles and fill the voids between larger size particles, reducing the amount of space to be filled by water cement paste as illustrated where in magnified image of a piece of concrete shows a well graded aggregate mix locked into a matrix of hardened cement paste.

- This results in improved strength, minimum shrinkage and lower cost of the concrete.
- Generally, the locally available aggregates do not conform to the standard gradings.
- In such cases, the aggregates need to be combined in suitable proportions so that the resultant (combined) grading approximates to a continuous grading close to the desired (or standard) grading.
- The process of combining aggregates is aimed at obtaining a grading close to the coarsest grading of standard grading curves the most economical mix having highest permissible aggregate cement ratio.
- IS : 882-1963 has recommended limits to the coarsest and finest gradings.
- The aggregates can be combined by analytical calculations.
- The method is easy to understand and calculations are trivial.
- Consider two aggregates (designated as aggregate-I and aggregate-II) are to be combined.
- Let  $x$ ,  $y$  and  $z$  represent the percentages of the combined (resultant) aggregate; aggregate-I and aggregate-II respectively, passing the sieve corresponding to the point on standard grading curve taken as criterion that is the point to which the combined aggregate

is required to approximate:

→ If  $x$  and  $y$  are the proportions of two aggregates in the combined state, then the condition that a percent of combined aggregate pass the criterion sieve results.

$$Px + \gamma y = a(x + y)$$

$$\frac{x}{y} = \frac{a - \gamma}{p - a} = \frac{1}{K}$$

$$x/y = 1/K$$
$$K = (p - a) / (a - \gamma)$$

or, where,

→ Hence the two aggregates have to be combined in the proportions of  $1/K$ .

→ The grading of the resulting combined aggregate is determined by first multiplying the grading of aggregates and aggregate by 1 and  $K$ , respectively, then dividing the sum of corresponding products of the percentages passing the sieve size by  $(1 + K)$ .

→ The values are rounded off to the nearest percentage.

Water-cement ratio:-

→ The compressive strength of concrete at a given age and under normal temperature depends primarily on the water-cement ratio. Lower the water-cement ratio greater is the compressive

strength and vice versa.

→ A number of relationships between compressive strength and water-cement ratio are available which are supposed to be valid for a wide range of conditions.

→ In so far as the selection of the water-cement ratio for the design of compressive strength at 28 days concerned is applicable for both ordinary portland and portland pozzolana cements with considerable validity.

→ The cement strength on grade specific relation between free water-cement ratio and 28-day compressive strength for cement of grades 23, 43 and 53.

→ However, the 28-day compressive strength of concrete is related to the 7-day compressive strength of cement mortar.

→ These relationships can also be used for the estimation of water-cement ratio.

→ For air-entrained concretes the compressive strengths are approximately 80 percent of that of air-entrained concretes.

The cement normally available have 7 day's compressive strength between 17.5 MPa to 40 MPa. Thus depending upon the cement strength, an appropriate curve should first be chosen. The steps to be followed in selecting the water-cement ratio are given below:

1. If the strength of cement to be used is determined in India, only those type of cement are officially recognized, which give minimum seven-day strength of 22 MPa.
2. When cement strength data are available, the corresponding curve is chosen for the determination of water-cement ratio. In the absence of such data, the curve corresponding to cement strength of 22 MPa the minimum permissible as per the Indian standards may be used.

### Workability:-

The workability of concrete for satisfactory placing and compaction is controlled by the size and shape of the section to be concreted, the quality and spacing of reinforcement, and the method to be employed for transportation, placing and compaction of concrete.

The situation should be properly assessed to arrive at the desired workability. The aim should be to have the minimum possible workability consistent with satisfactory placing and compaction of concrete. It should be kept in mind that insufficient workability resulting in improper compaction may severely affect the strength and durability of concrete.

and surface finish of concrete and may thus prove to be uneconomical. In the long run, there is no rigid correlation between workability of concrete as measured by different test methods. It is desirable that for a given concrete, the test method be identified beforehand and workability be measured accordingly.

- The workability measured by different test methods for comparable concrete ...

Durability :-

- The durability of concrete can be defined and interpreted to mean its resistance to deterioration influences which may arise inside the concrete itself, or to the aggressive environments.
- The requirements of durability are achieved by restricting the minimum cement content and the maximum water-cement ratio to the values specified by the Ministry of Road Transport and Highways (MORTH) specifications for Road and Bridges and by IS 456-2000 for other structures.
- The permeability of cement paste increases exponentially with increase in water-cement ratio above 0.45 or so.
- Thus from considerations of permeability, the water-cement ratio is usually restricted to 0.45 to 0.55, except in mild environments.

→ For a given water-cement ratio, the cement content in the concrete mix should correspond to the required workability, keeping in view the placing conditions and the concentration of reinforcement.

→ In addition, the cement content is chosen to ensure sufficient alkalinity to provide a passive environment against corrosion of steel e.g. in concrete for a marine environment or sea water minimum cement content of  $250 \text{ kg/m}^3$  or more is required.

→ Moreover, the cement content and water-cement ratio are so chosen as to provide a sufficient volume of cement paste to overfill the voids in the compacted aggregates.

→ The blended cements like portland pozzol and cement and portland slag cement impart greater durability to the concrete in sulfate environments and sea water.

→ Resistance to alternate freezing and thawing is not so important for Indian conditions but whenever situations demand, air entrained concrete could be employed using an air-entraining admixture. As

→ Air entrainment lowers the compressive strength but increases workability which may permit certain reduction in the water content to make up the loss in compressive strength.

Minimum cement content, minimum water-cement ratio and minimum grade of concrete for different exposure conditions (MORTAR: RCC specifications of Road and Bridge work - 2000)

For bridge with prestressed concrete on those with individual span lengths more than 50m or those that are built with innovative design/construction

Structural member	Min. cement content for all exposure conditions, kg/m <sup>3</sup>	Max. water cement ratio Exposure conditions		Min. grade of concrete Exposure conditions	
		Normal	Severe	Moderate	Severe
(i) RCC members	360	0.45	0.45	M25	M30
(ii) RCC members	400	0.45	0.40	M35	M40
(iii) PSC members	400	0.40	0.40	M35	M40

(b) For bridge other than those mentioned in part (a) and for culverts and other incidental construction

Structural member	Min. cement content for all exposure conditions, kg/m <sup>3</sup>		Max. water cement ratio Exposure conditions		Min. grade of concrete Exposure conditions	
	Normal	Severe	Normal	Severe	Moderate	Severe
(i) RCC members	250	310	0.50	0.45	M15	M20
(ii) PSC members	310	400	0.45	0.40	M20	M25



## Quality control:-

- The strength of concrete varies from batch over a period of time.
- The sources of variability in the strength of concrete may be considered due to variation in the quality of the constituent material, variations in mix proportion due to batch process, variations in the quality of batch and mixing equipment available, the quality of supervision and workmanship.
- These variations are inevitable, the quality of ~~supervision~~ and ~~workmanship~~ involved during production are to varying degree.
- Controlling these variations is important in lowering the difference between the mean strength and characteristic mean strength of the mix and hence reducing the cement content.
- The factor controlling this difference is quality control. The degree of control is ultimately evaluated by the variation in test results usually expressed in terms of the coefficient of variation.
- It can be summarized that the aim of mix design is to obtain a most practical and economical combination of materials that will produce a concrete mix of necessary plasticity (workability) and, at the same time,

produce hard and concrete of required strength and durability.

→ Most of the mix design procedures are primarily based on the water-cement ratio law and absolute volume system of calculating the amount of materials.

→ As explained earlier, according to Abram's law, the strength of fully compacted hardened concrete is approximately inversely proportional to the water content per cubic meter of concrete, i.e. water-cement ratio.

→ The calculation of the quantities of the aggregates to be used with a given cement paste is based on the absolute volume method. The absolute volume of loose materials is the actual volume of solid matter in all the particles ignoring the space occupied by the voids between the particles.

$$\text{Absolute volume} = \frac{\text{Mass of loose dry material}}{\text{Specific gravity} \times \text{Volume of unit}} \times \text{Mass of unit}$$

General process  
Methods of concrete mix design for medium strength concretes  
→ Most of the available mix design methods are based on empirical relationships, charts and graphs developed from extensive experimental investigations. Basically they follow the same principles enunciated in the preceding section and only minor variations exist in different mix design methods in the process of selecting the mix proportions.

→ The requirements of the concrete mix are usually dictated by the general experience with regard to the structural design conditions.

durability and conditions of placing. Some of the commonly used mix design methods for mass concrete are the following:

1. Trial and adjustment method of mix design.
2. British or mix design method.
3. ACI mix design method.
4. Concrete mix proportioning - IS Guidelines.
5. Rapid method for mix design.

The general step-by-step procedure for proportioning of concrete mixes is summarized below.

1. The maximum nominal size of the aggregate, which is economically available, is determined as per the specified requirements. The gradings of different size aggregates is determined. The proportions of different size aggregates to obtain a desired combined grading are determined.
2. The mean target strength is estimated from the specified characteristic strength and the level of quality control.
3. A suitable water-cement ratio to obtain a concrete mix of desired strength is selected from the generalized curves. The water-cement ratio so chosen is compared with that required for durability. The lower value is adopted.

4. The degree of workability in terms of slump, compacting factor or Vee-Bee time is selected as per job requirements. The water content for the required workability is computed.

5. The cement content is calculated above. Its quantity is checked for the requirements of durability.

6. The percentage of fine aggregate in the total aggregate is determined from the characteristics of coarse and fine aggregates. Alternatively, the aggregate cement ratio may be determined.

7. The concrete mix proportions for the final trial mix are computed and concrete cubes are cast in the laboratory as per standard procedure. After the required period of curing, the cubes are tested for the compressive strength of the mix.

8. The final batches, obtained by making suitable adjustment in water-cement ratio or aggregate-cement ratio or in proportions of cement, sand and aggregate, are tested till the final mix composition is arrived at.

9. The final proportions are expressed either in mass or volume basis.

→ Most of the available mix design methods are essentially based on the above procedure and due consideration should be given for the moisture content of aggregate and the entrained air.

## trial and adjustment method of mix design

- The trial and adjustment method is based on empirical approach and aims at producing a concrete which has minimum voids after having a max. density. If the fine aggregate is mixed in sufficient quantity to fill the voids for the coarse aggregate, and cement paste is used in insufficient quantity to fill the voids of aggregate which gives maximum mass of voids in mixed aggregate.
- The proportion of fine to coarse aggregate which gives maximum mass of combined aggregate can be obtained by trials.
- The process consists of filling a container of known volume with the two materials in thin layers, the fine being placed over the coarse aggregate and lightly rammed with each layer.
- If the container is shaken too much the coarse aggregate will try to come on the top and the fine aggregate will deposit at the bottom without filling the voids of the coarse aggregate.
- Since the density of the particles of fine and coarse aggregate is nearly the same, the mixture giving maximum weight will have maximum solid matter and hence least voids.
- Such a combination will give the least amount of cement per volume of concrete and hence

be most economical for given water-cement ratio and slump.

- In an alternate trial mix method, sand is combined with the coarse aggregate in several proportions such as 20:80, 30:70, 40:60, 50:50 and 60:40 on the basis of such mixture, the quantity of cement per unit volume of concrete is determined to give the required workability (expressed in terms of slump).

- The percentage of sand corresponding to the ratio requiring minimum cement is termed optimum value. It will be needed to have the same consistency.

- On the other hand, a smaller quantity of sand will make the mix harsh unless more cement is used for proper consistency.

- The optimum percentage of sand is lower for a low water-cement ratio. The water-cement ratio for mix proportioning is as follows.

1. The design mean compressive strength is determined from the characteristic strength.
2. The water-cement ratio is chosen for the target mean strength computed in step 1. The water-cement ratio so chosen is checked against limiting water-cement ratio for the requirements of durability and the lower of the two values is adopted.

3. The workability is determined in terms of the slump required for a particular job.

4. The maximum nominal size of the coarse aggregate that is available or desired to be used is determined.

5. The fine and coarse aggregates are so mixed that either the weight per liter of mixed aggregate is maximum or the sand percentage corresponds to the optimum value.

6. By actual trials the quantity of cement in the form of cement paste required per unit volume of aggregate to give the desired slump is determined.

7. ~~The~~ proportions of cement, fine aggregate, coarse aggregate and water to meet the requirements of strength, durability, workability and economy are computed and concrete cubes are cast and tested after the required period of curing for the compressive strength.

8. The trial mix is adjusted, if necessary, by varying the water-cement ratio or the aggregate-cement ratio to suit the actual requirements of the job.

Design Parameters:

Target consistency (workability) of fresh concrete  
IS 206 permits specification by slump class as per the

normal working range be increasing to 200 mm slump and by other test methods, where confidence other than slump is specified, it is recommended that a relationship between the two is established.

Characteristic compressive strength:

As discussed earlier, EN 206 classifies strength in terms of 28 day characteristic strength on the basis of cylinders and cubes, e.g. C25/19 where the first number is the strength of a 150 mm (diameter) x 300 mm (height) cylinder and the second number is the 150 mm cube strength.

However, it should not be presumed that by giving both cube and cylinder strengths a particular relationship is being assumed for purpose of conversion for concrete design or control.

The strength margin factor and the standard deviation can be used for calculation of the target mean corresponding to the strength specified and the degree of safety required. It should be noted that EN 206 takes account of the conformity rules stipulated in EN 206 for strength and for production control. It should be noted that the appropriate margin factor and standard deviation for cylinders may differ from those for cubes.



Design for tensile strength:-

Design for tensile strength can be performed on the basis of compressive strength by first determining the relationship between tensile and compressive strength from concrete trials. The relation is generally modeled as follows.

Target air content of fresh concrete:-

For non-air entrained concrete, air content is not specified but entrapped air is as per considered in design. For EN 206 concrete, for air entrained concrete, EN 206 specifies minimum total air content with a maximum total air content being four percent higher than the specified minimum.

Minimum target cement content and maximum target water-cement ratio:-

EN 206 requires specification of minimum cement and maximum water-cement ratio based on durability considerations which include a set of exposure classes relating to different mechanisms of deterioration.

The main classification, with the exception of XC, each class of exposure is split into a number of subclasses.

In practice, there will always be one or more relevant exposure class.

Exposure class XC exists on its own and there are no requirements for the water-cement ratio or the minimum cement content.

→ The exposure classes and resistive measures list will provide the planner and designer a practically usable basis for identifying relevant exposure classes.

→ An exposure class which requires the grade resistance in the form of the lowest water-cement ratio along with the highest minimum cement content and the highest concrete strength class is selected. However, the minimum cement contents are independent of the type of cement used. EN 126 specifies design margins in the minimum cement content of minus 10 kg and in maximum water-cement ratio plus 0.02 for trial batch tests.

Additions (admixtures):

EN 126 contains provisions for the use of Type 1 (neatly wet) additions and type 2 (reactive or latent hydraulic) additions. The effect of additions on water demand, strength and on the restrictions placed upon their use in specifications is taken into account. EN 126 specifications for durability allow to count the proportion (k) of addition in the combinations with cement towards satisfying specified limits for minimum cement content and maximum water-cement ratio. Here, the factor

k called the efficiency or strength factor of the addition is relative strength of addition with respect to the control. Some additions are allowed to be used fully towards durability provided special tests of the combinations have been made.

Mean size of Aggregate:-

A new series of standard sieve sizes for calculating mean sizes of aggregate for concrete has been recommended.

The designations are established from the nominal lower and upper sieve sizes for the particular aggregate, the lower size being stated first. For example, an aggregate of maximum nominal size of 10mm, is designated as  $\frac{4.75}{10}$ . The maximum aggregate sizes recommended are 10mm, 20mm and 40mm.

Procedure for concrete design

The method is suitable for the design of normal concrete having 28-day compressive strength as high as 45 MPa for non-air-entrained concretes. The method is also suitable for the design of concrete containing pulverised fuel ash (fly ash) and GGBFS. The concrete design is carried out in the following six steps described in the structure given on page 1.

1) Selection of fresh water cement ratio

a) The target mean strength is obtained by adding a margin to the stipulated characteristic strength. The


margin is either specified or calculated for a given proportion of defectives and statistical standard deviation.

(v) If an entrainment is specified, the suitably raised modified target mean strength is calculated.

(vi) The maximum free water-cement ratio is either specified or selected which will provide the target mean strength for concrete made from the given type of coarse aggregate and cement.

The procedure is as Follows :-

For the given type of cement and aggregate, the compressive strength at the specified age corresponding to the reference water-cement ratio 0.50 is obtained from Table 10.1.5. For example when normal portland cement and uncrushed aggregate are used, the compressive strength is 72 MPa at 28 days. With this pair of data (72 MPa and water-cement ratio = 0.50) as a controlling

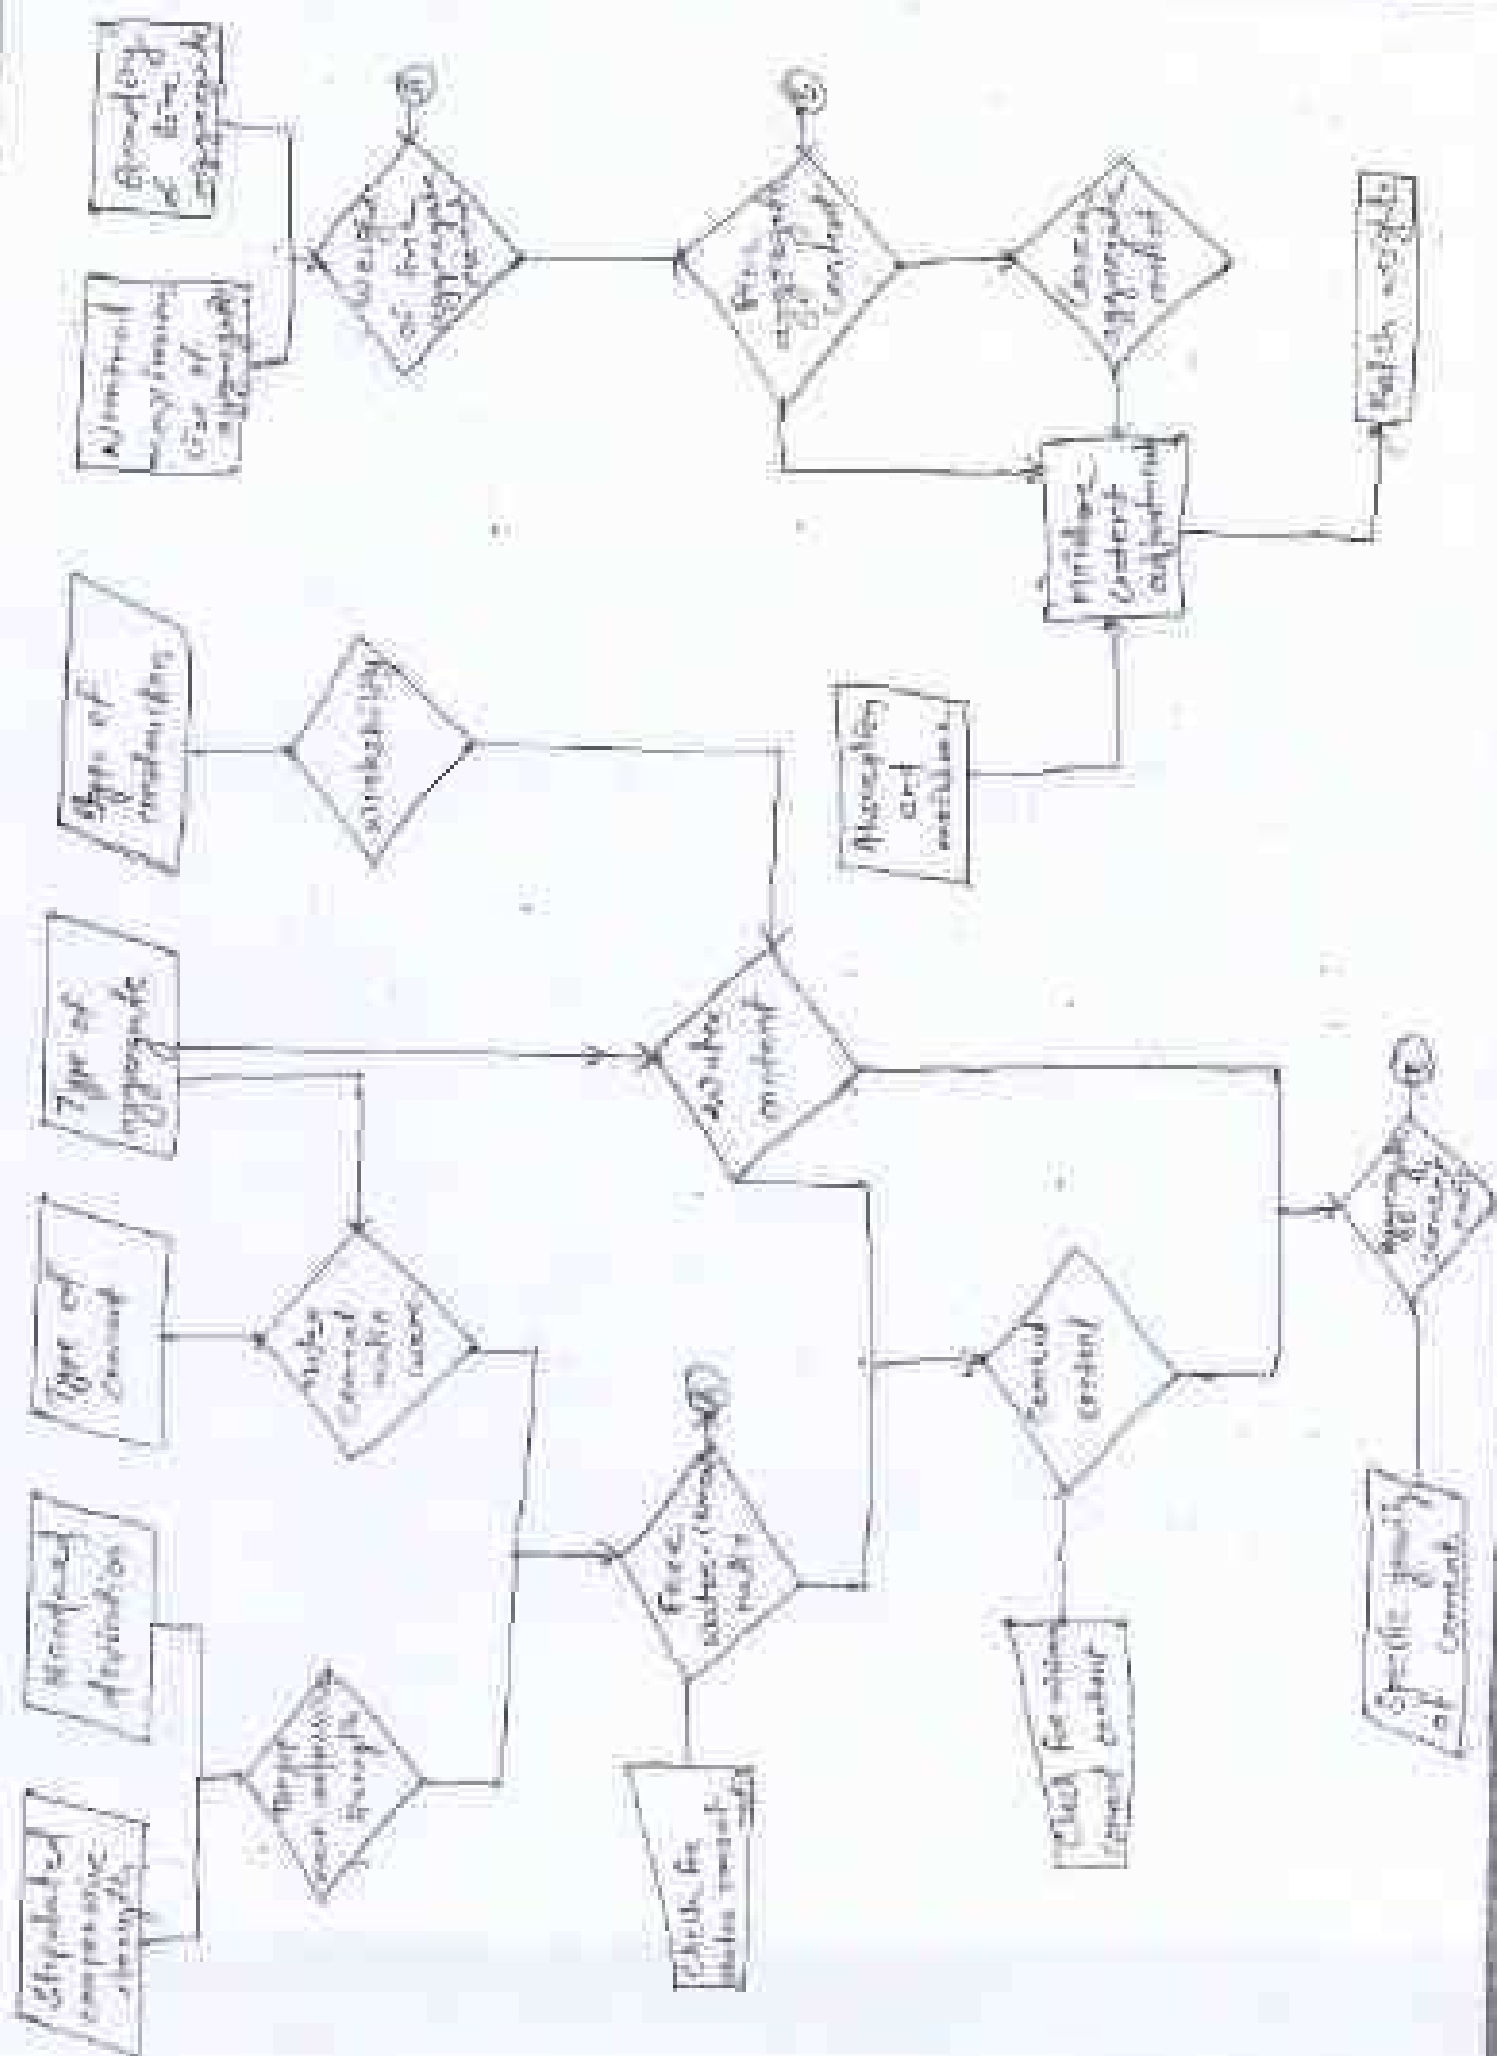

## → Establishing common goal

Incompatible goal may be a major reason for the development of conflict. The main strategy of reducing the conflict should be to find common goals upon which the groups agree and establish valid communication between the groups.

## 1) Conflict in Interdependence

Interdependence may be the major reason for intergroup conflict among the line and staff managers. The less is the interdependence, the less will be the amount of conflict among them.

## 2) Trust and communication

When the trust among the employees increases, then there will be more open and honest communication. The trust makes the individuals and groups to communicate openly with each other, so that the misunderstanding can be removed. They are encouraged to understand the problems of each other whenever necessary.

## 3) Co-ordination :-

Co-ordination is an important step for resolving the conflict and also it is the next step after communication. If proper co-ordinating activity can reduce the conflict. If there is a good co-ordination among the employees, then they will be able to solve the problems themselves and help each other.

## 4) Use of superior authority

When the conflict can't be resolved by two organizational members or by two groups, it should be referred to a common superior who will resolve the conflict to their